

Cite this: *Phys. Chem. Chem. Phys.*, 2013, **15**, 13538

## CO<sub>2</sub> capture properties of lithium silicates with different ratios of Li<sub>2</sub>O/SiO<sub>2</sub>: an *ab initio* thermodynamic and experimental approach†

Yuhua Duan,<sup>\*a</sup> Heriberto Pfeiffer,<sup>b</sup> Bingyun Li,<sup>ac</sup> Issis C. Romero-Ibarra,<sup>b</sup> Dan C. Sorescu,<sup>a</sup> David R. Luebke<sup>a</sup> and J. Woods Halley<sup>d</sup>

The lithium silicates have attracted scientific interest due to their potential use as high-temperature sorbents for CO<sub>2</sub> capture. The electronic properties and thermodynamic stabilities of lithium silicates with different Li<sub>2</sub>O/SiO<sub>2</sub> ratios (Li<sub>2</sub>O, Li<sub>8</sub>SiO<sub>6</sub>, Li<sub>4</sub>SiO<sub>4</sub>, Li<sub>6</sub>Si<sub>2</sub>O<sub>7</sub>, Li<sub>2</sub>SiO<sub>3</sub>, Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub>, Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub>, and α-SiO<sub>2</sub>) have been investigated by combining first-principles density functional theory with lattice phonon dynamics. All these lithium silicates examined are insulators with band-gaps larger than 4.5 eV. By decreasing the Li<sub>2</sub>O/SiO<sub>2</sub> ratio, the first valence bandwidth of the corresponding lithium silicate increases. Additionally, by decreasing the Li<sub>2</sub>O/SiO<sub>2</sub> ratio, the vibrational frequencies of the corresponding lithium silicates shift to higher frequencies. Based on the calculated energetic information, their CO<sub>2</sub> absorption capabilities were extensively analyzed through thermodynamic investigations on these absorption reactions. We found that by increasing the Li<sub>2</sub>O/SiO<sub>2</sub> ratio when going from Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub> to Li<sub>8</sub>SiO<sub>6</sub>, the corresponding lithium silicates have higher CO<sub>2</sub> capture capacity, higher turnover temperatures and heats of reaction, and require higher energy inputs for regeneration. Based on our experimentally measured isotherms of the CO<sub>2</sub> chemisorption by lithium silicates, we found that the CO<sub>2</sub> capture reactions are two-stage processes: (1) a superficial reaction to form the external shell composed of Li<sub>2</sub>CO<sub>3</sub> and a metal oxide or lithium silicate secondary phase and (2) lithium diffusion from bulk to the surface with a simultaneous diffusion of CO<sub>2</sub> into the shell to continue the CO<sub>2</sub> chemisorption process. The second stage is the rate determining step for the capture process. By changing the mixing ratio of Li<sub>2</sub>O and SiO<sub>2</sub>, we can obtain different lithium silicate solids which exhibit different thermodynamic behaviors. Based on our results, three mixing scenarios are discussed to provide general guidelines for designing new CO<sub>2</sub> sorbents to fit practical needs.

Received 18th April 2013,  
Accepted 5th June 2013

DOI: 10.1039/c3cp51659h

www.rsc.org/pccp

### 1. Introduction

During the past few decades, lithium silicates and zirconates have been extensively investigated as CO<sub>2</sub> sorbents in an attempt to alleviate the consequences of global warming.<sup>1–30</sup>

Nakagawa and Ohashi<sup>12,13</sup> reported a novel method to capture CO<sub>2</sub> from high-temperature gases through the reversible reaction of Li<sub>2</sub>ZrO<sub>3</sub> + CO<sub>2</sub> ↔ ZrO<sub>2</sub> + Li<sub>2</sub>CO<sub>3</sub>. Later, a similar reaction mechanism Li<sub>4</sub>SiO<sub>4</sub> + CO<sub>2</sub> ↔ Li<sub>2</sub>SiO<sub>3</sub> + Li<sub>2</sub>CO<sub>3</sub> was reported for the Li<sub>4</sub>SiO<sub>4</sub> case.<sup>7,8,11,16–19</sup> It has been found that Li<sub>4</sub>SiO<sub>4</sub> maintains its CO<sub>2</sub> absorption effectiveness during cycling between absorption at 973 K and regeneration at 1123 K in the case of pure CO<sub>2</sub> at a total pressure of 1.0 × 10<sup>5</sup> Pa.<sup>4,7</sup> Following this pioneering work, several other studies have been published on the possibility of using lithium ceramics to separate CO<sub>2</sub> and N<sub>2</sub>. Venegas *et al.*<sup>17</sup> pointed out that Li<sub>2</sub>SiO<sub>3</sub> could further react with CO<sub>2</sub> through the reaction Li<sub>2</sub>SiO<sub>3</sub> + CO<sub>2</sub> ↔ SiO<sub>2</sub> + Li<sub>2</sub>CO<sub>3</sub> and in doing so make Li<sub>4</sub>SiO<sub>4</sub> a more efficient sorbent. Kato *et al.*<sup>7,8</sup> compared Li<sub>4</sub>SiO<sub>4</sub> with Li<sub>2</sub>ZrO<sub>3</sub> and found that at 500 °C and in an atmosphere containing 20% CO<sub>2</sub> gas, the weight increase of Li<sub>4</sub>SiO<sub>4</sub> was about 50% greater than that

<sup>a</sup> National Energy Technology Laboratory, United States Department of Energy, 236 Cochran Mill Road, Pittsburgh, Pennsylvania 15236, USA.

E-mail: yuhua.duan@netl.doe.gov; Fax: +1 412-386-5990; Tel: +1 412-386-5771

<sup>b</sup> Instituto de Investigaciones en Materiales, Universidad Nacional Autónoma de México, Circuito Exterior s/n, Cd Universitaria, Del. Coyoacan, CP 04510, México DF, Mexico

<sup>c</sup> School of Medicine, West Virginia University, Morgantown, West Virginia 26506, USA

<sup>d</sup> School of Physics and Astronomy, University of Minnesota, Minneapolis, Minnesota 55455, USA

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c3cp51659h

of  $\text{Li}_2\text{ZrO}_3$ . Additionally,  $\text{Li}_4\text{SiO}_4$  was found to absorb  $\text{CO}_2$  more than 30 times faster than  $\text{Li}_2\text{ZrO}_3$ . Sodium-based oxides have also been used either as low-temperature ( $T < 250^\circ\text{C}$ )  $\text{CO}_2$  sorbents or as promoters for lithium-based acceptors. Lopez-Ortiz *et al.*<sup>9</sup> reported the use of Na-based sorbents at high temperatures as an alternative to lithium-based  $\text{CO}_2$  sorbents, and their results showed that Na-ceramics are able to capture  $\text{CO}_2$  at  $600^\circ\text{C}$  and are candidates to compete with  $\text{Li}_4\text{SiO}_4$  and  $\text{Li}_2\text{ZrO}_3$ . Essaki *et al.*<sup>2–4</sup> concluded that the  $\text{CO}_2$  absorption properties of  $\text{Li}_4\text{SiO}_4$  pellets are strongly affected by the absorption temperature. Between  $550^\circ\text{C}$  and  $600^\circ\text{C}$ ,  $\text{Li}_4\text{SiO}_4$  shows the most rapid  $\text{CO}_2$  absorption. Above  $600^\circ\text{C}$ , it absorbs only a very small amount of  $\text{CO}_2$ . Gauer and Heschel<sup>5</sup> as well as Ortiz-Landeros and coworkers<sup>31</sup> demonstrated that doping in  $\text{Li}_4\text{SiO}_4$  with vacancies or hetero elements can enhance its  $\text{CO}_2$  absorption at moderate temperature. Venegas *et al.*<sup>17</sup> investigated the effect of particle size upon  $\text{CO}_2$  absorption by  $\text{Li}_4\text{SiO}_4$  and found that this may influence the stability of the  $\text{Li}_4\text{SiO}_4$  particles during the  $\text{CO}_2$  sorption-desorption cycles, and lithium sublimation as  $\text{Li}_2\text{O}$  takes place on small particles. Yamaguchi *et al.*<sup>19</sup> made  $\text{Li}_4\text{SiO}_4$  membranes from powders and performed measurements of  $\text{CO}_2$  separation. Using such membranes, they obtained a separation factor of 5.5 for  $\text{CO}_2$  and  $\text{N}_2$  at a temperature of  $525^\circ\text{C}$ . Using thermogravimetric analysis (TGA), Okumura *et al.*<sup>14</sup> investigated  $\text{CO}_2$  absorption in  $\text{Li}_4\text{SiO}_4$  and found that it corresponds to a pseudo first order reaction. They estimated activation energies of about  $115\text{ kJ mol}^{-1}$  in the  $620\text{--}660^\circ\text{C}$  region and about  $56\text{ kJ mol}^{-1}$  in the  $680\text{--}700^\circ\text{C}$  region. The large differences among these activation energies were associated with the different surface states of the  $\text{Li}_4\text{SiO}_4$  particle. Olivares-Marin *et al.*<sup>15</sup> investigated  $\text{Li}_4\text{SiO}_4$ -based sorbents made from fly ashes for  $\text{CO}_2$  capture at high temperature. Recently, Durán-Muñoz *et al.*<sup>32</sup> explored the  $\text{CO}_2$  capture properties of a high lithium-content silicate ( $\text{Li}_8\text{SiO}_6$ ) and found that it could absorb  $\text{CO}_2$  over a wide range of temperatures and has a maximum capacity of  $11.8\text{ mmol CO}_2$  per gram of  $\text{Li}_8\text{SiO}_6$ . They also found that its  $\text{CO}_2$  capture mechanism depends on the reaction temperature.

To date, the mechanisms of these reversible reactions for lithium silicates capturing  $\text{CO}_2$  are still unclear. Essaki *et al.*<sup>4</sup> proposed a reaction model for  $\text{CO}_2$  absorption by lithium silicate at room temperature. In the model, the  $\text{CO}_2$  reacts with  $\text{Li}_2\text{O}$  in  $\text{Li}_4\text{SiO}_4$  to form  $\text{Li}_2\text{CO}_3$ . If  $\text{H}_2\text{O}$  is also present,  $\text{CO}_2$  and  $\text{Li}_2\text{O}$  will first hydrolyze, and then form  $\text{Li}_2\text{CO}_3$ . Recently, Rodríguez-Mosqueda and Pfeiffer<sup>16</sup> evaluated the  $\text{CO}_2$  chemisorption capacity of  $\text{Li}_4\text{SiO}_4$  as a function of  $\text{CO}_2$  flow rate and sorbent particle size. Their results showed that at low  $\text{CO}_2$  flows  $\text{CO}_2$  capture is controlled by  $\text{CO}_2$  diffusion through the gas-film system, whereas at high  $\text{CO}_2$  flows it is controlled by the  $\text{CO}_2$  chemisorption reaction rate. After formation of the carbonate-oxide external shell, the whole  $\text{CO}_2$  capture process is controlled kinetically by lithium diffusion. However, they failed to explain how  $\text{CO}_2$  diffuses into the shell and the  $\text{Li}_2\text{O}$  (in the form of  $\text{Li}^+$  and  $\text{O}^{2-}$ ) diffuses out of  $\text{Li}_4\text{SiO}_4$  to further form carbonate. Mosqueda *et al.*<sup>10</sup> investigated the chemical sorption of  $\text{CO}_2$  on  $\text{Li}_2\text{O}$  and found that in order to continue to form  $\text{Li}_2\text{CO}_3$ ,

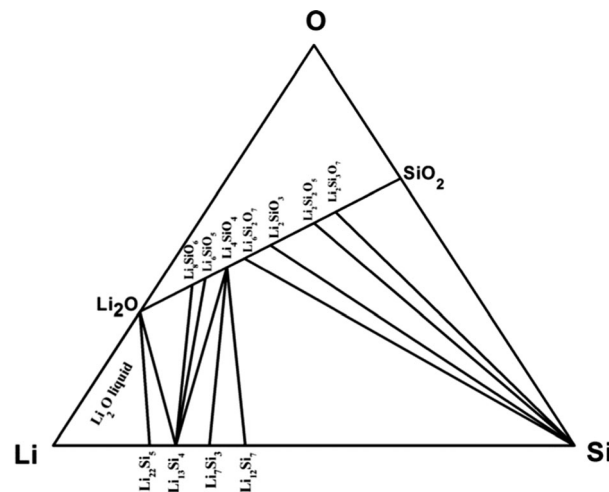


Fig. 1 Illustrative phase diagram of the ternary system Li-Si-O at high temperatures ( $>700\text{ K}$ ) obtained based on data in ref. 33–36.

the lithium has to migrate and cross the  $\text{Li}_2\text{CO}_3$  shell. Such diffusion is topochemical and is promoted by temperature. A similar double shell model was also used to describe the  $\text{Li}_2\text{ZrO}_3$  sorbent.<sup>6,18</sup> However, to date it is not yet known how the  $\text{Li}_4\text{SiO}_4$  structure is changed upon  $\text{CO}_2$  absorption to form  $\text{Li}_2\text{CO}_3$  with  $\text{Li}_2\text{SiO}_3$  or  $\text{SiO}_2$  and how the  $\text{Li}_2\text{O}$  component of  $\text{Li}_4\text{SiO}_4$  is extracted and reacts with  $\text{CO}_2$ . Cruz *et al.*<sup>1</sup> analyzed the thermal decomposition of  $\text{Li}_4\text{SiO}_4$  and  $\text{Li}_2\text{SiO}_3$ . By lithium sublimation,  $\text{Li}_4\text{SiO}_4$  begins to decompose between  $900$  and  $1000^\circ\text{C}$ , while  $\text{Li}_2\text{SiO}_3$  was highly stable. However, the nature of the intermediates involved in this structural transformation is not clear. Actually, from the phase diagram of the  $\text{Li}_2\text{O}$ - $\text{SiO}_2$  binary system made by Kracek,<sup>35</sup> it can be seen that different lithium silicate compositions can be formed as a function of  $\text{SiO}_2$  percentage and the external temperature. Such a phase diagram corresponding to the Li-Si-O system at high temperature is summarized in Fig. 1.<sup>33–36</sup> Based on Kracek's work, Claus *et al.*<sup>36</sup> investigated the phase equilibria in the  $\text{Li}_4\text{SiO}_4$ - $\text{Li}_2\text{SiO}_3$  region of the pseudo binary  $\text{Li}_2\text{O}$ - $\text{SiO}_2$  system at temperatures between  $1000$  and  $1300^\circ\text{C}$ . Above  $1000^\circ\text{C}$ , with increasing percentage of  $\text{SiO}_2$ , as shown in Fig. 1, several different lithium silicate phases can exist, e.g.  $\text{Li}_8\text{SiO}_6$ ,  $\text{Li}_4\text{SiO}_4$ ,  $\text{Li}_6\text{Si}_2\text{O}_7$ ,  $\text{Li}_2\text{SiO}_3$ ,  $\text{Li}_2\text{Si}_2\text{O}_5$ , and  $\text{Li}_3\text{Si}_2\text{O}_7$ . Between  $\text{Li}_8\text{SiO}_6$  and  $\text{Li}_4\text{SiO}_4$ , and between  $\text{Li}_2\text{Si}_2\text{O}_5$  and  $\text{SiO}_2$ , there are also a number of meta-stable intermediate phases such as  $\text{Li}_6\text{SiO}_5$  and  $\text{Li}_2\text{Si}_3\text{O}_7$ .<sup>33,34,37</sup> Obviously,  $\text{Li}_6\text{Si}_2\text{O}_7$  could be one of the intermediates between  $\text{Li}_4\text{SiO}_4$  and  $\text{Li}_2\text{SiO}_3$  as it could be formed through the transition reaction  $\text{Li}_6\text{Si}_2\text{O}_7 \leftrightarrow \text{Li}_4\text{SiO}_4 + \text{Li}_2\text{SiO}_3$ .

In the literature there are only limited theoretical studies on the electronic structures of crystalline lithium silicates. By employing an orthogonalized linear combination of atomic orbitals method (OLCAO), Ching *et al.*<sup>38</sup> calculated the electronic structures of  $\text{Li}_2\text{SiO}_3$  and  $\text{Li}_2\text{Si}_2\text{O}_5$  and compared them with XPS measurements. Their results showed that the effective charge on Li is quite small ( $0.07$  in  $\text{Li}_2\text{SiO}_3$ , and  $0.02$  in  $\text{Li}_2\text{Si}_2\text{O}_5$ ). With an *ab initio* approach, Uchino and Yoko<sup>39,40</sup> investigated the local coordination environments of the alkali cations ( $\text{Li}^+$  and  $\text{Na}^+$ ) in

the cluster model of single- and mixed-alkali silicate glasses. Their results demonstrated that the average coordination number of alkali cations increased from Li to Na and each alkali cation is located in individual local sites in both single- and mixed-alkali clusters. Munakata and Yokoyama<sup>41</sup> calculated the electronic structure of  $\text{Li}_4\text{SiO}_4$  and obtained a band gap of 17.5 eV. Du and Corrales<sup>42–44</sup> employed density functional theory to characterize the structural and electronic properties of alkali silicate glasses ( $\text{M}_2\text{O}$ ,  $\text{M} = \text{Li}$ ,  $\text{Na}$ ,  $\text{K}$ ),  $\text{Li}_2\text{SiO}_3$ , and  $\text{Li}_2\text{Si}_2\text{O}_5$ . Their results revealed that there are clear differences in the band structure corresponding to the bridging and non-bridging oxygen ions. To the best of our knowledge no theoretical analysis of the electronic properties of  $\text{Li}_8\text{SiO}_6$  and  $\text{Li}_6\text{Si}_2\text{O}_7$  has been reported to date. In our previous studies,<sup>23,30,45</sup> we have investigated the structural, electronic and thermodynamic properties of  $\text{Li}_2\text{O}$  and  $\text{Li}_2\text{CO}_3$  and the reaction of  $\text{Li}_2\text{O} + \text{CO}_2 \leftrightarrow \text{Li}_2\text{CO}_3$ , and concluded that although  $\text{Li}_2\text{O}$  is efficient to absorb  $\text{CO}_2$ , by comparison with other lithium salts (such as  $\text{Li}_4\text{SiO}_4$ ,  $\text{Li}_2\text{ZrO}_3$ , etc.) it is still not a good  $\text{CO}_2$  sorbent due to the large energetic requirements involved in the reverse reaction ( $\text{Li}_2\text{CO}_3 \rightarrow \text{Li}_2\text{O} + \text{CO}_2$ ). We also investigated the thermodynamic properties of two phases of  $\text{Li}_4\text{SiO}_4$  and found that the thermodynamic properties of these two phases are similar while their optical properties are different.<sup>23</sup> Overall, it was found that the  $\text{CO}_2$  capture performances of  $\text{Li}_4\text{SiO}_4$  are better than those of lithium zirconates.<sup>23</sup>

For these alkali silicates to capture  $\text{CO}_2$ , their necessary regeneration temperatures are very high (>900 K). Such operating temperatures are outside the normal operating range for pre-combustion  $\text{CO}_2$  capture systems, which normally operate at temperatures of 260–500 °C for concurrent water-gas-shift/separation and 40–260 °C for post water-gas-shift separation. Our previous studies already showed that the  $\text{CO}_2$  capture temperature of pure  $\text{Li}_2\text{O}$  is higher than the corresponding ones for the silicate ( $\text{Li}_4\text{SiO}_4$ ) and zirconate ( $\text{Li}_2\text{ZrO}_3$ ).<sup>23,24,30,45</sup> Because the lithium silicates are made by  $\text{Li}_2\text{O}$  and  $\text{SiO}_2$ , where  $\text{SiO}_2$  is a very weak  $\text{CO}_2$  sorbent while  $\text{Li}_2\text{O}$  is a strong  $\text{CO}_2$  sorbent, it becomes scientifically relevant to analyze the sorption properties of these mixed types of materials. As a result we have conducted further investigations to develop  $\text{CO}_2$  sorbents, which could work at the desired operating temperature for pre- or post-combustion  $\text{CO}_2$  capture technologies, by mixing weak and strong  $\text{CO}_2$  sorbents with different ratios. In this study, we focus on the structural and electronic properties of a series of lithium silicates ( $\text{Li}_8\text{SiO}_6$ ,  $\text{Li}_4\text{SiO}_4$ ,  $\text{Li}_6\text{Si}_2\text{O}_7$ ,  $\text{Li}_2\text{SiO}_3$ ,  $\text{Li}_2\text{Si}_2\text{O}_5$ , and  $\text{Li}_2\text{Si}_3\text{O}_7$ ) and try to understand the phase evolution  $\text{Li}_2\text{O} \leftrightarrow \text{Li}_8\text{SiO}_6 \leftrightarrow \text{Li}_4\text{SiO}_4 \leftrightarrow \text{Li}_6\text{Si}_2\text{O}_7 \leftrightarrow \text{Li}_2\text{SiO}_3 \leftrightarrow \text{Li}_2\text{Si}_2\text{O}_5 \leftrightarrow \text{Li}_2\text{Si}_3\text{O}_7 \leftrightarrow \text{SiO}_2$  by increasing the percentage of  $\text{SiO}_2$ . Particular attention has been paid to the phase transformations  $\text{Li}_4\text{SiO}_4 \leftrightarrow \text{Li}_6\text{Si}_2\text{O}_7 \leftrightarrow \text{Li}_2\text{SiO}_3$  and  $\text{Li}_2\text{SiO}_3 \leftrightarrow \text{Li}_2\text{Si}_2\text{O}_5 \leftrightarrow \text{SiO}_2$ , which are the key structural transformations for the  $\text{Li}_4\text{SiO}_4$  sorbent during  $\text{CO}_2$  sorption-desorption cycles. In contrast to the lithium ion transport problem in a lithium-ion battery, we are interested in the migration mechanism of  $\text{Li}_2\text{O}$  from lithium silicates because the  $\text{Li}_2\text{O}$  (as  $\text{Li}^+$  and  $\text{O}^{2-}$ ) group

is responsible for the  $\text{CO}_2$  absorption process. We want to explore whether, in this series of lithium silicates, optimal compositions can be identified to be used as  $\text{CO}_2$  capture sorbents in pre- and/or post-combustion technologies.

This paper is organized as follows: in the next two sections we briefly describe the theoretical method and the experimental measurements we employed, in the fourth section we show our results on these crystals and compare them with other available reports, and in the last section we summarize our conclusions.

## 2. Theoretical methods

First-principles density-functional theory (DFT) calculations with plane-wave basis sets and pseudopotential approximation were done to describe the structural, energetic and electronic properties of lithium silicates considered in this study. All calculations were performed using the Vienna *ab initio* simulation package (VASP).<sup>46,47</sup> Similar to our previous tests on proper choice of pseudo-potential and exchange–correlation functions for other solid materials,<sup>45,48–50</sup> in this study, we employ the PAW pseudo-potentials and PW91 exchange–correlation functional in all of the calculations. Plane wave basis sets were used with a kinetic energy cutoff of 520 eV and an augmentation charge cutoff of 605.4 eV. The  $k$ -point sampling grids of  $m \times n \times l$ , obtained using the Monkhorst–Pack method,<sup>51</sup> were used for these bulk calculations, where  $m$ ,  $n$ , and  $l$  were determined with a spacing of about  $0.028 \text{ \AA}^{-1}$  along the reciprocal axes of their unit cells. The corresponding  $k$ -point sampling grid of each solid is listed in Table 1. The valence electrons contained


**Table 1** The experimental crystal structure constants of lithium silicates

Crystal	Lattice constant	Space group and ref.	$\text{Li}_2\text{O}/\text{SiO}_2$ ratio	$k$ -Point grid	f.u. <sup>a</sup>
$\text{Li}_2\text{O}$	$a = 4.573 \text{ \AA}$	$Fm3m$ (no. 225) <sup>66</sup>	1:0	$8 \times 8 \times 8$	4
$\text{Li}_8\text{SiO}_6$	$a = 5.4243 \text{ \AA}$ $c = 10.626 \text{ \AA}$	$P6_3cm$ (no. 185) <sup>60</sup>	4:1	$8 \times 8 \times 4$	2
$\text{Li}_4\text{SiO}_4$	$a = 11.532 \text{ \AA}$ $b = 6.075 \text{ \AA}$ $c = 16.678 \text{ \AA}$ $\beta = 99.04^\circ$	$P2_1/m$ (no. 11) <sup>73</sup>	2:1	$4 \times 6 \times 2$	14
$\text{Li}_6\text{Si}_2\text{O}_7$	$a = 7.71 \text{ \AA}$ $c = 4.88 \text{ \AA}$	$P\bar{4}2_1m$ (no. 113) <sup>61</sup>	3:2	$5 \times 5 \times 8$	2
$\text{Li}_2\text{SiO}_3$	$a = 9.392 \text{ \AA}$ $b = 5.397 \text{ \AA}$ $c = 4.660 \text{ \AA}$	$Cmc2_1$ (no. 36) <sup>62,63</sup>	1:1	$4 \times 8 \times 8$	4
$\text{Li}_2\text{Si}_2\text{O}_5$	$a = 5.82 \text{ \AA}$ $b = 14.66 \text{ \AA}$ $c = 4.79 \text{ \AA}$ $\beta = 90^\circ$	$Ccc2$ (no. 37) <sup>64</sup>	1:2	$6 \times 3 \times 8$	4
meta- $\text{Li}_2\text{Si}_2\text{O}_5$	$a = 5.683 \text{ \AA}$ $b = 4.784 \text{ \AA}$ $c = 14.648 \text{ \AA}$	$Pbcn$ (no. 60) <sup>65</sup>	1:2	$7 \times 8 \times 3$	4
$\text{Li}_2\text{Si}_3\text{O}_7$	$a = 19.648 \text{ \AA}$ $b = 5.9969 \text{ \AA}$ $c = 4.8691 \text{ \AA}$	$Pmca$ (no. 57) <sup>37</sup>	1:3	$3 \times 7 \times 8$	4
$\alpha\text{-SiO}_2$	$a = 4.8992 \text{ \AA}$ $c = 5.3832 \text{ \AA}$ $\gamma = 120^\circ$	$P3_121$ (no. 154) <sup>72</sup>	0:1	$8 \times 8 \times 8$	3

<sup>a</sup> The f.u. acronym stands for formula unit.

the s and p orbitals for Li, C, O, and Si atoms. During optimizations all atoms in the cell were allowed to relax. For band structure calculations, the symbols and coordinates of the high symmetrical points in the crystals were taken from Bradley and Cracknell's definitions.<sup>52</sup>

The CO<sub>2</sub> capture reactions of solids can be expressed generically in the form (for convenient description, we normalized the reaction to 1 mole of CO<sub>2</sub>)



where  $n_{R_i}$ ,  $n_{P_j}$  are the numbers of moles of reactants ( $R_i$ ) and products ( $P_j$ ) involved in the capture reactions. We treat the gas phase CO<sub>2</sub> as an ideal gas. By assuming that the difference between the chemical potentials ( $\Delta\mu^0$ ) of the solid phases of reactants ( $R_i$ ) and products ( $P_j$ ) can be approximated by the difference in their total energies ( $\Delta E^{\text{DFT}}$ ), obtained directly from DFT calculations, and the vibrational free energy of the phonons and by ignoring the PV contribution terms for solids, the variation of the chemical potential ( $\Delta\mu$ ) for reaction (a) with temperature and pressure can be written as<sup>45,48–50,53,54</sup>

$$\Delta\mu(T, P) = \Delta\mu^0(T) - RT \ln \frac{P_{\text{CO}_2}}{P_0} \quad (1)$$

where

$$\Delta\mu^0(T) \approx \Delta E^{\text{DFT}} + \Delta E_{\text{ZP}} + \Delta F^{\text{PH}}(T) - G_{\text{CO}_2}^0(T) \quad (2)$$

Here,  $\Delta E^{\text{DFT}}$  is the DFT energy difference between the reactants and products of the reaction (a),  $\Delta E_{\text{ZP}}$  is the zero point energy difference between the reactants and products and can be obtained directly from phonon calculations.  $\Delta F^{\text{PH}}$  is the phonon free energy change excluding zero-point energy (which is already counted into the  $\Delta E_{\text{ZP}}$  term) between the solids of products and reactants.  $P_{\text{CO}_2}$  is the partial pressure of CO<sub>2</sub> in the gas phase and  $P_0$  is the standard state reference pressure taken to be 1 bar. The heat of reaction ( $\Delta H^{\text{cal}}(T)$ ) can be evaluated through the following equation:

$$\Delta H^{\text{cal}}(T) = \Delta\mu^0(T) + T[\Delta S_{\text{PH}}(T) - S_{\text{CO}_2}(T)] \quad (3)$$

where  $\Delta S_{\text{PH}}(T)$  is the difference of entropies between product solids and reactant solids. The free energy of CO<sub>2</sub> ( $G_{\text{CO}_2}^0$ ) can be obtained from standard statistical mechanics,<sup>45,49,55</sup> and its entropy ( $S_{\text{CO}_2}$ ) can be found in the empirical thermodynamic databases as follows:<sup>56</sup>

$$G_{\text{CO}_2}^0(T) = \frac{7}{2}RT + \sum_{i=1}^4 \frac{N_a h \nu_i}{e^{h\nu_i/kT} - 1} - TS_{\text{CO}_2}(T) \quad (4)$$

$$S_{\text{CO}_2}(T) = A \ln(t) + Bt + C \frac{t^2}{2} + D \frac{t^3}{3} + \frac{E}{2t^2} + G \quad (5)$$

where  $N_a$  is the Avogadro constant, the vibrational frequencies ( $\nu_i$ ) of the CO<sub>2</sub> molecule are 673 cm<sup>−1</sup> ( $\pi_u$ ), 1354 cm<sup>−1</sup> ( $\sigma_g^+$ ), and 2397 cm<sup>−1</sup> ( $\sigma_u^+$ ), from which the zero-point energy of a CO<sub>2</sub> molecule is obtained with a value of 0.316 eV and included in eqn (2),<sup>45,49</sup>  $t = T/1000$ , and the remaining parameters ( $A$ ,  $B$ ,  $C$ ,  $D$ ,  $E$ ,  $G$ ) can be found from ref. 30 and 56.

The “grand-canonical” Gibbs free energy  $G'$  of multi-component systems of all lithium silicates in contact with a CO<sub>2</sub> gas-phase reservoir can be written as (see additional details in the Appendix)<sup>50,55,57,58</sup>

$$G'(T, \mu_g^{\text{CO}_2}) = \sum_j^{p-1} x_j F_j(T) - \mu_g^{\text{CO}_2}(T, p) \sum_j^{p-1} x_j n_j^c \quad (6)$$

where  $F_j(T)$  is the free energy of the solid phase “j” ( $F_j(T) = E^{\text{DFT}} + F^{\text{PH}}(T)$ , ignoring the PV term contribution),  $p$  is the number of phases (solid substances and gas phase),  $x_j$  is the unknown mole fraction of phase  $j$  coexisting at a given composition, temperature, and pressure. The molar fractions  $x_j$  are based on elements appearing only as solids and are determined by minimizing the grand-canonical Gibbs free energy, subject to the following mass-conservation constraints for the solid phase species:<sup>57</sup>

$$f_i = \sum_j^{p-1} x_j^{\text{solid}} n_i^{j,\text{solid}} = \text{constant} \quad (7)$$

for any element  $i$  in a solid except carbon (C in eqn (6)), where  $f_i$  is the molar ratio of solid element  $i$  and is normalized to obey  $\sum_{i=1}^M f_i = 1$ ,  $n_i^{j,\text{solid}}$  represents the number of atoms of type  $i$  in one formula unit of phase  $j$ , and  $M$  is the number of elements. The minimization of  $G$  as given in eqn (6) as a function of  $x_j$  and subject to the constraints eqn (7) is a linear programming problem which can be solved using standard techniques.<sup>59</sup> The conditions under which a chemical reaction occurs can be identified by comparing the molar fractions  $x_j$  at two consecutive temperature or pressure steps. If the  $x_j$  values change then a reaction occurs between the successive temperature or pressure steps. The change in the Gibbs free energy of the system due to a reaction is zero at thermodynamic equilibrium and can be calculated by setting  $\Delta\mu(T, P) = 0$  in eqn (1).

### 3. Experimental

Different thermokinetic analyses and CO<sub>2</sub> chemisorptions were performed using a Q500HR instrument from TA Instruments. Several lithium silicates (Li<sub>8</sub>SiO<sub>6</sub>, Li<sub>4</sub>SiO<sub>4</sub> and Li<sub>2</sub>SiO<sub>3</sub>, synthesized by solid-state reaction<sup>1,22,31,32</sup>) and lithium oxide (Li<sub>2</sub>O, Aldrich) were tested dynamically and isothermally in the presence of a CO<sub>2</sub> flow (Praxair grade 3.0 at 60 mL min<sup>−1</sup>). Dynamic thermogravimetric analysis (TGA) experiments were performed at 5 °C min<sup>−1</sup> from 30 to 800 °C, while specific isothermal analyses were performed at 600 °C. To avoid a previous carbonation process, samples were initially heated using a N<sub>2</sub> flow (Praxair grade 4.8, at 60 mL min<sup>−1</sup>). Thus, once the experimental temperature (600 °C) was reached, the flow gas was switched to CO<sub>2</sub> and the isothermal mass gain experiments were carried out using a CO<sub>2</sub> gas flow.

## 4. Results and discussions

### 4.1 Crystalline structures of lithium silicates

According to the phase diagram of the ternary Li–Si–O system illustrated in Fig. 1, one can see that with different Li<sub>2</sub>O to SiO<sub>2</sub> ratios, several Li–Si–O crystalline phases can be formed. For Li<sub>2</sub>O, the SiO<sub>2</sub>/Li<sub>2</sub>O ratio is zero and becomes 1.0 for Li<sub>2</sub>SiO<sub>3</sub>. Li<sub>8</sub>SiO<sub>6</sub>, Li<sub>4</sub>SiO<sub>4</sub>, and Li<sub>6</sub>Si<sub>2</sub>O<sub>7</sub> have more Li<sub>2</sub>O than SiO<sub>2</sub> as their Li<sub>2</sub>O/SiO<sub>2</sub> ratios are greater than 1.0, while Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub> and Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub> have more SiO<sub>2</sub> than Li<sub>2</sub>O due to their Li<sub>2</sub>O/SiO<sub>2</sub> ratios less than 1.0. The crystal structures of these silicates are shown in Fig. 2 and their corresponding experimental crystallographic structural data are summarized in Table 1.

As shown in Fig. 2(a), Li<sub>8</sub>SiO<sub>6</sub> has a hexagonal structure with space group *P*6<sub>3</sub>*cm* (no. 185).<sup>60</sup> As discussed in our previous study,<sup>23</sup> lithium orthosilicate (Li<sub>4</sub>SiO<sub>4</sub>) usually is found in a monoclinic structure with space group *P*2<sub>1</sub>/*m* (no. 11), but it also has another phase ( $\gamma$ -Li<sub>4</sub>SiO<sub>4</sub>) which is in triclinic structure with space group *P* $\bar{1}$  (no. 2). As shown in Fig. 2(b), the crystal structure of Li<sub>6</sub>Si<sub>2</sub>O<sub>7</sub> is tetragonal with space group *P*4<sub>2</sub>*m*-*D*<sub>2d</sub><sup>3</sup> (no. 113).<sup>61</sup> It belongs to the class of sorosilicates having isolated [Si<sub>2</sub>O<sub>7</sub>]-groups. As shown in Fig. 2(c), lithium catenasilicate (Li<sub>2</sub>SiO<sub>3</sub>) is in an orthorhombic structure with space group *Cmc*2<sub>1</sub> (no. 36).<sup>62,63</sup> As one can see from Fig. 2(c) in this structure, the tetrahedra form chains parallel to [001] with two tetrahedra in the identity period. Lithium is tetrahedrally coordinated with a mean Li–O distance of 2.0 Å. Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub> has two kinds of structures as shown in Fig. 2(e) and (f): monoclinic with space group *Ccc*2 (no. 37)<sup>64</sup> and a meta-stable orthorhombic structure with space group *Pbcn* (no. 60).<sup>65</sup> Very recently, based on single crystal X-ray diffraction Kruger *et al.*<sup>37</sup> determined the structure of Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub> silicate sheets for which a space group *Pmca* (no. 57) was found as shown in Fig. 2(g). Under ambient conditions, Li<sub>2</sub>O has an antifluorite structure with


space group *Fm*3*m*,<sup>66</sup> and Li<sub>2</sub>CO<sub>3</sub> has a monoclinic structure with space group *C*2/*c* (no. 15).<sup>67</sup> According to the phase diagram from Fig. 1, the Li<sub>6</sub>SiO<sub>5</sub> phase may also exist, but no crystal structure is currently available for this phase. For this reason this phase was not included in the current study. Although SiO<sub>2</sub> exhibits many different crystalline phases under different temperatures and pressures,<sup>68–71</sup> here we only deal with  $\alpha$ -quartz, which is the common phase at room-temperature. This phase could exist either as amorphous (*P*3<sub>2</sub>21, no. 154) or low quartz (*P*3<sub>1</sub>21, no. 152). Above 573 °C, the  $\alpha$ -quartz could transform into  $\beta$ -quartz (*P*6<sub>2</sub>22, no. 180). Since SiO<sub>2</sub> is involved in our capture reactions, here, we only consider the  $\alpha$ -phase of SiO<sub>2</sub> as shown in Fig. 2(d) with the crystallographic parameters taken from ref. 72.

These lithium silicates can be synthesized at high temperature with different mixture ratios of Li<sub>2</sub>O and SiO<sub>2</sub>. Table 1 also lists the Li<sub>2</sub>O/SiO<sub>2</sub> molar ratio in each silicate and the number of formula units (f.u.) in their corresponding unit cell. As shown in Fig. 2, the main difference between the metastable Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub> and the stable form is related to orientation of the silicon oxygen tetrahedra within the silicon oxygen layers. In both Li<sub>8</sub>SiO<sub>6</sub> and Li<sub>4</sub>SiO<sub>4</sub>, the [SiO<sub>4</sub>] tetrahedra do not connect directly. Therefore, Li<sub>8</sub>SiO<sub>6</sub> can be considered as being composed by two Li<sub>2</sub>O units intercalated into Li<sub>4</sub>SiO<sub>4</sub>. In Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub>, Li<sub>2</sub>SiO<sub>3</sub>, and Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub>, the [SiO<sub>4</sub>] tetrahedra are connected by bridge-oxygen atoms with formation of several [SiO<sub>4</sub>] chains. In  $\alpha$ -SiO<sub>2</sub>, as shown in Fig. 2(d) all [SiO<sub>4</sub>] tetrahedra are connected and built into one chain.

The optimized crystal constants of these lithium silicates as determined from our DFT calculations are listed in Table 2. From the table, one can see that the largest deviation from experimental measurements is less than 2%, which indicates that our DFT-based theoretical approach can provide accurate crystallographic parameters for these solids.

Other bulk properties of interest, which we determined by DFT calculations for these solids, are their bulk moduli and cohesive energies. These properties were determined from the dependence of unit cell energy on cell volume by fitting the DFT results to Birch–Murnaghan equation of state.<sup>74,75</sup> The fitted results of these lithium silicates are listed in Table 2. The bulk modulus *B* is defined as  $B = B_0 + B'_0 \times P$ , where *P* is the pressure set here to a value of 1 atm. The cohesive energy (*E*<sub>C</sub>) is calculated by subtracting the total bulk energy (*E*<sub>0</sub> in Table 2) from the sum of spin polarized total energies of the related atoms (such as Li, Si, O) using the same level of calculations (in our case, we get *E*<sub>Li</sub> = −0.04403 eV, *E*<sub>Si</sub> = −0.12847 eV, and *E*<sub>O</sub> = −0.12996 eV), and then dividing it by the number of formula units in the unit cell (f.u.) shown in Table 1. In Table 2 we indicate the calculated cohesive energies *E*<sub>C</sub> as well as other values reported in the literature.

For comparison, the bulk properties of Li<sub>4</sub>SiO<sub>4</sub> and Li<sub>2</sub>O from ref. 23 and 45 are also listed in Table 2. From Table 2, it can be seen that overall our fitted parameters and calculated bulk moduli and cohesive energies are in good agreement with the available experimental and theoretical results. From Li<sub>2</sub>O to SiO<sub>2</sub>, by decreasing the Li<sub>2</sub>O/SiO<sub>2</sub> ratio, the bulk modulus

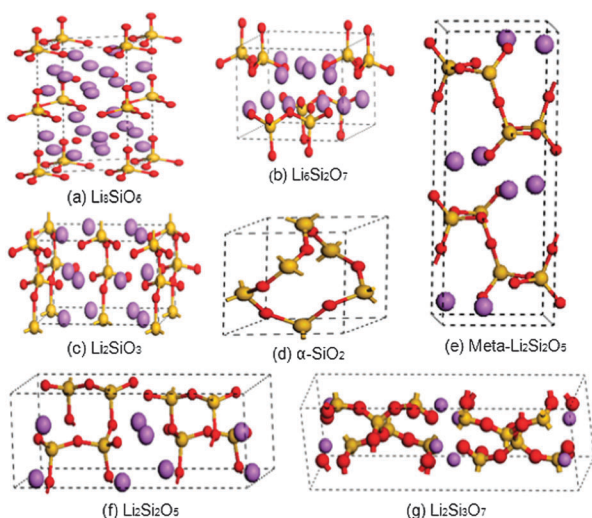

**Fig. 2** The crystal structures of lithium silicates. The largest balls (in pink) correspond to Li, the medium size balls (in yellow) stand for silicon while the smallest balls (in red) indicate O atoms. The *c*-axis is taken as the vertical axis for each structure.


**Table 2** The optimized crystal structural constants in Å, the bulk modulus, cohesive energy ( $E_c$ ), and the fitted parameters of the Birch–Murnaghan equation of state for each lithium silicate and  $\alpha$ -SiO<sub>2</sub>. The zero-point energy ( $E_{ZP}$ ) and entropy ( $S$ ) at  $T = 300$  K from phonon calculations

Crystal	Equilibrium structure and deviations	$E_0$ (eV per unit cell)	$B_0$ (eV Å <sup>-3</sup> )	$B'_0$	Cell volume $V_0$ (Å <sup>3</sup> )	Bulk modulus (GPa)	$E_c$ (eV/f.u.)	$E_{ZP}$ (kJ mol <sup>-1</sup> )	$S$ (J mol <sup>-1</sup> K <sup>-1</sup> )
Li <sub>2</sub> O <sup>a</sup>	$a = 4.631(1.3\%)$	-57.699	0.513	4.074	99.54	82.2	14.207	22.8	44.3
Li <sub>8</sub> SiO <sub>6</sub>	$a = 5.458(0.63\%)$ $c = 10.710(0.79\%)$	-167.303	0.470	4.436	277.38 312.65(exp) <sup>b</sup>	75.34	82.392	116.9	206.5
Li <sub>4</sub> SiO <sub>4</sub> <sup>c</sup>	$a = 11.644(0.97\%)$ $b = 6.142(1.10\%)$ $c = 16.875(1.18\%)$ $\beta = 99.1^\circ(0.05\%)$	-765.319	0.462	4.328	1197.37 1153.9(exp) <sup>d</sup>	73.94	54.231	71.7	128.7
Li <sub>6</sub> Si <sub>2</sub> O <sub>7</sub>	$a = 7.776(0.86\%)$ $c = 4.910(0.61\%)$	-188.221	0.484	4.424	298.52 290.09(exp) <sup>e</sup>	77.56	92.683	114.9	225.6
Li <sub>2</sub> SiO <sub>3</sub>	$a = 9.459(0.71\%)$ $b = 5.441(0.82\%)$ $c = 4.717(1.23\%)$	-158.627 -158.32 <sup>f</sup>	0.454	4.699 5.12 <sup>f</sup>	244.55 245.6 <sup>f</sup> 236.2(exp) <sup>g</sup>	72.69 72.86 <sup>f</sup>	39.050	50.4	83.2 82.0 <sup>m</sup>
Li <sub>2</sub> Si <sub>2</sub> O <sub>5</sub>	$a = 5.881(1.05\%)$ $b = 14.778(0.80\%)$ $c = 4.838(0.99\%)$	-254.424 -254.08 <sup>f</sup>	0.469	3.575 4.28 <sup>f</sup>	423.63 408.68(exp) <sup>h</sup> 424.6 <sup>f</sup>	75.13 73.04 <sup>f</sup>	62.611	79.9	126.9
meta-Li <sub>2</sub> Si <sub>2</sub> O <sub>5</sub>	$a = 5.737(0.94\%)$ $b = 4.853(1.45\%)$ $c = 14.792(0.98\%)$	-254.205 -253.88 <sup>f</sup>	0.416	4.043 4.72 <sup>f</sup>	415.18 398.52(exp) <sup>i</sup> 416.0 <sup>f</sup>	66.60 66.48 <sup>f</sup>	62.557	79.5	127.4
Li <sub>2</sub> Si <sub>3</sub> O <sub>7</sub>	$a = 19.890(1.23\%)$ $b = 6.055(0.97\%)$ $c = 4.9304(1.26\%)$	-350.038	0.442	3.783	598.91 573.70(exp) <sup>j</sup>	70.83	86.127	109.5	171.1
$\alpha$ -SiO <sub>2</sub>	$a = 5.006(1.88\%)$ 4.9160 <sup>k</sup> , 4.92 <sup>l</sup> $c = 5.499(1.72\%)$ 5.4054 <sup>k</sup> , 5.412 <sup>l</sup>	-71.621	0.253	4.168 5.99(exp) <sup>k</sup> (3.1, 4.9) <sup>k</sup> 3.9 <sup>l</sup>	119.38 113.7(exp) <sup>l</sup> 107.4 <sup>l</sup>	40.56 34-37(exp) <sup>k,l</sup> 31.3 <sup>k</sup> 38.1 <sup>l</sup>	23.492 19.2(exp) <sup>k,l</sup> 23.83 <sup>k</sup> 22.2 <sup>l</sup>	29.2	63.2

<sup>a</sup> Ref. 45. <sup>b</sup> Ref. 60. <sup>c</sup> Ref. 73. <sup>d</sup> Ref. 23. <sup>e</sup> Ref. 61. <sup>f</sup> Ref. 44. <sup>g</sup> Ref. 62 and 63. <sup>h</sup> Ref. 64. <sup>i</sup> Ref. 65. <sup>j</sup> Ref. 37. <sup>k</sup> Ref. 71. <sup>l</sup> Ref. 70. <sup>m</sup> Ref. 76.

of the corresponding lithium silicate decreases except for Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub>. For Li<sub>2</sub>SiO<sub>3</sub> and two phases of Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub>, our calculated results are very close to those obtained by Du and Corrales<sup>44</sup>

under a similar approach. The calculated cohesive energy ( $E_c$ ) of monoclinic phase of Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub> (no. 37) is larger than its corresponding meta-stable phase (no. 60) because it has

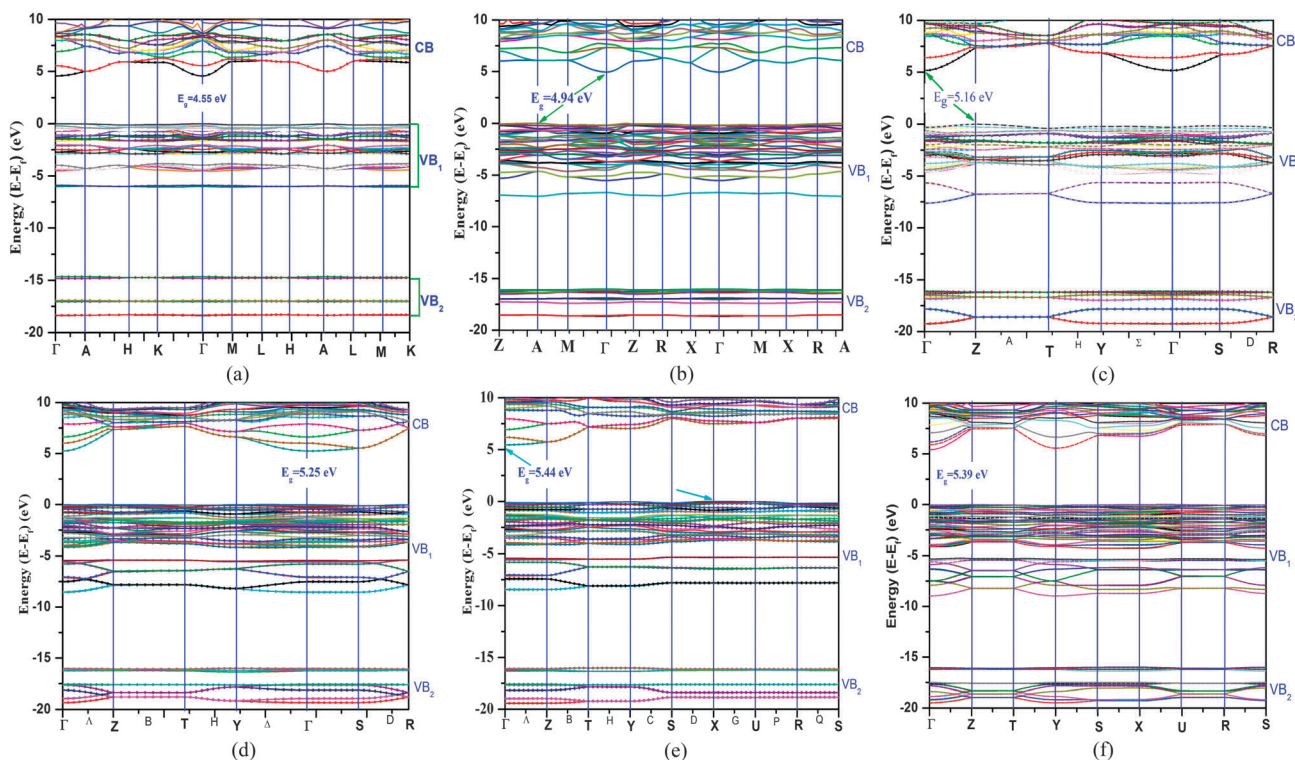

**Fig. 3** The calculated band structures of lithium silicates: (a) Li<sub>8</sub>SiO<sub>6</sub>, (b) Li<sub>6</sub>Si<sub>2</sub>O<sub>7</sub>, (c) Li<sub>2</sub>SiO<sub>3</sub>, (d) Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub>, (e) meta-Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub>, (f) Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub>.

slightly lower unit cell energy ( $E_0$ ) than the meta-stable one as shown in Table 2.

## 4.2 Electronic properties and band structures

The calculated band structures of various lithium silicates considered in this study are shown in Fig. 3. Within the energy range of  $-20$ – $10$  eV, for all lithium silicates, their valence bands (VBs) can be grouped into two bands:  $VB_1$  and  $VB_2$ . Within each VB, there are small gaps to separate them into several sub-bands. The band gaps and bandwidths of these lithium silicates with different  $Li_2O/SiO_2$  ratios are summarized in Table 3.

The calculated total density of states (TDOS) and partial density of states (PDOS) projected onto Li, O, and Si contributions for all of these lithium silicates studied are shown in Fig. 4.

**4.2.1  $Li_8SiO_6$ .** Among various known lithium silicates,  $Li_8SiO_6$  contains the highest amount of  $Li_2O$  component with a  $Li_2O/SiO_2$  ratio of 4:1. By comparing the band structure of  $Li_8SiO_6$  indicated in Fig. 3(a) with the band structure of  $Li_2O$  reported in ref. 45, it can be seen that similarly to pure  $Li_2O$ ,  $Li_8SiO_6$  has a direct band gap with a value of 4.55 eV, which is smaller than that of  $Li_2O$  (5.39 eV). The first VB is located just below the Fermi level and has a width of 6.19 eV, which is much wider than that of  $Li_2O$ . In contrast to  $Li_2O$ ,<sup>45</sup> the  $VB_1$  of  $Li_8SiO_6$  is separated into four sub-bands by several small gaps as shown in Fig. 3(a). Its second VB is located below  $-15$  eV and was also separated into three narrow sub-bands as listed in Table 3.

From its TDOS and PDOS shown in Fig. 4(a), one can see that in  $Li_8SiO_6$  the p orbitals of Li have a larger contribution than the s orbital and both these components contribute to all VBs and conduction band (CB). The p orbitals of O mainly contribute to  $VB_1$  while its s orbital mainly contributes to  $VB_2$ . Both s and p orbitals of Si contribute to the lower portion of  $VB_1$  and  $VB_2$ . Obviously, the upper portion of  $VB_1$  is mainly determined by the interactions between Li and O, which are the reacting orbitals to interact with  $CO_2$  during absorption,

while the lower portion of  $VB_1$  is determined by interactions among Li, O and Si. Similar to  $VB_1$ , the upper sub-band of  $VB_2$  is also mainly determined by the interaction between the s and p orbitals of Li and the s orbital of O, while the lower two sub-bands contain the interactions among the p orbitals of Li, the s orbital of O and the s and p orbitals of Si. From Fig. 2(a), one can see that the Li atoms are just located around the  $[SiO_4]$  tetrahedra with various Li–O distances. The shortest Li–O bond is only 1.224 Å. Around each O, there are at most four Li atoms with bond lengths less than 4.0 Å. Since the location of Li atoms is not symmetric with  $[SiO_4]$  tetrahedra, the Si–O bond-lengths in the  $[SiO_4]$  tetrahedra of  $Li_8SiO_6$  are not equivalent, with the values of 1.449 Å, 1.683 Å, 3.359 Å, and 3.674 Å respectively. The O with the larger Si–O bond length is expected to play a larger role in reactions associated with  $CO_2$  absorption.

**4.2.2  $Li_6Si_2O_7$ .** In  $Li_6Si_2O_7$ , the  $Li_2O/SiO_2$  ratio is 3:2, which is lower than those in  $Li_8SiO_6$  and  $Li_4SiO_4$ . Comparing Fig. 3(b) with the band structures of  $Li_8SiO_6$  (Fig. 3(a)) and  $Li_4SiO_4$  reported in ref. 23, one can see that their band structures have similarities, with the VBs separated into several sub-bands by small gaps. However, in contrast to  $Li_8SiO_6$  and  $Li_4SiO_4$ ,  $Li_6Si_2O_7$  has an indirect band gap between the high symmetry points  $A$ – $\Gamma$  with a value of 4.94 eV. Its first VB is located just below the Fermi level and has a width of 7.04 eV, which is much wider than those of  $Li_2O$ ,  $Li_8SiO_6$  and  $Li_4SiO_4$ . As shown in Fig. 3(b) and Table 3, its  $VB_1$  and  $VB_2$  are also separated into two and four sub-bands respectively.

From the TDOS and PDOS as shown in Fig. 4(b), one can see that as in  $Li_8SiO_6$ , in  $Li_6Si_2O_7$  the p orbitals of Li have larger contributions than its s orbital and all of them involved to form all VBs and CB. The p orbitals of O mainly contribute to  $VB_1$  while its s orbital mainly contributes to  $VB_2$ . Both s and p orbitals of Si contribute to the lower portion of  $VB_1$  and  $VB_2$ . The upper portion of  $VB_1$  is mainly determined by interactions between Li and O. From Fig. 2(a) and (b) and ref. 23, one can see that in these  $Li_2O$ -rich ( $Li_2O/SiO_2$  ratio  $>1$ ) lithium silicates,

**Table 3** The calculated band gaps and the valence band widths of lithium silicates. The corresponding widths of the sub-valence-bands of  $VB_1$  and  $VB_2$  are listed in parentheses. (Unit: eV)

Crystal	$VB_2$ width	$VB_1$ – $VB_2$ gap	$VB_1$ width	Band gap
$Li_2O^a$	0.31	12.44	2.59	5.39 (direct)
$Li_8SiO_6$	3.84 (0.21, 0.21, 0.32)	8.43	6.19 (0.32, 0.64, 0.40, 1.71)	4.55 (direct)
$Li_4SiO_4^b$	2.30	9.83	6.17	5.24 (direct) <sup>b</sup>
$Li_6Si_2O_7$	2.77 (0.21, 0.21, 0.11, 0.53)	8.99	7.04 (0.32, 5.44)	4.94 (indirect, $A$ – $\Gamma$ )
$Li_2SiO_3$	3.15 (1.41, 0.87)	8.47	7.60 (1.95, 4.78)	5.16 (indirect $Z$ – $\Gamma$ )
$Li_2Si_2O_5$	3.27 (1.75, 0.33)	7.53	8.51 (1.09, 1.75, 4.15)	5.7 <sup>d</sup> , 7.26 <sup>c</sup> 5.25 (direct)
<i>meta</i> - $Li_2Si_2O_5$	2.36 <sup>c</sup> 3.39 (1.86, 0.33)	7.44	7.51 <sup>c</sup> 8.54 (1.09, 1.75, 4.27)	5.5 <sup>d</sup> , 7.45 <sup>c</sup> 5.44 (indirect $X$ – $\Gamma$ )
$Li_2Si_3O_7$	3.53 (1.99, 0.44)	7.06	8.93 (3.64, 4.30)	5.6 <sup>d</sup> 5.39 (direct)
$\alpha$ - $SiO_2$	2.06	7.71	9.44 (4.88, 3.26)	5.75 (indirect, $F$ – $\Gamma$ ) 5.84 <sup>e</sup> , 17.03 (HF) <sup>e</sup>

<sup>a</sup> Ref. 45. <sup>b</sup> Ref. 23. <sup>c</sup> Ref. 38. <sup>d</sup> Ref. 44. <sup>e</sup> Ref. 77.

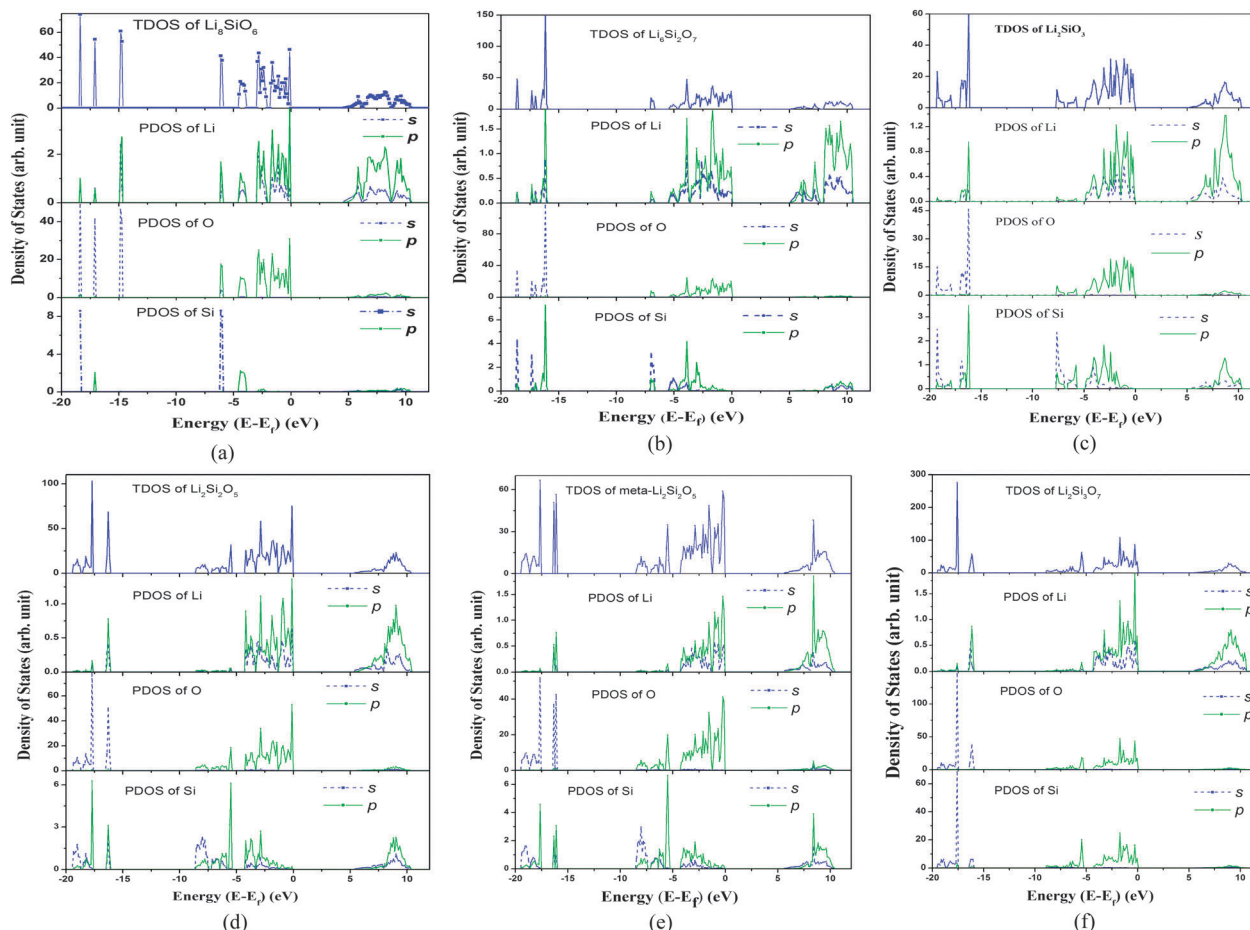


Fig. 4 The calculated density of states of lithium silicates: (a)  $\text{Li}_8\text{SiO}_6$ , (b)  $\text{Li}_6\text{Si}_2\text{O}_7$ , (c)  $\text{Li}_2\text{SiO}_3$ , (d)  $\text{Li}_2\text{Si}_2\text{O}_5$ , (e) *meta*- $\text{Li}_2\text{Si}_2\text{O}_5$ , (f)  $\text{Li}_2\text{Si}_3\text{O}_7$ .

the  $[\text{SiO}_4]$  tetrahedra are not bonded to each other and are separated by Li atoms. The Li–O bond-length varies with a shortest length of only 1.931 Å. Since the location of Li atoms is not fully symmetric with  $[\text{SiO}_4]$ , not all the Si–O bond-lengths in  $[\text{SiO}_4]$  of  $\text{Li}_6\text{Si}_2\text{O}_7$  are equal. Unlike  $\text{Li}_8\text{SiO}_6$ , but similar to  $\text{Li}_4\text{SiO}_4$ , the Si–O bond-lengths in  $\text{Li}_6\text{Si}_2\text{O}_7$  are much shorter. Two of them are equal with the same value of 1.627 Å and the other two are close with values of 1.640 Å and 1.720 Å, respectively. These findings indicate that the binding between O and Si in  $\text{Li}_6\text{Si}_2\text{O}_7$  is stronger than that in  $\text{Li}_8\text{SiO}_6$ .

**4.2.3  $\text{Li}_2\text{SiO}_3$ .** Lithium metasilicate,  $\text{Li}_2\text{SiO}_3$ , has a 1:1  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio. As shown in Fig. 3(c), the calculated band gap is an indirect one between the high symmetry points  $Z$  and  $\Gamma$  of the Brillouin zone with a value of 5.16 eV, which is close to the value of 5.7 eV determined by Du and Corrales<sup>44</sup> using a similar computational method, but lower than the value of 7.26 eV determined by Ching *et al.*<sup>38</sup> using an OLCAO method. Usually, the band-gaps calculated by a Hartree–Fock (HF) method are larger than the experimental measurements. As described in our previous work,<sup>23,24,45,48</sup> due to underestimation of the excited-state energy in standard DFT calculations, our calculated band-gaps are usually smaller than the experimental measurements. Although there is no experimental band gap available for crystalline lithium silicates, it is expected that the real band gap should

be between our DFT predictions and the OLCAO values. As shown in Fig. 3(c) and Table 3, within the energy range of  $-20$ – $0$  eV, there are two VBs and each of them is separated into two sub-bands by a small gap. Compared to  $\text{Li}_2\text{O}$ -rich lithium silicates ( $\text{Li}_8\text{SiO}_6$ ,  $\text{Li}_4\text{SiO}_4$ ,  $\text{Li}_6\text{Si}_2\text{O}_7$ ), the widths of the VBs of  $\text{Li}_2\text{SiO}_3$  are larger with a reduced gap between  $\text{VB}_1$  and  $\text{VB}_2$ .

From its DOS shown in Fig. 4(c), one can see that in  $\text{Li}_2\text{SiO}_3$  the upper portion of  $\text{VB}_1$  is mainly dominated by s and p orbitals of Li interacting with the p orbitals of O, while the lower portion of  $\text{VB}_1$  is mainly dominated by orbitals of Si ( $\text{sp}^3$  hybrid) interacting with orbitals of O and Li. Unlike  $\text{Li}_2\text{O}$ -rich lithium silicates, from Fig. 2(c), in  $\text{Li}_2\text{SiO}_3$ ,  $[\text{SiO}_4]$  tetrahedra are bridged to form a chain. Each  $[\text{SiO}_4]_n$  chain is surrounded by Li atoms. Due to the symmetry, the Si–O bond-lengths in the  $[\text{SiO}_4]$  tetrahedra of  $\text{Li}_2\text{SiO}_3$  are divided into two groups with values of 1.61 Å and 1.70 Å respectively.

**4.2.4  $\text{Li}_2\text{Si}_2\text{O}_5$ .**  $\text{Li}_2\text{Si}_2\text{O}_5$  has a 1:2  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio and is a  $\text{SiO}_2$ -rich ( $\text{Li}_2\text{O}/\text{SiO}_2$  ratio  $< 1$ ) lithium silicate. It exists in two phases as shown in Fig. 2(e) and (f). The main difference between them is in the direction in which the silicon oxygen tetrahedra are pointing within the silicon oxygen layers. As shown in Fig. 3(d) and (e), although these two phases have similar band-structure and VB widths, the stable phase (no. 37) has a direct band-gap of 5.25 eV while its meta-stable phase (no. 60)


has an indirect band gap of 5.44 eV between  $X$  and  $\Gamma$  wave vectors. These values are comparable with the values of 5.5 eV and 5.6 eV respectively calculated by Du and Corrales.<sup>44</sup> However, from their electronic density of states (EDOS) analysis, no information about the band-gap type (direct or indirect) could be obtained. We note that our calculated band gap of the stable  $\text{Li}_2\text{SiO}_3$  is lower than 7.45 eV obtained by OLCAO.<sup>38</sup> Compared to  $\text{Li}_2\text{SiO}_3$ , these two phases of  $\text{Li}_2\text{Si}_2\text{O}_5$  have larger band gaps and wider widths of  $\text{VB}_1$  and  $\text{VB}_2$ .

By comparing Fig. 4(d) and (e), one can see that these two phases have very similar DOS. In both phases, the upper portion of  $\text{VB}_1$ , which is the most important for reactivity properties (in our case to react with  $\text{CO}_2$ ), is mainly dominated by the interaction of the s and p orbitals of Li and the p orbitals of O. The lower portion of  $\text{VB}_1$  is mainly formed by s and p orbitals of Si interacting with the p orbital of O and a small contribution from Li, while their  $\text{VB}_2$  are from the interactions among orbitals of Li, O and Si. From Fig. 2(e) and (f), one can see that, similar to  $\text{Li}_2\text{SiO}_3$ , in the two phases of  $\text{Li}_2\text{Si}_2\text{O}_5$ , the  $[\text{SiO}_4]$  tetrahedra are bridged to form a chain. Each  $[\text{SiO}_4]_n$  chain is surrounded with Li atoms. Although the Si–O bond-lengths in  $[\text{SiO}_4]$  tetrahedra of these two phases are not equal, they are very close to each other. For the stable phase the Si–O bond-lengths are 1.595, 1.628, 1.666, and 1.672 Å while for the meta-stable phase the Si–O bond-lengths are 1.598, 1.626, 1.664, and 1.671 Å respectively.

**4.2.5  $\text{Li}_2\text{Si}_3\text{O}_7$ .**  $\text{Li}_2\text{Si}_3\text{O}_7$  is the most  $\text{SiO}_2$ -rich lithium silicate found in the literature, with a  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio of 1 : 3. As shown in Fig. 3(f),  $\text{Li}_2\text{Si}_3\text{O}_7$  has a direct band gap with a value of 5.39 eV. Compared to other  $\text{SiO}_2$ -rich lithium silicates ( $\text{Li}_2\text{Si}_2\text{O}_5$  in Fig. 3(d) and (e)), its  $\text{VB}_1$  has a wider band-width and is separated into two sub-bands. Its  $\text{VB}_2$  is located below  $-15$  eV and was also separated into two narrow sub-bands.

From its TDOS and PDOS shown in Fig. 4(f), one can see that like other lithium silicates, in  $\text{Li}_2\text{Si}_3\text{O}_7$  the p orbitals of Li have a larger contribution than its s orbital and all these orbitals contribute to both VBs and CB. The p orbitals of O mainly contribute to  $\text{VB}_1$  while its s orbital mainly contributes to  $\text{VB}_2$ . Unlike other lithium silicates, in  $\text{Li}_2\text{Si}_3\text{O}_7$ , the p orbitals of Si have a larger contribution to  $\text{VB}_1$  while its s orbital mainly involves in  $\text{VB}_2$ . As  $\text{Li}_2\text{Si}_3\text{O}_7$  is the most  $\text{SiO}_2$ -rich lithium silicate in this series, the orbitals of Si have a larger influence on  $\text{VB}_1$  formation, and therefore, will be significantly involved in interaction with  $\text{CO}_2$  during absorption–desorption. From Fig. 2(f), one can see that in  $\text{Li}_2\text{Si}_3\text{O}_7$ , the  $[\text{SiO}_4]$  tetrahedra are connected by bridge oxygen and form  $[\text{SiO}_4]_n$  chain. Li atom layers separate these  $[\text{SiO}_4]_n$  chains. Again, the Si–O bond-lengths in  $[\text{SiO}_4]$  of  $\text{Li}_2\text{Si}_3\text{O}_7$  are not equal but they have close values of 1.594 Å, 1.631 Å, 1.668 Å, and 1.673 Å respectively.

**4.2.6  $\alpha\text{-SiO}_2$ .** As aforementioned,  $\text{SiO}_2$  is used to synthesize these lithium silicates and can also be involved in  $\text{CO}_2$  capture reactions. As shown in Table 2, our calculated bulk modulus and cohesive energy of  $\alpha\text{-SiO}_2$  are close to experimental data and other theoretical results.<sup>70,71</sup> Fig. 5 shows the calculated band structure and DOS of  $\alpha\text{-SiO}_2$ . The band gap of  $\alpha\text{-SiO}_2$  is indirect between the  $F$  and  $\Gamma$  high symmetric points with a

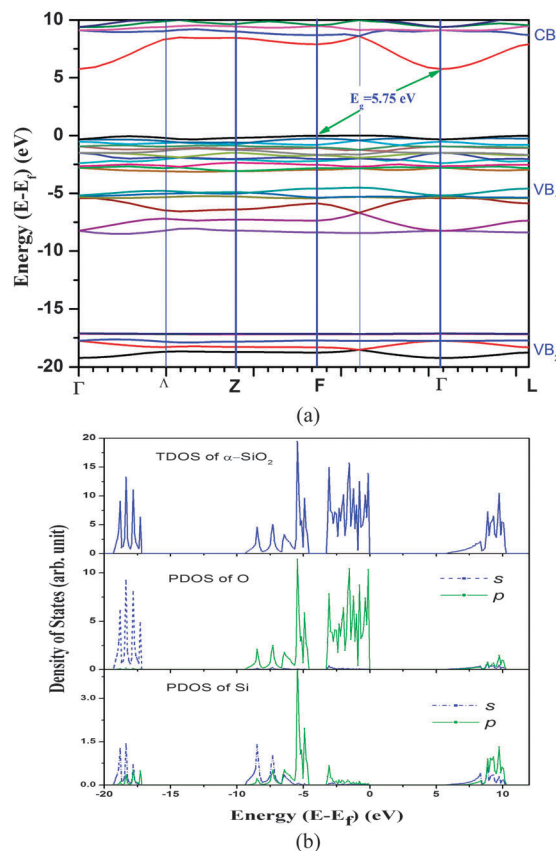


**Fig. 5** The calculated electronic properties of  $\alpha\text{-SiO}_2$ : (a) band structure, (b) density of states.

value of 5.75 eV, in good agreement with other DFT calculated results (5.84 eV).<sup>77</sup> As shown in Fig. 5(a) and Table 3, within the energy range of  $(-20, 10)$  eV, the  $\alpha\text{-SiO}_2$  also has two VBs with widths of 9.44 eV and 2.06 eV. The gap between these two VBs is 7.71 eV. These two VBs are also separated into two sub-bands with a small gap. From its DOS as shown in Fig. 5(b), the upper portion of  $\text{VB}_1$  is mainly the interaction of p orbitals of O and Si while its lower portion is given by contributions of p orbitals of O and s and p orbitals of Si. The  $\text{VB}_2$  is mainly from s orbital of O and the s and p orbitals of Si. From Fig. 2(d), one can see that  $[\text{SiO}_4]$  tetrahedra form a  $[\text{SiO}_4]_n$  chain structure. Within its unit cell there are three  $\text{SiO}_2$  f.u. The calculated results showed that there are three inequivalent  $[\text{SiO}_4]$  units with different Si–O bond-lengths: (0.980 Å, 1.273 Å, 3.247 Å, 3.384 Å), (1.616 Å, 2.357 Å, 2.831 Å, 3.786 Å), and (2.034 Å, 2.412 Å, 3.201 Å, 3.366 Å).

### 4.3 Phonon dynamical properties

The calculated phonon dispersions of the set of lithium silicates considered in this study are shown in Fig. 6 while their corresponding total phonon densities of states are shown in Fig. 7.

**4.3.1  $\text{Li}_8\text{SiO}_6$ .** As shown in Fig. 2(a) and Table 1, in the  $\text{Li}_8\text{SiO}_6$  unit cell there are two f.u. Its primitive cell is the same as its unit cell. Therefore, there are 90 phonon modes as shown in Fig. 6(a). Along the  $\Gamma\text{--}A$  wave-vector and around the high symmetry point  $A$ , there is a small negligible imaginary frequency

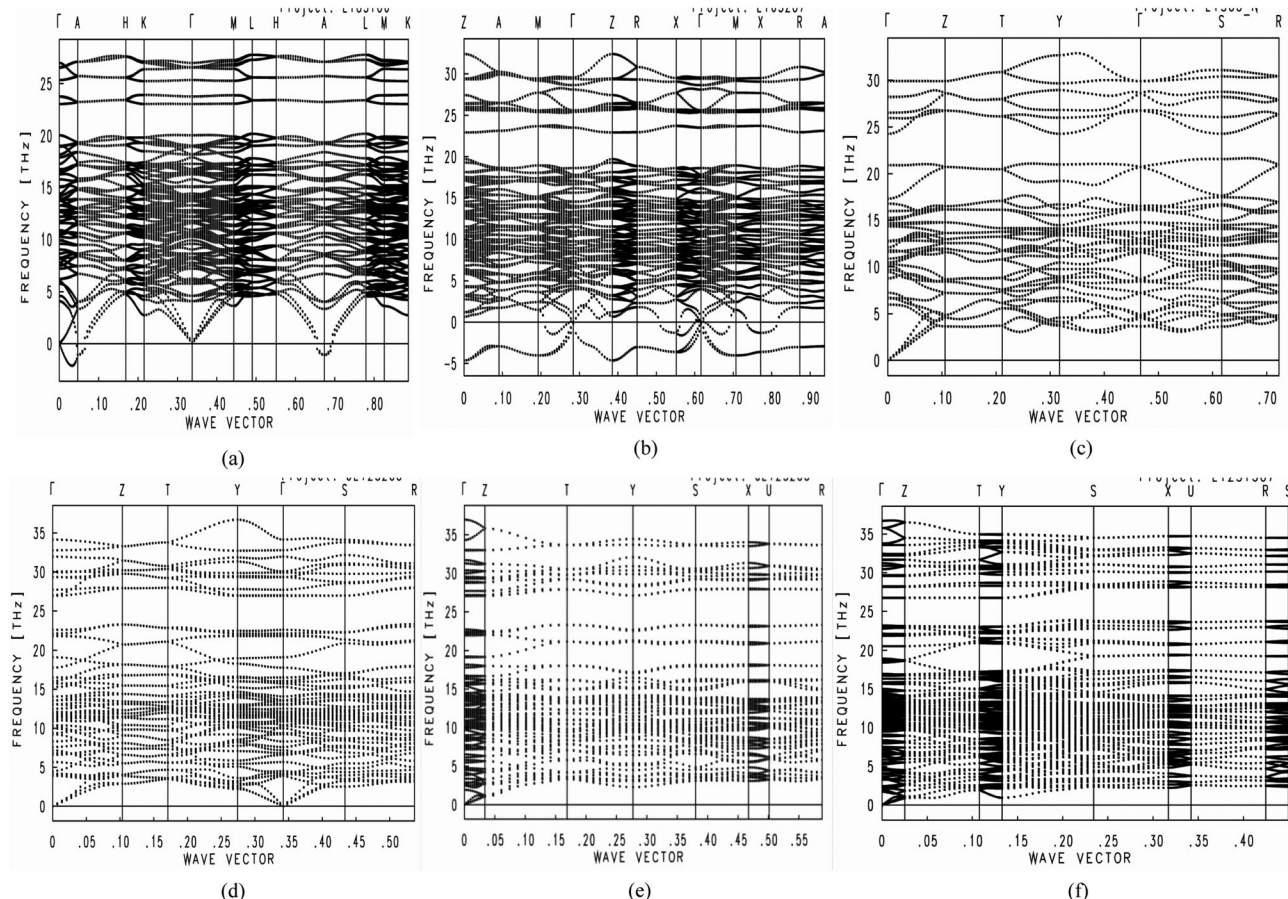


**Fig. 6** The calculated phonon dispersions of lithium silicates: (a)  $\text{Li}_8\text{SiO}_6$ , (b)  $\text{Li}_6\text{Si}_2\text{O}_7$ , (c)  $\text{Li}_2\text{SiO}_3$ , (d)  $\text{Li}_2\text{Si}_2\text{O}_5$ , (e) *meta*- $\text{Li}_2\text{Si}_2\text{O}_5$ , and (f)  $\text{Li}_2\text{Si}_3\text{O}_7$ .

mode (soft mode), indicating instability. Since the space group of  $\text{Li}_8\text{SiO}_6$  is  $P6_3cm$  (no. 185),<sup>60</sup> its corresponding point group is  $C_{6v}$ , having the following representation:  $10 \otimes (A_1(\text{RI}) + B_2) + 5 \otimes (A_2 + B_1) + 15 \otimes (E_1(\text{RI}) + E_2(\text{R}))$ . Obviously, among these vibrational modes, 30 of them ( $15 \otimes E_2(\text{R})$ ) are only Raman (R) active, 40 of them ( $10 \otimes A_1(\text{RI}) + 15 \otimes E_1(\text{RI})$ ) are both Infrared (I) and Raman active, while the remaining 20 vibrational modes ( $10 \otimes B_2 + 5 \otimes (A_2 + B_1)$ ) are silent. From its phonon DOS in Fig. 7(a), one can see that along the frequency axis, the amplitude distribution could be grouped into two peaks. The higher frequency ( $>20$  THz) peak is mainly from the Si–O bond vibrations, while the low frequency band ( $<20$  THz) contains contributions from all types of bond vibrations.

**4.3.2  $\text{Li}_6\text{Si}_2\text{O}_7$ .** As shown in Fig. 2(b) and Table 1, in  $\text{Li}_6\text{Si}_2\text{O}_7$ , both the unit cell and the primitive cell, there are two f.u. Therefore, this system contains 90 phonon modes which are shown in Fig. 6(b). Unlike other lithium silicates, in  $\text{Li}_6\text{Si}_2\text{O}_7$  our DFT calculations give two imaginary frequency modes at all wave vectors, indicating that our calculations do not confirm the stability of this reported experimental crystallographic structure. In order to determine what kind of instability is predicted, we explored the dispersion for each inequivalent atom type along  $x$ -,  $y$ -, and  $z$ -directions. Interestingly, as shown in Fig. S1 (in the ESI†), we found that these relaxing modes are only due to motions of O and Si atoms along the  $x$ - and  $y$ -directions.

These results indicate that along the  $xy$  plane, the Si–O bonds were constrained and could not be fully relaxed during optimization. Since the space group of  $\text{Li}_6\text{Si}_2\text{O}_7$  is  $P4_21m-D_{2d}^3$  (no. 113),<sup>61</sup> its corresponding point group is  $D_{2d}$ , having a  $23 \otimes E(\text{RI}) + 13 \otimes B_2(\text{RI}) + 13 \otimes A_1(\text{R}) + 9 \otimes B_1(\text{R}) + 9 \otimes A_2$  representation. Obviously, among them, 59 vibrational modes ( $23 \otimes E(\text{RI}) + 13 \otimes B_2(\text{RI})$ ) are both Infrared and Raman active, 22 vibrational modes ( $13 \otimes A_1(\text{R}) + 9 \otimes B_1(\text{R})$ ) are only Raman active, and 9 vibrational modes ( $9 \otimes A_2$ ) are silent. From its phonon DOS in Fig. 7(a), one can see that as a function of frequency, the amplitude of the phonon DOS has three main peaks. One peak appeared below zero frequency ( $<0$  THz), indicating an imaginary frequency or relaxation rather than a vibration, and is due to relaxation of O and Si atoms in the  $xy$  plane as discussed above (see Fig. 7(a) and Fig. S1, ESI†). From the partial phonon DOS for each type of atom (not shown here), we observed that the high frequency ( $>20$  THz) band contains three peaks and is mainly from contributions of Si and O vibrations, while the low frequency peak ( $<20$  THz) represents all types of bond vibrations. The Li vibration frequencies are mainly between 5 and 15 THz.

**4.3.3  $\text{Li}_2\text{SiO}_3$ .** As shown in Fig. 2(d) and Table 1, in the  $\text{Li}_2\text{SiO}_3$  unit cell there are four f.u. However, its primitive cell only contains two f.u. Therefore, it has 36 phonon modes as shown in Fig. 6(c). Clearly, we predict no instabilities in  $\text{Li}_2\text{SiO}_3$ .

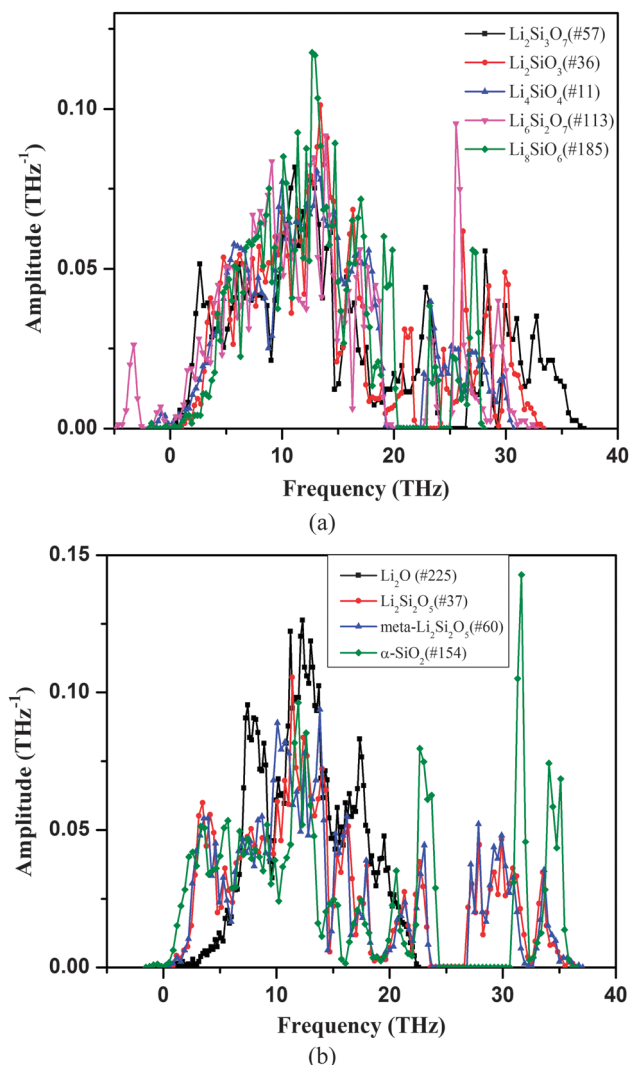

**Fig. 7** The calculated phonon total density of states: (a)  $\text{Li}_2\text{Si}_3\text{O}_7$ ,  $\text{Li}_2\text{SiO}_3$ ,  $\text{Li}_4\text{SiO}_4$ ,  $\text{Li}_6\text{Si}_2\text{O}_7$ ,  $\text{Li}_8\text{SiO}_6$ ; (b)  $\text{Li}_2\text{O}$ ,  $\alpha\text{-SiO}_2$ ,  $\text{Li}_2\text{Si}_2\text{O}_5$ ,  $\text{meta-Li}_2\text{Si}_2\text{O}_5$ .


Since  $\text{Li}_2\text{SiO}_3$  is in an orthorhombic structure with space group  $Cmc2_1$  (no. 36),<sup>62,63</sup> its corresponding point group is  $C_{2v}$ , which represents  $10 \otimes (A_1(\text{RI}) + B_2(\text{RI})) + 8 \otimes (A_2(\text{R}) + B_1(\text{RI}))$ . Among them, 28 modes are both Raman and Infrared active, and 8 modes are only Raman active. Compared to  $\text{Li}_2\text{O}$ -rich lithium silicates, the vibrational frequencies of  $\text{Li}_2\text{SiO}_3$  are shifted to higher frequencies. From its phonon DOS in Fig. 7(a) as seen for other  $\text{Li}_2\text{O}$ -rich lithium silicates, the phonon DOS as a function of frequency could be described as having two peaks. The higher frequency ( $>20$  THz) peak is mainly from Si–O bond vibrations, while the low frequency peak ( $<20$  THz) includes contributions from all types of bond vibrations.

**4.3.4  $\text{Li}_2\text{Si}_2\text{O}_5$ .** As shown in Fig. 2(e) and (f) and Table 1,  $\text{Li}_2\text{Si}_2\text{O}_5$  has two phases. In its stable phase (no. 37) there are four f.u. in its unit cell, but only two f.u. in its primitive cell, while in its metastable phase (no. 60) there are four f.u. in its both unit cell and primitive cell. Therefore, the metastable phase has twice the number of phonon modes (108 modes) over its stable phase (54 modes), as shown in Fig. 6(d) and (e).

Similar to  $\text{Li}_2\text{SiO}_3$ , for this  $\text{SiO}_2$ -rich lithium silicate, there are no predicted instabilities in either phase. Since the space group of the stable phase of  $\text{Li}_2\text{Si}_2\text{O}_5$  is  $Ccc2$  (no. 37)<sup>64</sup> and the space group of the meta-stable  $\text{Li}_2\text{Si}_2\text{O}_5$  is  $Pbcn$  (no. 60),<sup>65</sup> their corresponding point groups are  $C_{2v}$  and  $D_{2h}$  respectively. Their vibrational frequency modes can be represented by  $13 \otimes (A_1(\text{RI}) + A_2(\text{R})) + 14 \otimes (B_1(\text{RI}) + B_2(\text{RI}))$  and  $13 \otimes (A_g(\text{R}) + A_u + B_{2g}(\text{R}) + B_{2u}(\text{I})) + 14 \otimes (B_{1g}(\text{R}) + B_{1u}(\text{I}) + B_{3g}(\text{R}) + B_{3u}(\text{I}))$  respectively. In the stable phase, there are 41 vibrational modes both Raman and Infrared active and 13 vibrational modes which are only Raman active. In its metastable phase, there are 54 Raman active vibrational modes, 41 Infrared active modes, and 13 silent modes. From their phonon DOS represented in Fig. 7(b), it can be observed that the frequencies of both phases of  $\text{Li}_2\text{Si}_2\text{O}_5$  shift to even higher frequencies related to those of other  $\text{Li}_2\text{O}$ -rich lithium silicates and  $\text{Li}_2\text{SiO}_3$ . Above 27 THz, there are two peaks which are mainly from O and Si vibrations. The Li vibrational frequencies are mainly located between 7 and 17 THz, while the lower peak ( $<7$  THz) is due to contributions from both O and Si vibrations.

**4.3.5  $\text{Li}_2\text{Si}_3\text{O}_7$ .** As shown in Fig. 2(g) and Table 1, the unit cell and the primitive cell of  $\text{Li}_2\text{Si}_3\text{O}_7$  coincide and contain four f.u. Therefore, there are 144 phonon modes as shown in Fig. 6(f). There is no unstable relaxation mode predicted for  $\text{Li}_2\text{Si}_3\text{O}_7$  when using phonon dispersion calculations. Since the space group of  $\text{Li}_2\text{Si}_3\text{O}_7$  is  $Pmca$  (no. 57),<sup>37</sup> its corresponding point group is  $D_{2h}$ , which has the irreducible representations  $19 \otimes (A_g(\text{R}) + B_{1g}(\text{R}) + B_{2u}(\text{I}) + B_{3u}(\text{I})) + 17 \otimes (A_u(\text{I}) + B_{1u}(\text{I}) + B_{2g}(\text{R}) + B_{3g}(\text{R}))$ . Obviously, among them, 72 vibrational modes are only Raman active, 55 vibrational modes are only Infrared active, and 17 vibrational modes are silent. From its phonon DOS represented in Fig. 7(a), similar to other  $\text{SiO}_2$ -rich lithium silicates, it was found that the higher frequency ( $>20$  THz) DOS peak is mainly due to Si–O bond vibrations, while the low frequency peak ( $<20$  THz) contains contributions from all types of bond vibrations.

**4.3.6  $\alpha\text{-SiO}_2$ .** As shown in Fig. 2(d) and Table 1, the  $\alpha\text{-SiO}_2$  unit cell coincides with its primitive cell and both contain three f.u. Therefore, there are 27 phonon modes in  $\alpha\text{-SiO}_2$  as shown in Fig. 8. Along the  $\Gamma$ –L wave-vector, there is a slow relaxation mode, indicating a slight instability. Since the space group of  $\alpha\text{-SiO}_2$  is  $P3_121$  (no. 154),<sup>72</sup> its corresponding point group is  $D_3$ , which has the irreducible representations  $4 \otimes A_1 + 5 \otimes A_2 + 9 \otimes E$  at the

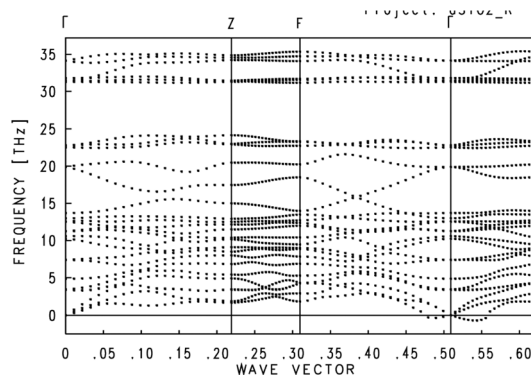

**Fig. 8** The calculated phonon dispersions of  $\alpha\text{-SiO}_2$ .

zone center  $\Gamma$  point.<sup>78</sup> Our calculated frequencies at the  $\Gamma$  point of  $\alpha$ -SiO<sub>2</sub> are comparable with other theoretical results<sup>78</sup> and experimental measurements.<sup>79</sup>

Overall, by decreasing the Li<sub>2</sub>O/SiO<sub>2</sub> ratio, from Li<sub>8</sub>SiO<sub>6</sub> to Li<sub>6</sub>Si<sub>2</sub>O<sub>7</sub>, Li<sub>2</sub>SiO<sub>3</sub>, Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub>, and to Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub>, the frequencies of the vibrational modes are found to increase as shown in Fig. 7.

**4.3.7 Phonon free energy and entropy.** The calculated phonon free energies and entropies of the above-described lithium silicates and  $\alpha$ -SiO<sub>2</sub> *versus* temperature are shown in Fig. 9(a) and (b), respectively. For comparison, the data for Li<sub>4</sub>SiO<sub>4</sub><sup>23</sup> and Li<sub>2</sub>O<sup>45</sup> are also shown in these figures.

From Fig. 9(a), the zero-point energies ( $E_{zp}$ ) of these lithium silicates and  $\alpha$ -SiO<sub>2</sub> can be obtained and listed in Table 2. Among them, Li<sub>8</sub>SiO<sub>6</sub>, Li<sub>6</sub>Si<sub>2</sub>O<sub>7</sub> and Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub> have larger  $E_{zp}$  values. However, with increasing temperature, their phonon free energies decrease faster. These results indicate that in different temperature regions, their thermodynamic properties could be different. The  $E_{zp}$  of these lithium silicates make significant contributions to the prediction of thermodynamic properties as indicated in eqn (2).

The entropies of these lithium silicates and  $\alpha$ -SiO<sub>2</sub> at 300 K are listed in Table 2. From Fig. 9(b), one can see that, at 0 K, the entropies are zero and increase with increasing temperature. Additionally, we note that the calculated entropy of Li<sub>2</sub>SiO<sub>3</sub>

(83.18 J mol<sup>-1</sup> K at 300 K) is very close to the experimental value (81.97 J mol<sup>-1</sup> K at 300 K) from HSC Chemistry Database,<sup>76</sup> which indicates that our theoretical approach can predict sufficiently accurate the experimentally measured thermodynamic properties of these solids.

By comparing the data for both phases of Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub>, we can see that although these two phases of Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub> have different electronic and phonon dispersion features, their thermodynamic data are very close to each other. Therefore, in the following thermodynamic analysis, we only use the thermodynamic properties of the stable phase.

#### 4.4 Structural transformation

By changing the SiO<sub>2</sub>/Li<sub>2</sub>O ratio, several phase transformations among these lithium silicates can happen as indicated in Table 4. The corresponding calculated energy change ( $\Delta E^{\text{DFT}}$ ) and the thermodynamic properties ( $\Delta H$ ,  $\Delta G$ ) for each reaction are also listed in Table 4.


From the phase diagram shown in Fig. 1, the reactions (1)–(6) show that the corresponding lithium silicate phases can be transformed to the closest phase with lower Li<sub>2</sub>O/SiO<sub>2</sub> ratio by adding more SiO<sub>2</sub>. As the  $\Delta H$  and  $\Delta G$  of these reactions (1)–(6) are negative, thermodynamically, these phase transformations can take place spontaneously once the SiO<sub>2</sub> is available. Since Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub> has the highest SiO<sub>2</sub> content in this series and in the literature no evidence showed even higher SiO<sub>2</sub> content silicate available, here, we consider that Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub> does not react with SiO<sub>2</sub> to form even high SiO<sub>2</sub> content silicate.

As shown in Table 4, reactions (2a)–(7a) indicate that the lithium silicate phases can be intermediates to the adjacent two phases as shown in Fig. 1. However, only Li<sub>6</sub>Si<sub>2</sub>O<sub>7</sub> in reaction (4a) could be transformed to its adjacent phases (Li<sub>4</sub>SiO<sub>4</sub> and Li<sub>2</sub>SiO<sub>3</sub>) at ambient conditions as its  $\Delta H$  and  $\Delta G$  are less than zero. Li<sub>8</sub>SiO<sub>6</sub> in reaction (2a) could be transformed to Li<sub>4</sub>SiO<sub>4</sub> and Li<sub>2</sub>O by supplying some energy as its  $\Delta H$  and  $\Delta G$  have small positive values. By adding energy (e.g. by increasing temperature), this reaction could go forward. As for reaction (3a), its free energy is also positive (25.17 kJ mol<sup>-1</sup>), to convert Li<sub>4</sub>SiO<sub>4</sub> into Li<sub>8</sub>SiO<sub>6</sub> and Li<sub>6</sub>Si<sub>2</sub>O<sub>7</sub> also needs input energy. Obviously, among these Li<sub>2</sub>O-rich lithium silicates, Li<sub>4</sub>SiO<sub>4</sub> is the most stable phase. As shown by reaction (5a) in Table 4, it is possible to convert Li<sub>2</sub>SiO<sub>3</sub> into its adjacent silicates (Li<sub>6</sub>Si<sub>2</sub>O<sub>7</sub> and Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub>) by adding extra energy as its  $\Delta H$  and  $\Delta G$  have small positive values. Similarly, for those SiO<sub>2</sub>-rich lithium silicates (Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub> and Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub>), reactions (6a) and (7a) may be driven forward by providing extra energy.

Reactions (3b), (5b), (6b), and (7b) reveal that under normal conditions these lithium silicates (Li<sub>4</sub>SiO<sub>4</sub>, Li<sub>2</sub>SiO<sub>3</sub>, Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub>, and Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub>) cannot release Li<sub>2</sub>O to form low Li<sub>2</sub>O/SiO<sub>2</sub> ratio lithium silicates. Instead, as shown in Table 4 the reverse reactions can occur at ambient conditions. In other words, by adding Li<sub>2</sub>O into low Li<sub>2</sub>O/SiO<sub>2</sub> ratio lithium silicates, we can obtain new lithium silicate phases with higher Li<sub>2</sub>O/SiO<sub>2</sub> ratios.

#### 4.5 Capabilities of lithium silicates for CO<sub>2</sub> capture

As described in the first section, among the lithium silicates considered in this study, Li<sub>4</sub>SiO<sub>4</sub> was widely investigated as

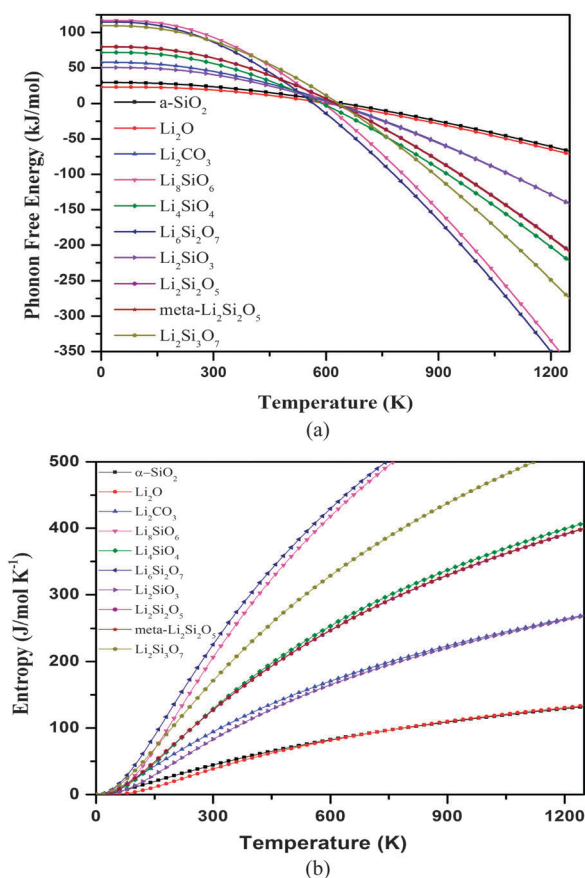

**Fig. 9** (a) The calculated phonon free energies of lithium silicates in which the zero point energy included; (b) the calculated entropies of lithium silicates and Li<sub>2</sub>O and  $\alpha$ -SiO<sub>2</sub>.

**Table 4** The phase transition reactions among various lithium silicates and the corresponding calculated energy changes ( $\Delta E^{\text{DFT}}$ ), heat of reaction ( $\Delta H$ ), and Gibbs free energy change ( $\Delta G$ ) at  $T = 300$  K (unit:  $\text{kJ mol}^{-1}$ )

Reactions	$\Delta E^{\text{DFT}}$	$\Delta H$	$\Delta G$
$\text{Li}_2\text{O} + \frac{1}{4}\text{SiO}_2 \leftrightarrow \frac{1}{4}\text{Li}_8\text{SiO}_6$ (1)	−50.2	−50.8	−51.4
$\text{Li}_8\text{SiO}_6 + \text{SiO}_2 \leftrightarrow 2\text{Li}_4\text{SiO}_4$ (2)	−174.3	−176.4	−178.4
$\text{Li}_8\text{SiO}_6 \leftrightarrow \text{Li}_4\text{SiO}_4 + 2\text{Li}_2\text{O}$ (2a)	13.2	13.30	13.56
$\text{Li}_4\text{SiO}_4 + \frac{1}{3}\text{SiO}_2 \leftrightarrow \frac{2}{3}\text{Li}_6\text{Si}_2\text{O}_7$ (3)	−11.3	−15.4	−17.5
$\text{Li}_4\text{SiO}_4 \leftrightarrow \frac{1}{5}\text{Li}_8\text{SiO}_6 + \frac{1}{5}\text{Li}_6\text{Si}_2\text{O}_7$ (3a)	28.1	26.03	25.2
$\text{Li}_4\text{SiO}_4 \leftrightarrow \text{Li}_2\text{SiO}_3 + \text{Li}_2\text{O}$ (3b)	56.4	57.3	59.4
		82.7 <sup>a</sup>	83.7 <sup>a</sup>
$\text{Li}_6\text{Si}_2\text{O}_7 + \text{SiO}_2 \leftrightarrow 3\text{Li}_2\text{SiO}_3$ (4)	−95.2	−89.7	−83.6
$\text{Li}_6\text{Si}_2\text{O}_7 \leftrightarrow \text{Li}_4\text{SiO}_4 + \text{Li}_2\text{SiO}_3$ (4a)	−20.5	−14.5	−10.3
$\text{Li}_2\text{SiO}_3 + \text{SiO}_2 \leftrightarrow \text{Li}_2\text{Si}_2\text{O}_5$ (5)	−7.3	−7.1	−6.9
		0.6 <sup>a</sup>	1.7 <sup>a</sup>
$\text{Li}_2\text{SiO}_3 \leftrightarrow \frac{1}{4}\text{Li}_6\text{Si}_2\text{O}_7 + \frac{1}{4}\text{Li}_2\text{Si}_2\text{O}_5$ (5a)	22.0	20.6	19.2
$\text{Li}_2\text{SiO}_3 \leftrightarrow \text{Li}_2\text{O} + \text{SiO}_2$ (5b)	131.2	132.5	132.6
		140.8 <sup>a</sup>	141.1 <sup>a</sup>
$\text{Li}_2\text{Si}_2\text{O}_5 + \text{SiO}_2 \leftrightarrow \text{Li}_2\text{Si}_3\text{O}_7$ (6)	−2.9	−2.7	−2.6
$\text{Li}_2\text{Si}_2\text{O}_5 \leftrightarrow \frac{1}{4}\text{Li}_2\text{SiO}_3 + \frac{1}{4}\text{Li}_2\text{Si}_3\text{O}_7$ (6a)	2.2	2.2	2.2
$\text{Li}_2\text{Si}_2\text{O}_5 \leftrightarrow \text{Li}_2\text{O} + 2\text{SiO}_2$ (6b)	138.4	139.6	139.6
		141.3 <sup>a</sup>	142.9 <sup>a</sup>
$\text{Li}_2\text{Si}_3\text{O}_7 \leftrightarrow \text{Li}_2\text{Si}_2\text{O}_5 + \text{SiO}_2$ (7a)	2.9	2.7	2.6
$\text{Li}_2\text{Si}_3\text{O}_7 \leftrightarrow \text{Li}_2\text{O} + 3\text{SiO}_2$ (7b)	141.3	142.3	142.2

<sup>a</sup> Calculated from HSC Chemistry package<sup>76</sup> at  $T = 303.15$  K. The  $\text{Li}_4\text{SiO}_4$ ,  $\text{Li}_2\text{SiO}_3$  and  $\text{Li}_2\text{Si}_2\text{O}_5$  in this database are the mixtures  $2\text{Li}_2\text{O} \cdot \text{SiO}_2$ ,  $\text{Li}_2\text{O} \cdot \text{SiO}_2$  and  $\text{Li}_2\text{O} \cdot 2\text{SiO}_2$  respectively.

a high-temperature  $\text{CO}_2$  sorbent using both experimental measurements<sup>1,7,14,15,17,21,26,28,29,80</sup> and theoretical methods.<sup>23</sup> For  $\text{Li}_2\text{SiO}_3$ , Khomane *et al.*<sup>81</sup> found that this can absorb  $\text{CO}_2$  up to  $610^\circ\text{C}$  and release  $\text{CO}_2$  above  $630^\circ\text{C}$ . Venegas *et al.*<sup>17</sup> found that  $\text{Li}_4\text{SiO}_4$  first captured  $\text{CO}_2$  to form  $\text{Li}_2\text{CO}_3$  and  $\text{Li}_2\text{SiO}_3$ , then, some of the  $\text{Li}_2\text{SiO}_3$  further reacted with  $\text{CO}_2$  to form  $\text{SiO}_2$  and  $\text{Li}_2\text{CO}_3$ . It was also found that the kinetic behavior of  $\text{CO}_2$  absorption on  $\text{Li}_2\text{SiO}_3$  is much slower than that on  $\text{Li}_4\text{SiO}_4$ .<sup>16</sup> Recently, Durán-Muñoz *et al.*<sup>32</sup> explored the  $\text{CO}_2$  capture properties of  $\text{Li}_8\text{SiO}_6$  and found that  $\text{Li}_8\text{SiO}_6$  can absorb  $\text{CO}_2$  over a wide temperature range with a maximum capacity of  $11.8$  mmol  $\text{CO}_2$  per gram  $\text{Li}_8\text{SiO}_6$ . Their results also showed that the  $\text{CO}_2$  capture mechanism of  $\text{Li}_8\text{SiO}_6$  is temperature dependent. Apart from these three lithium silicates ( $\text{Li}_8\text{SiO}_6$ ,  $\text{Li}_4\text{SiO}_4$ ,  $\text{Li}_2\text{SiO}_3$ ), no other reports on  $\text{CO}_2$  capture by other lithium silicates could be found.


**4.5.1 Thermodynamic properties of lithium silicates capturing  $\text{CO}_2$ .** We used the calculated thermodynamic properties of the  $\text{Li}_2\text{O} \cdot \text{SiO}_2$  series of lithium silicates reported above, together with the calculated thermodynamic properties of  $\text{Li}_2\text{CO}_3$  which we previously reported<sup>45</sup> in order to compute the temperature dependence of the free energy differences described by eqn (2) and (3). This analysis has been done for the series of  $\text{CO}_2$  capture reactions indicated in Fig. 10 and in Table 5. Specifically, we used the heat of reactions (enthalpy change  $\Delta H$ ) and Gibbs free energy differences ( $\Delta G$ , in this case same as  $\Delta\mu^0$ ) associated with the solid component alone, for which we ignore any pressure dependence. For those lithium silicates ( $\text{Li}_8\text{SiO}_6$ ,  $\text{Li}_4\text{SiO}_4$ ,  $\text{Li}_6\text{Si}_2\text{O}_7$ ) with the  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio greater than one, we also considered their  $\text{CO}_2$  capture reactions with two steps: first to form  $\text{Li}_2\text{SiO}_3$ , then to form  $\text{SiO}_2$ .

It is generally accepted that the  $\text{CO}_2$  capacity of solid sorbents should be above  $3$  mol  $\text{CO}_2$  per kilogram solid ( $\sim 15$  wt%) in order to meet the industrial requirements and have a chance of

providing energy reductions of  $30\text{--}50\%$  or more compared to the optimum aqueous-MEA-based process.<sup>82</sup> As shown in Table 5, the theoretical  $\text{CO}_2$  weight percentage maxima of all these lithium silicates are greater than this minimum requirement ( $>15$  wt%). Therefore, from the  $\text{CO}_2$  capture capacity point of view, all of these systems could meet this criterion to be used as  $\text{CO}_2$  sorbents.


From Fig. 10 and Table 5, one can see that when going from  $\text{Li}_2\text{O}$  to  $\text{Li}_2\text{Si}_3\text{O}_7$  by decreasing the  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio, the calculated  $\Delta H$  and  $\Delta G$  values of the corresponding  $\text{CO}_2$  capture reactions are decreased (less negative). Throughout the entire temperature range as shown in Fig. 10(a), only three  $\text{CO}_2$  capture reactions by  $\text{Li}_2\text{Si}_3\text{O}_7$ ,  $\text{Li}_2\text{Si}_2\text{O}_5$  and  $\text{Li}_2\text{SiO}_3$  have  $\Delta H$  greater than zero starting at  $640$  K,  $840$  K, and  $1320$  K, respectively. Since  $\Delta G = \Delta H - T\Delta S$ , as shown in Fig. 10(b) the Gibbs free energies of these reactions can be positive starting from a certain temperature for each reaction. In this subsection we call the temperature at which  $\Delta G$  changes its sign as the turnover temperature. From Fig. 10(b) one can see that these reactions could be grouped into four categories:  $\text{Li}_2\text{Si}_3\text{O}_7$ ,  $\text{Li}_2\text{Si}_2\text{O}_5$  and  $\text{Li}_2\text{SiO}_3$  systems, with a  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio  $\geq 1.0$ , have the lowest turnover temperatures ( $365$  K,  $345$  K,  $425$  K respectively);  $\text{Li}_2\text{O}$  and  $\text{Li}_8\text{SiO}_6$  ( $\text{Li}_2\text{O}/\text{SiO}_2 = 4:1$ , partially transform to  $\text{Li}_2\text{SiO}_3$ ) have the highest turnover temperatures ( $1155$  K and  $1105$  K), while  $\text{Li}_4\text{SiO}_4$  and  $\text{Li}_6\text{Si}_2\text{O}_7$  have medium turnover temperatures ( $600\text{--}900$  K). Among them,  $\text{Li}_4\text{SiO}_4$  has the lowest turnover temperature and forms a single group, while  $\text{Li}_6\text{Si}_2\text{O}_7$  and  $\text{Li}_8\text{SiO}_6$  formed another group with higher turnover temperatures.

**4.5.2 The relationship among the chemical potential, temperature, and the  $\text{CO}_2$  pressure.** According to eqn (1) and (4), we can explore the relationship among the chemical potential ( $\Delta\mu(T,P)$ ), the temperature, and the  $\text{CO}_2$  pressure ( $P_{\text{CO}_2}$ ) of the set of  $\text{CO}_2$  capture reactions by various lithium silicates.

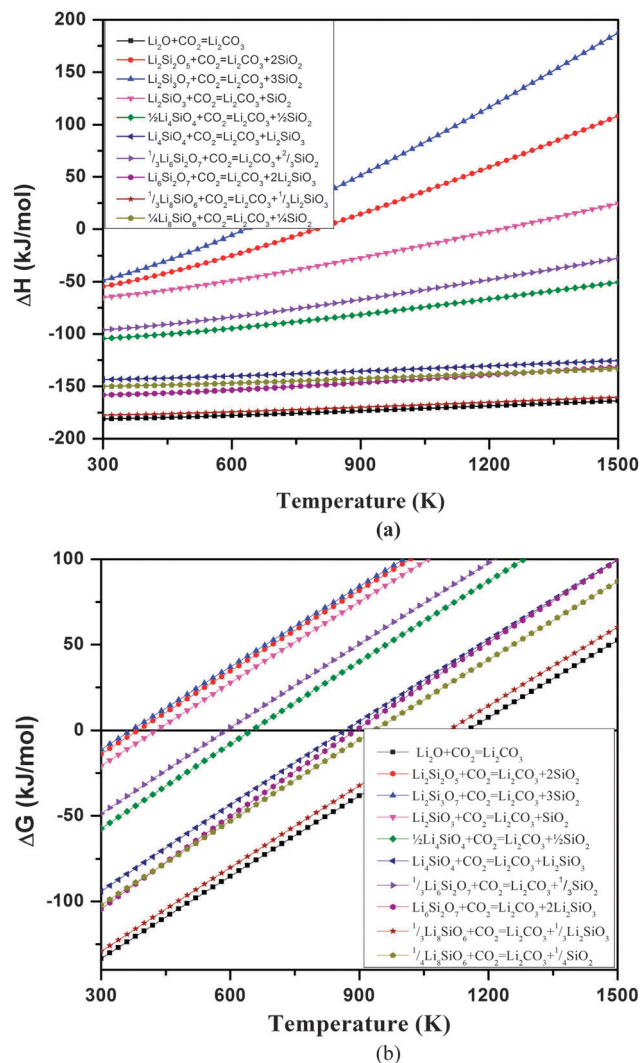

**Fig. 10** The calculated thermodynamic properties of the reactions for lithium silicates capture  $\text{CO}_2$  versus temperature: (a) heat of reaction versus temperature; (b) Gibbs free energy versus temperature.

These corresponding results are shown in Fig. 11. The lines in this figure give the values of  $T$  and  $P$  for which  $\Delta\mu(T, P) = 0$  for each reaction. Around each line is a good region for absorption and desorption with optimal conditions because of the

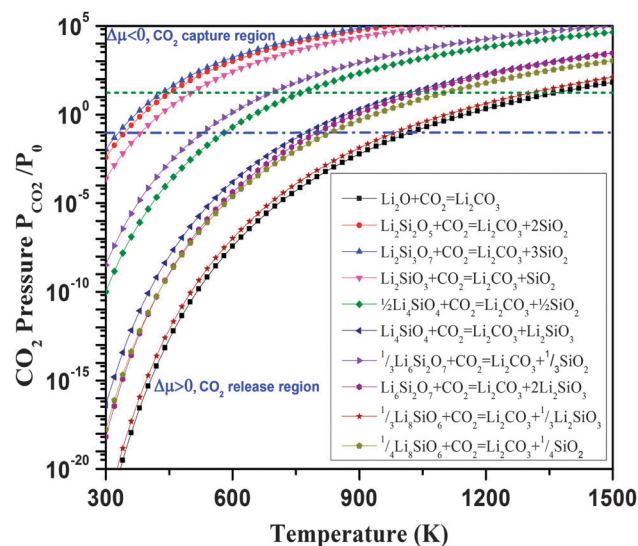

**Fig. 11** Contour plots of the calculated chemical potential ( $\Delta\mu$ ) versus temperature and the  $\text{CO}_2$  pressure ( $P$  plotted on the logarithmic scale) for the  $\text{CO}_2$  capture reactions. Only the  $\Delta\mu = 0$  curve is shown explicitly. For each reaction, above its  $\Delta\mu = 0$  curve, their  $\Delta\mu < 0$ , which means the sorbents absorb  $\text{CO}_2$  and the reaction goes forward, whereas below the  $\Delta\mu = 0$  curve, their  $\Delta\mu > 0$ , which indicates  $\text{CO}_2$  starts to be released and reaction goes backward with regeneration of the sorbents.

minimal energy costs at the respective temperature and pressure conditions. Above the lines, the respective reactions are driven in the  $\text{CO}_2$  absorption direction and  $\text{Li}_2\text{CO}_3$  is formed, while below the respective lines the reactions are driven in the opposite direction, releasing  $\text{CO}_2$  and regenerating the lithium silicate solid.

As aforementioned and shown in Fig. 11, all of the reactions are thermodynamically favorable over a certain range of temperatures and  $P_{\text{CO}_2}$ , which means that under such conditions  $\text{CO}_2$  is thermodynamically favored to be captured by these lithium silicates. Obviously, with increasing  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio, the  $\text{CO}_2$  absorption by these lithium silicates becomes more exothermic and a large amount of heat is released as shown in Fig. 10(a). Such heat will drive the system to higher temperature where absorption might be stopped. Therefore, the heat resulting from the reaction must be removed from the system and re-used in order to reduce the overall costs.

**Table 5** The maximum weight percentages of  $\text{CO}_2$  capture capacity of lithium silicates, the calculated thermodynamic properties of reactions of  $\text{CO}_2$  captured by these lithium silicates at  $T = 300$  K (in  $\text{kJ mol}^{-1}$ ); highest temperature for lithium silicates capturing  $\text{CO}_2$  at pre-combustion ( $T_1$ ) ( $P_{\text{CO}_2} = 20$  bar) and post-combustion ( $T_2$ ) ( $P_{\text{CO}_2} = 0.1$  bar) conditions are also listed

Reaction	Wt%	$\Delta E_{\text{DFT}}$	$\Delta E_{\text{ZP}}$	$\Delta H$	$\Delta G$	$T_1$	$T_2$
$\text{Li}_2\text{O} + \text{CO}_2 \leftrightarrow \text{Li}_2\text{CO}_3$	147.28	-203.96	4.52	-180.89	-133.42	1375	1025
$\frac{1}{3}\text{Li}_6\text{Si}_6\text{O}_6 + \text{CO}_2 \leftrightarrow \text{Li}_2\text{CO}_3 + \frac{1}{3}\text{Li}_2\text{SiO}_3$	73.51	-181.97	5.16	-177.37	-129.11	1325	985
$\frac{1}{4}\text{Li}_8\text{Si}_6\text{O}_6 + \text{CO}_2 \leftrightarrow \text{Li}_2\text{CO}_3 + \frac{1}{4}\text{SiO}_2$	98.01	-154.99	5.42	-150.13	-102.04	1115	835
$\text{Li}_4\text{SiO}_4 + \text{CO}_2 \leftrightarrow \text{Li}_2\text{CO}_3 + \text{Li}_2\text{SiO}_3$	36.72	-148.78	5.97	-143.55	-94.05	1025	775
$\frac{1}{2}\text{Li}_4\text{SiO}_4 + \text{CO}_2 \leftrightarrow \text{Li}_2\text{CO}_3 + \frac{1}{2}\text{SiO}_2$	73.44	-111.42	6.07	-104.36	-57.44	765	585
$\text{Li}_6\text{Si}_2\text{O}_7 + \text{CO}_2 \leftrightarrow \text{Li}_2\text{CO}_3 + 2\text{Li}_2\text{SiO}_3$	20.98	-169.26	13.09	-158.09	-104.38	1045	805
$\frac{1}{3}\text{Li}_6\text{Si}_2\text{O}_7 + \text{CO}_2 \leftrightarrow \text{Li}_2\text{CO}_3 + \frac{2}{3}\text{SiO}_2$	62.93	-105.79	8.48	-96.08	-48.68	695	525
$\text{Li}_2\text{SiO}_3 + \text{CO}_2 \leftrightarrow \text{Li}_2\text{CO}_3 + \text{SiO}_2$	48.92	-74.06	6.18	-65.08	-20.83	505	385
$\text{Li}_2\text{Si}_2\text{O}_5 + \text{CO}_2 \leftrightarrow \text{Li}_2\text{CO}_3 + 2\text{SiO}_2$	29.33	-66.75	5.90	-54.06	-13.87	455	345
$\text{Li}_2\text{Si}_3\text{O}_7 + \text{CO}_2 \leftrightarrow \text{Li}_2\text{CO}_3 + 3\text{SiO}_2$	20.94	-63.83	5.52	-48.60	-11.26	435	335

The operating conditions for absorption–desorption processes depend on the specific pre- and post-combustion technologies. Under pre-combustion conditions, after water-gas shift, the gas stream mainly contains  $\text{CO}_2$ ,  $\text{H}_2\text{O}$  and  $\text{H}_2$ . The partial  $\text{CO}_2$  pressure is around 15–25 bar and the temperature is around 523–773 K. To minimize the energy consumption, the ideal sorbents should work in these pressure and temperature ranges to separate  $\text{CO}_2$  from  $\text{H}_2$ . We define  $T_1$  for each reaction to be the temperature at which the  $\Delta\mu(P,T) = 0$  curve crosses the  $P = 20$  bar line in Fig. 11. This temperature  $T_1$ , listed in Table 5, is the temperature above which the lithium silicate cannot absorb  $\text{CO}_2$  anymore and will start to release  $\text{CO}_2$  when the  $\text{CO}_2$  partial pressure is 20 bar. This indicates that, during capture of  $\text{CO}_2$ , the operating temperature should be lower than  $T_1$ , whereas the operating temperature must be higher than  $T_1$  in order to release  $\text{CO}_2$ . For post-combustion conditions, the gas stream mainly contains  $\text{CO}_2$  and  $\text{N}_2$ , the partial pressure of  $\text{CO}_2$  is around 0.1–0.2 bar, and the temperature range is quite different. We similarly define  $T_2$  to be the temperature at which the  $\Delta\mu = 0$  curve for each reaction crosses the horizontal  $P = 0.1$  bar line in Fig. 11. These corresponding  $T_2$  values obtained for post-combustion capture by these lithium silicates are also listed in Table 5.


Obviously, the  $T_1$  and  $T_2$  values listed in Table 5 are the highest temperatures at which the  $\text{CO}_2$  absorption reaction still can occur for the specific pre- and respectively post-combustion conditions. However, depending on which capture technology is considered, the real capture temperatures should be lower than what we showed in Table 5 ( $T_1$  and  $T_2$ ). The United States Department of Energy (US-DOE) programmatic goal for post-combustion  $\text{CO}_2$  capture is to capture at least 90%  $\text{CO}_2$  with an increase in the cost of electricity of no more than 35%, whereas in the case of pre-combustion  $\text{CO}_2$  capture it is to capture at least 90%  $\text{CO}_2$  with an increase in the cost of electricity of no more than 10%.<sup>83</sup> Assuming that 90% of the  $\text{CO}_2$  is captured, the final  $\text{CO}_2$  partial pressure will be lower than its initial value at 0.01–0.02 bar for post-combustion and at 1.5–2.5 bar for pre-combustion. Therefore, at the end, the final  $T_1$  and  $T_2$  shift to a lower temperature range. Generally speaking, at high temperature the kinetics is faster. From the kinetics point of view, the capture temperature should be as close to the corresponding  $T_1$  and  $T_2$  as possible. However, as aforementioned the capture process is exothermic; during  $\text{CO}_2$  capture, the system temperature will be increased even when heat-exchangers are used. Therefore, the practical operating temperature should be lower than  $T_1$  and  $T_2$  for pre- and post-combustion technologies respectively.

However, as a  $\text{CO}_2$  solid sorbent, the materials of interest should not only be able to absorb  $\text{CO}_2$  easily, but also easily release the  $\text{CO}_2$  from the products. As shown in Fig. 10 and 11, to reverse the  $\text{CO}_2$  capture reaction (a), energy input is needed as these reverse reactions are endothermic. Obviously, the operating temperature for  $\text{CO}_2$  desorption should be higher than the indicated temperatures  $T_1$  (pre-combustion) or  $T_2$  (post-combustion) as shown in Fig. 11.

From Fig. 10 and 11, one can see that during absorption of  $\text{CO}_2$ , the lithium silicates with  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio  $>1$  (e.g.  $\text{Li}_8\text{SiO}_6$ ,  $\text{Li}_6\text{Si}_2\text{O}_7$ ,  $\text{Li}_4\text{SiO}_4$ ) can be fully converted into  $\text{SiO}_2$  and  $\text{Li}_2\text{CO}_3$

because thermodynamically  $\text{Li}_2\text{SiO}_3$  can further absorb  $\text{CO}_2$  to gain energetic advantage. As shown in Fig. 11, for these  $\text{Li}_2\text{O}$ -rich lithium silicates, in order to obtain maximum  $\text{CO}_2$  capture capacity, the operating temperatures during capture should be lower than the turnover temperatures ( $T_1$  for pre-combustion capture or  $T_2$  for post-combustion capture) of  $\text{Li}_2\text{SiO}_3$ . If the capture temperature is higher than that temperature for  $\text{Li}_2\text{SiO}_3$ , the reverse reaction ( $\text{Li}_2\text{CO}_3 + \text{SiO}_2 = \text{Li}_2\text{SiO}_3 + \text{CO}_2$ ) will start and the products will be  $\text{Li}_2\text{SiO}_3$  and  $\text{Li}_2\text{CO}_3$ . In this case, the  $\text{CO}_2$  capture capacities of these  $\text{Li}_2\text{O}$ -rich lithium silicates could not reach their maxima. However, during regeneration, when  $\text{Li}_2\text{CO}_3$  and  $\text{Li}_2\text{SiO}_3$  (or  $\text{SiO}_2$ ) react with each other to release  $\text{CO}_2$  and regenerate the sorbent, the temperature is the key factor to ensure that the original lithium silicate is being regenerated. Actually, from Fig. 11 one can see that from the “ $\text{CO}_2$  capture region” to the “ $\text{CO}_2$  release region” we can have different regenerating temperatures for different silicates. For example, even if one uses  $\text{Li}_8\text{SiO}_6$  to capture  $\text{CO}_2$ , if the regenerating temperature is lower than its corresponding  $T_1$  or  $T_2$  in Table 5, one cannot obtain  $\text{Li}_8\text{SiO}_6$ , but instead other silicates with lower  $\text{Li}_2\text{O}/\text{SiO}_2$  ratios will be formed. Durán-Muñoz *et al.*<sup>32</sup> measured the XRD pattern of  $\text{Li}_8\text{SiO}_6$  capture  $\text{CO}_2$  at 550 °C and 650 °C and found that the products contain  $\text{Li}_4\text{SiO}_4$  and  $\text{Li}_2\text{SiO}_3$ , which reflect the fact that  $\text{Li}_8\text{SiO}_6$  first absorbs  $2\text{CO}_2$  to form  $\text{Li}_2\text{CO}_3$  and  $\text{Li}_4\text{SiO}_4$ , then  $\text{Li}_4\text{SiO}_4$  further absorbs another  $\text{CO}_2$  to form  $\text{Li}_2\text{CO}_3$  and  $\text{Li}_2\text{SiO}_3$ . Similar results were obtained by Qi *et al.*<sup>84</sup> Their results showed that in a temperature range of 25–228 °C,  $\text{Li}_4\text{SiO}_4$  could fully react with  $\text{CO}_2$  to form  $\text{Li}_2\text{CO}_3$  and  $\text{SiO}_2$  with highest  $\text{CO}_2$  capacity as shown in Table 5. In the temperature range of 229–262 °C,  $\text{Li}_4\text{SiO}_4$  absorbs  $\text{CO}_2$  to form  $\text{Li}_2\text{CO}_3$  and  $\text{Li}_2\text{Si}_2\text{O}_5$ , and above 262 °C, the  $\text{Li}_4\text{SiO}_4$  absorbs  $\text{CO}_2$  only to form  $\text{Li}_2\text{SiO}_3$  and  $\text{Li}_2\text{CO}_3$  with lower  $\text{CO}_2$  capture capacity. Such experimental evidence is in good agreement with our theoretical predictions. Although in the literature, there is no experimental study on  $\text{CO}_2$  captured by  $\text{Li}_6\text{Si}_2\text{O}_7$ , from our calculated results in Fig. 11, it can be seen that its  $\text{CO}_2$  capture behavior should be intermediate between  $\text{Li}_4\text{SiO}_4$  and  $\text{Li}_2\text{SiO}_3$ .

Among these lithium silicates, we present experimental results on  $\text{Li}_8\text{SiO}_6$ ,  $\text{Li}_4\text{SiO}_4$  and  $\text{Li}_2\text{SiO}_3$  as possible  $\text{CO}_2$  captors.<sup>16,32,85,86</sup> Here, Fig. 12 shows our dynamic TGA data on the  $\text{CO}_2$  capture of these lithium silicates, in addition to the  $\text{Li}_2\text{O}$ . From these curves, it is clearly seen how the  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio modified the amount of  $\text{CO}_2$  captured and the temperature range in which the process is performed. We note that these experiments are not quantitative, thus the weight increase analysis must be performed in other types of experiments presented below. From the temperature point of view, it is evident that all the silicates captured  $\text{CO}_2$  in two different steps, as it was previously described. Analyzing the  $\text{Li}_2\text{O}$ , as example, the first  $\text{CO}_2$  capture process occurred between 180 and 380 °C. The weight increase at this stage is associated with the  $\text{CO}_2$  superficial reaction. Then, once the diffusion processes are activated, the second weight increment was produced between 580 and 710 °C. Here, the  $\text{CO}_2$  capture is produced in the silicate bulk. A similar interpretation is possible for the other curves depicted as an

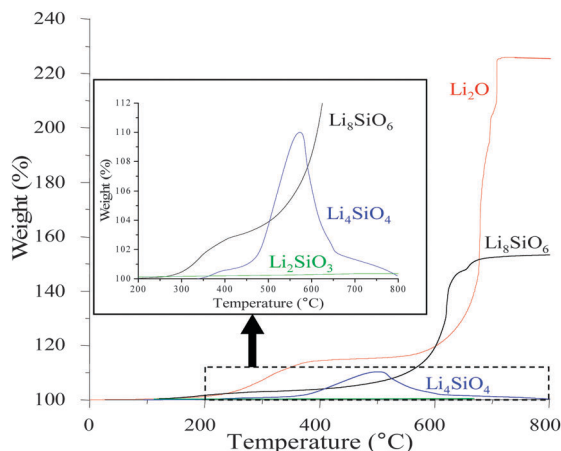

**Fig. 12** Dynamic thermogravimetric analyses of different lithium silicates ( $\text{Li}_2\text{O}$ ,  $\text{Li}_8\text{SiO}_6$ ,  $\text{Li}_4\text{SiO}_4$  and  $\text{Li}_2\text{SiO}_3$ ) into a  $\text{CO}_2$  flux ( $60 \text{ mL min}^{-1}$ ).


inset in Fig. 12, although the reaction process and the external shell composition may differ in each lithium silicate whose reactions are proposed in Table 5.

The maximum temperature, at which each lithium silicate is able to trap  $\text{CO}_2$ , has the following trend:  $\text{Li}_2\text{O} > \text{Li}_8\text{SiO}_6 > \text{Li}_4\text{SiO}_4 > \text{Li}_2\text{SiO}_3$ , at which the  $\text{CO}_2$  capture properties of  $\text{Li}_2\text{SiO}_3$  can be considered as negligible. These results are in good agreement with our theoretical results presented in Fig. 11 and in Table 5. Therefore, based on these results, if the non-tested lithium silicates were evaluated as possible  $\text{CO}_2$  capture sorbent, the  $\text{Li}_6\text{Si}_2\text{O}_7$  ( $\text{Li}_2\text{O}/\text{SiO}_2$  ratio higher than that of  $\text{Li}_2\text{SiO}_3$ ) could present some interesting properties.

Except for those  $\text{Li}_2\text{O}$ -rich lithium silicates, our calculated results also showed that thermodynamically  $\text{SiO}_2$ -rich lithium silicates ( $\text{Li}_2\text{SiO}_3$ ,  $\text{Li}_2\text{Si}_2\text{O}_5$ , and  $\text{Li}_2\text{Si}_3\text{O}_7$ ) could absorb  $\text{CO}_2$  at even lower temperatures. However, the experimental data showed that the  $\text{Li}_2\text{SiO}_3$  had a very small  $\text{CO}_2$  capture capacity. We suggest that this disagreement between prediction and experiment arises because the capture reaction rates of the  $\text{SiO}_2$ -rich lithium silicates are very slow. To consider this possibility further we discuss the kinetics of  $\text{CO}_2$  capture by lithium silicates in the following section.

**4.5.3 The kinetics of lithium silicates capturing  $\text{CO}_2$ .** Kinetically, it is generally accepted that the  $\text{CO}_2$  capture of lithium silicates is a two-step process. Initially, the lithium silicate particles react with  $\text{CO}_2$  at the particle surface. This superficial reaction involves the formation of an external shell composed of lithium carbonate and a metal oxide or a lithium secondary phase, depending on the initial composition.<sup>87</sup> Once the first stage is complete, bulk diffusion processes must be activated for the silicate to continue  $\text{CO}_2$  chemisorption.<sup>87,88</sup>

As discussed in previous section, depending on the operating temperature, the  $\text{Li}_2\text{O}$ -rich lithium silicates capturing  $\text{CO}_2$  can lead to different products. Our experimental results showed that  $\text{Li}_2\text{O}$  only produces  $\text{Li}_2\text{CO}_3$ , but  $\text{Li}_8\text{SiO}_6$ ,  $\text{Li}_4\text{SiO}_4$  and  $\text{Li}_2\text{SiO}_3$  produce more complex external shell compositions.  $\text{Li}_8\text{SiO}_6$  produces two consecutive reactions: (1)  $\text{Li}_8\text{SiO}_6 + 2\text{CO}_2 = \text{Li}_4\text{SiO}_4 + 2\text{Li}_2\text{CO}_3$  and (2)  $\text{Li}_4\text{SiO}_4 + \text{CO}_2 = \text{Li}_2\text{SiO}_3 + \text{Li}_2\text{CO}_3$ .

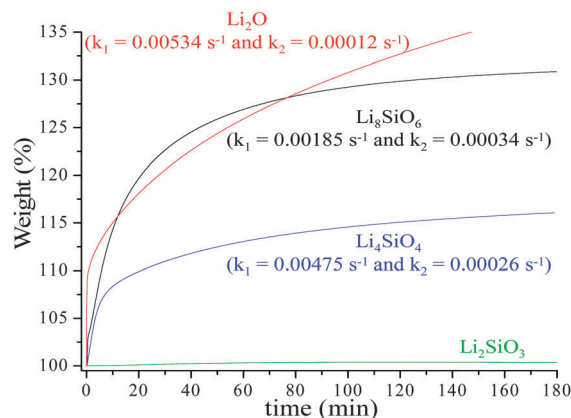

**Fig. 13**  $\text{CO}_2$  isothermal experiments performed at  $600^\circ\text{C}$  in the following lithium silicates:  $\text{Li}_8\text{SiO}_6$ ,  $\text{Li}_4\text{SiO}_4$ ,  $\text{Li}_2\text{SiO}_3$  and  $\text{Li}_2\text{O}$ . The  $k$  constant values reported correspond to the isothermal fitting to a double exponential model.

In fact, the second consecutive  $\text{CO}_2$  capture process is evident in the corresponding dynamic TGA experiment ( $\text{Li}_8\text{SiO}_6$ ) between  $630$  and  $670^\circ\text{C}$ .  $\text{Li}_4\text{SiO}_4$  presents the second reaction proposed just above the  $\text{Li}_8\text{SiO}_6$  curve while  $\text{Li}_2\text{SiO}_3$  hardly reacts at all.

It must be mentioned that there is not general agreement about the second weight increase ( $\text{CO}_2$  capture controlled by the diffusion processes). While some authors proposed  $\text{CO}_2$  diffusion, others proposed  $\text{Li}^+$  and  $\text{O}^{2-}$  ionic diffusion. In any case, the whole diffusion process is highly controlled by the chemical composition and the microstructure of the external shell, which is composed of a mixture of  $\text{Li}_2\text{CO}_3$  and/or lithium secondary phases and/or metal oxides.<sup>87,88</sup>

Fig. 13 shows the  $\text{CO}_2$  isothermal weight gain due to  $\text{CO}_2$  absorption as a function of time of the same lithium silicates ( $\text{Li}_2\text{O}$ ,  $\text{Li}_8\text{SiO}_6$ ,  $\text{Li}_4\text{SiO}_4$  and  $\text{Li}_2\text{SiO}_3$ ), at  $600^\circ\text{C}$ . Qualitatively, at short times ( $\sim 10$  min) the  $\text{CO}_2$  capture rates for the lithium silicates are ordered as follows (fastest first):  $\text{Li}_2\text{O} > \text{Li}_8\text{SiO}_6 > \text{Li}_4\text{SiO}_4 > \text{Li}_2\text{SiO}_3$ , and the same trend is observed for long times ( $\sim 80$  min). The only significant variation of this tendency was observed between  $\text{Li}_2\text{O}$  and  $\text{Li}_8\text{SiO}_6$  in the 10 to 80 min interval. At  $t < 10$  min, the curves' behaviors were inverted and  $\text{Li}_8\text{SiO}_6$  started to absorb faster than  $\text{Li}_2\text{O}$  up to 80 min. This effect can be attributed to the diffusion process that must control the reaction process. Therefore, different microstructural features may have induced this change. At  $t > 80$  min,  $\text{Li}_2\text{O}$  captures more  $\text{CO}_2$  than  $\text{Li}_8\text{SiO}_6$  due to chemical capacity of both ceramics  $33.3$  and  $16.6 \text{ mmol g}^{-1}$ , respectively. It was confirmed at long times, where the isothermal curves presented  $\text{CO}_2$  absorptions as a function of their chemical capacity.

Similar isothermal data have been fitted to various kinetic models.<sup>10,16,21,84,85,89,90</sup> In general, simple (eqn (8)) or double (eqn (9)) exponential models have been used in order to elucidate the direct  $\text{CO}_2$  capture (superficial reaction), and the  $\text{CO}_2$  capture kinetically controlled by diffusion processes, which occurs once the external shell is formed.

$$Q = Ae^{-k_1t} + C \quad (8)$$

$$Q = Ae^{-k_1t} + Be^{-k_2t} + C \quad (9)$$

where  $Q$  corresponds to the rate at which  $\text{CO}_2$  is captured (weight increase);  $t$  is the time; and  $k_1$  and  $k_2$  are the exponential constants for the  $\text{CO}_2$  directly captured over the lithium silicate particles and  $\text{CO}_2$  captured kinetically controlled by diffusion processes, respectively. In Fig. 13 we show data ( $k_1$  and  $k_2$  values) together with fits of the integral of eqn (9) from 0 to  $t$  with fitted values for the constants  $A$ ,  $B$ ,  $k_1$ ,  $k_2$ . The fitted rate constants  $k_1$ ,  $k_2$  differ significantly for each lithium silicate. Similar results have been obtained by others,<sup>15,17,21,32,85,86,91–93</sup> and it has been established that  $k_1$  values are always, at least, one order of magnitude higher than those obtained for the  $k_2$  constants, independently of the lithium ceramic. We associate the small  $k_2$  rate constant with the slow diffusion processes of stage two of the capture mechanism as discussed at the beginning of this section.

Once the isotherms were fitted to the double exponential model, the following results were obtained. For  $\text{Li}_2\text{O}$  we found the highest  $k_1$  value, but the smallest  $k_2$  value. It means that  $\text{Li}_2\text{O}$  reacts very quickly with the particle surface, but once the diffusion processes are activated,  $\text{CO}_2$  capture is very slow. The slow diffusion in  $\text{Li}_2\text{O}$  may arise because the external shell is composed of  $\text{Li}_2\text{CO}_3$  in this case, whereas other lithium secondary phases are present in the external shell during  $\text{CO}_2$  absorption by the other lithium silicates and may make faster diffusion possible, depending on temperature.<sup>87</sup>

$\text{Li}_8\text{SiO}_6$  presents a smaller  $k_1$  value than that of  $\text{Li}_4\text{SiO}_4$ . However, we must take into account that  $\text{Li}_8\text{SiO}_6$  presents a double consecutive reaction process producing  $\text{Li}_4\text{SiO}_4$  as an initial intermediate, which may attenuate the superficial reaction, as it is evidenced in the corresponding  $\text{Li}_4\text{SiO}_4$  isothermal curve. In contrast, the presence of the same  $\text{Li}_4\text{SiO}_4$  as intermediate may increase the lithium ion diffusion, enhancing the  $k_2$  value of the corresponding  $\text{Li}_8\text{SiO}_6$ .

Some of these kinetic data have been further analyzed by fitting the temperature dependence of the fitted rate constants using Arrhenius or Eyring models. Table 6 shows the experimental results reported for different lithium silicates. In each case, the corresponding activation energies ( $E_a$  from the Arrhenius model)

or activation enthalpies ( $\Delta H^\ddagger$  from the Eyring model) are reported.<sup>10,15,17,21,32,85,86,91–93</sup> It should be pointed out that none of these samples presented any kind of porosity, and their surfaces areas were  $\leq 3.0 \text{ m}^2 \text{ g}^{-1}$ .

According to the results listed in Table 6, it seems that there is not a general defined trend. While some results suggest that the  $\text{CO}_2$  direct absorption process is more dependent on temperature than the  $\text{CO}_2$  absorption controlled by diffusion processes, for other lithium silicates we find exactly the contrary. The variations observed between these results may arise in part from the fact that the temperature range over which the fit was done was not large and varied from one silicate to another. However,  $\text{Li}_8\text{SiO}_6$  possesses smaller activation enthalpy than  $\text{Li}_4\text{SiO}_4$ , independently of the specific  $\text{Li}_4\text{SiO}_4$  physicochemical characteristics, but larger than  $\text{Li}_2\text{O}$  (the reported value of  $\text{Li}_2\text{O}$  corresponds to  $E_a$ ). In the  $\text{Li}_8\text{SiO}_6$  case, the experimental results showed that  $\text{Li}_8\text{SiO}_6$  reacts with  $\text{CO}_2$  to produce  $\text{Li}_4\text{SiO}_4$  over the external shell, which consequently reacts with more  $\text{CO}_2$  (depending on temperature) to produce  $\text{Li}_2\text{SiO}_3$ . This reaction mechanism agrees with the theoretical results reported above. Finally, two other factors must be taken into account: (1) doped-lithium silicates present better  $\text{CO}_2$  absorption capacities, and it has been associated with the eutectic phase formation.<sup>11,13,18</sup> (2) Surface area increments modified the  $\text{CO}_2$  capture process as this whole process depends on the direct (related to the surface area) and diffusion control reactions (related to the bulk material).<sup>16,87,92</sup>

In addition, one of the major parameters for potential applications of these materials is related to the cyclability. Among these lithium silicates, there are a few cyclability reports related to  $\text{Li}_4\text{SiO}_4$ . Kato *et al.* reported efficiency cyclic performances up to 90% after 50 cycles using  $\text{Li}_4\text{SiO}_4$  alone or mixed with other lithium ceramics.<sup>94</sup>

Obviously, in order to fully understand the mechanisms of their  $\text{CO}_2$  capture process and evaluate their possible industrial applications further theoretical and experimental analyses of  $\text{Li}^+$  and  $\text{O}^{2-}$  diffusion through the shell are needed and under investigation.


**4.5.4 Synthesis of new lithium silicate materials by adjusting the  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio.** As shown in Fig. 11,  $\text{Li}_2\text{O}$  is a strong  $\text{CO}_2$  sorbent as it can absorb  $\text{CO}_2$  over a wide range of  $P_{\text{CO}_2}$  at high temperatures.<sup>45</sup> However, it is not a good  $\text{CO}_2$  sorbent because its reverse reaction to release  $\text{CO}_2$  can happen only at much higher temperatures.<sup>45,50</sup> Meanwhile, as a very weak  $\text{CO}_2$  sorbent,  $\text{SiO}_2$  usually does not capture  $\text{CO}_2$ . As shown in Table 1, when going from  $\text{Li}_2\text{O}$  to various lithium silicates and further to  $\text{SiO}_2$ , the  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio decreases. Fig. 14 shows the relationship of the  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio (plotted as a function of  $\text{SiO}_2$  molar percentage) with the turnover temperatures ( $T_1$ ,  $T_2$ ,  $T'_1$ ,  $T'_2$ ) and  $\text{CO}_2$  capture capacities among various lithium silicates.

As shown in Fig. 14 and Table 5, by decreasing the  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio, the corresponding turnover temperatures ( $T_1$  and  $T_2$ ) and the  $\text{CO}_2$  capture capacities of these lithium silicates also decreased. Such results indicate that by changing the  $\text{Li}_2\text{O}/\text{SiO}_2$  ratio we can find and synthesize a lithium silicate with an

**Table 6** The obtained activation enthalpy ( $\Delta H^\ddagger$ ) or energy activation ( $E_a$ ) values of the  $\text{CO}_2$  capture on lithium silicates

Lithium silicates	Temperature range (°C)	Energy ( $\text{kJ mol}^{-1}$ )		Ref.
		$\text{CO}_2$ direct	Diffusion control	
$\text{Li}_2\text{O}$	200–600	3.6 <sup>a</sup>	—	10
$\text{Li}_8\text{SiO}_6$	500–700	48.1 <sup>b</sup>	—	32
$\text{Li}_4\text{SiO}_4$	500–600	71.2 <sup>a</sup>	83.4 <sup>a</sup>	86
K-doped $\text{Li}_4\text{SiO}_4$	500–650	45.8 <sup>a</sup>	60.1 <sup>a</sup>	86
Na-doped $\text{Li}_4\text{SiO}_4$	500–650	56.6 <sup>b</sup>	96.8 <sup>b</sup>	85
$\text{Li}_4\text{SiO}_4$	460–650	94.4 <sup>b</sup>	37.2 <sup>b</sup>	16
( $S_{\text{BET}}$ , $0.4 \text{ m}^2 \text{ g}^{-1}$ ) $\text{Li}_4\text{SiO}_4$	460–650	83.4 <sup>b</sup>	32.0 <sup>b</sup>	16
( $S_{\text{BET}}$ , $1.5 \text{ m}^2 \text{ g}^{-1}$ ) $\text{Li}_4\text{SiO}_4$	500–650	88.9 <sup>b</sup>	79.5 <sup>b</sup>	85
( $S_{\text{BET}}$ , $3.0 \text{ m}^2 \text{ g}^{-1}$ )				

<sup>a</sup>  $E_a$  value. <sup>b</sup>  $\Delta H^\ddagger$  value.

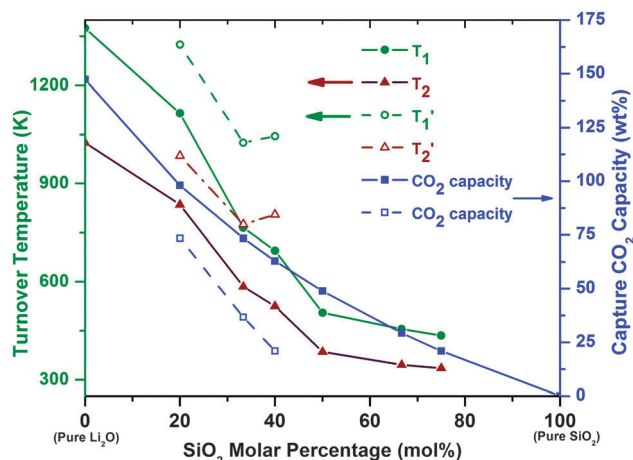

**Fig. 14** The dependence of the turnover temperatures defined in the text and of CO<sub>2</sub> capture capacity on molar percentage of SiO<sub>2</sub> in the silicates for which calculations are reported here.  $T_1$  and  $T_1'$  are the turnover temperatures under pre-combustion conditions with CO<sub>2</sub> partial pressure at 20 bars, while  $T_2$  and  $T_2'$  are the turnover temperatures under post-combustion conditions with CO<sub>2</sub> partial pressure at 0.1 bar. The solid lines indicate conversion of lithium silicates into SiO<sub>2</sub> and Li<sub>2</sub>CO<sub>3</sub> ( $T_1$ ,  $T_2$ ). For those Li<sub>2</sub>O-rich lithium silicates (Li<sub>6</sub>SiO<sub>6</sub>, Li<sub>4</sub>SiO<sub>4</sub>, Li<sub>6</sub>Si<sub>2</sub>O<sub>7</sub>) capturing CO<sub>2</sub>, the data shown in dashed lines indicate their conversion into Li<sub>2</sub>SiO<sub>3</sub> and Li<sub>2</sub>CO<sub>3</sub> ( $T_1'$ ,  $T_2'$ ). The corresponding CO<sub>2</sub> capture capacities are plotted using open blue squares.

operating temperature which falls into the range required for certain existing power plants because the regenerating temperature of pure Li<sub>2</sub>O is too high to be used in practical CO<sub>2</sub> capture technologies.<sup>45,50</sup> In other words, even if one single material (*e.g.* Li<sub>2</sub>O, SiO<sub>2</sub>, *etc.*) may not be a good CO<sub>2</sub> sorbent to fit practical capture needs (certain ranges of  $P_{\text{CO}_2}$  and temperature), by mixing (or doping) two or more solids (*e.g.* Li<sub>2</sub>O + SiO<sub>2</sub>, Li<sub>2</sub>O + ZrO<sub>2</sub>, MgO + Na<sub>2</sub>O, *etc.*) to form a new material (such as lithium silicates, lithium zirconates,<sup>24,30,95</sup> double salts,<sup>96</sup> *etc.*), the resulting material may satisfy the industrial requirements. Generally speaking, when we add more quantities of weak-sorbent (in our case SiO<sub>2</sub>) into a strong sorbent (in our case Li<sub>2</sub>O), the newly formed lithium silicate will have an overall lower CO<sub>2</sub> capture capacity and its turnover temperatures will shift to lower values compared to those obtained for the pure Li<sub>2</sub>O as shown in Fig. 14. From this figure and the data in Table 5, the theoretical CO<sub>2</sub> weight percentage maxima of these lithium silicates are greater than 3 mmol per gram sorbent ( $\sim 15$  wt%). Therefore, all these systems satisfy the required criteria related to the minimum amount of CO<sub>2</sub> capture capacity, and only other issues could limit their applications as CO<sub>2</sub> sorbents.

Based on our results, when we mix two solids A and B to form a new sorbent C, the turnover temperature of the newly resulting system ( $T_C$ ) is located between those of A and B ( $T_A$ ,  $T_B$ ). Here it was assumed that A is a strong CO<sub>2</sub> sorbent while B is a weak CO<sub>2</sub> sorbent and  $T_A > T_B$ . Also, we assumed that the desired operating temperature  $T_O$  is between  $T_A$  and  $T_B$  ( $T_A > T_O > T_B$ ). Now, depending on the properties of A and B, we have typically three scenarios to synthesize the mixing sorbent C: (1)  $T_A \gg T_B$  and the A component is the key part

to capture CO<sub>2</sub>. Our Li<sub>2</sub>O–SiO<sub>2</sub> mixed lithium silicates belong to this category. Li<sub>2</sub>O–ZrO<sub>2</sub> mixed lithium zirconates are also part of this category.<sup>24,30,95</sup> As discussed above, in this case,  $T_A$  is too high to be useful for CO<sub>2</sub> capture. After mixing A and B with adjusted A/B ratio, the  $T_C$  of the newly formed C compound could be close to the  $T_O$  temperature to fit the practical needs; (2)  $T_A \gg T_B$  and B component is the key part to capture CO<sub>2</sub>. In this case, since  $T_B$  is lower than  $T_O$ , mixing A with B will increase the turnover temperature  $T_C$  of the C solid to values closer to  $T_O$ . For example, pure MgO has a very high theoretical CO<sub>2</sub> capture capacity. However, its turnover temperature (250 °C) is lower than the required temperature range of 300–470 °C in warm gas clean up technology, and therefore, it cannot be directly used as a CO<sub>2</sub> sorbent in this technology. By mixing alkali metal oxides M<sub>2</sub>O (M = Na, K, Cs) or carbonates (M<sub>2</sub>CO<sub>3</sub>) with MgO, the corresponding newly formed systems have higher turnover temperatures, making them useful as CO<sub>2</sub> sorbents through the reaction  $\text{MgO} + \text{CO}_2 + \text{M}_2\text{CO}_3 = \text{M}_2\text{Mg}(\text{CO}_3)_2$ ;<sup>96</sup> (3) the  $T_A$  and  $T_B$  are close to each other. In this case, both A and B components are active to capture CO<sub>2</sub>, and the CO<sub>2</sub> capacity of the mixture is the summation of those of A and B. As we know another potential advantage of mixing solids is to increase the surface area of the solids in order to have faster reaction rate. Such a mixing scenario doesn't show too much advantage in shifting the capture temperature, but may enhance the kinetics of the capture process and eventually make the mixtures more efficient. Although there is no such report in the literature, we think such an attempt is worthwhile. Our primary results for the class of lithium silicates can provide some general guidelines to design and synthesize new CO<sub>2</sub> sorbents and in such cases computational modeling can play a decisive role in identifying materials with optimal performance.

## 5. Summary and conclusions

By combining first-principles density functional theory with lattice phonon dynamics, we investigated the electronic and lattice dynamics properties of a series of lithium silicates with different Li<sub>2</sub>O/SiO<sub>2</sub> ratios. Based on the calculated thermodynamic properties of these solids, we further explored their CO<sub>2</sub> capture properties.

The calculated band structures showed that these lithium silicates have larger band-gaps ( $>4.5$  eV). By decreasing the Li<sub>2</sub>O/SiO<sub>2</sub> ratio, the band gap and the VB<sub>1</sub> width of the corresponding lithium silicate increase. In all lithium silicates, the p orbitals of Li have a larger contribution than its s orbital and all of them are involved in forming all the VBs and CB. The p orbitals of O mainly contribute to VB<sub>1</sub> while its s orbital mainly contributes to VB<sub>2</sub>. The upper portion of VB<sub>1</sub> is mainly due to the interactions between Li and O. Both the s and p orbitals of Si contribute to the lower portion of VB<sub>1</sub> and VB<sub>2</sub>.

Based on the calculated phonon dispersions of these lithium silicates, we confirm the stability of the reported crystallographic structure in all but one case. The exception is Li<sub>6</sub>Si<sub>2</sub>O<sub>7</sub> for which the phonon analysis gave two branches of relaxation modes,

indicating the existence of an unstable structure. The instability in this case is associated with relaxation of Si–O tetrahedra in the *xy* plane and is under continuing investigation. By decreasing the Li<sub>2</sub>O/SiO<sub>2</sub> ratio, the vibrational frequencies of the lithium silicates shift to high frequencies. The phonon free energies and entropies obtained from the phonon calculations on these lithium silicates are used to evaluate their thermo-stability, phase transformation, and CO<sub>2</sub> capture properties.

By mixing Li<sub>2</sub>O with SiO<sub>2</sub> in different ratios, all of the resulting lithium silicates are favored thermodynamically to be formed. By adding SiO<sub>2</sub> to a Li<sub>2</sub>O-rich lithium silicate, a Li<sub>2</sub>O-poor lithium silicate could be obtained, and *vice versa*. It is also possible to convert a SiO<sub>2</sub>-rich lithium silicate to one with a high Li<sub>2</sub>O/SiO<sub>2</sub> ratio by adding Li<sub>2</sub>O.

Based on the calculated thermodynamic data for lithium silicates, their CO<sub>2</sub> capture properties (such as the CO<sub>2</sub> capacity, the turnover temperatures, and the heat of reaction) were fully investigated. By increasing the Li<sub>2</sub>O/SiO<sub>2</sub> ratio (from Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub> up to Li<sub>8</sub>SiO<sub>6</sub>), the corresponding lithium silicates were found to have higher CO<sub>2</sub> capture capacities, higher turnover temperatures, and higher heats of reaction. Obviously, the lithium silicate with higher Li<sub>2</sub>O/SiO<sub>2</sub> ratio will require more energy input to be regenerated at higher temperature. For the Li<sub>2</sub>O-rich lithium silicates (Li<sub>8</sub>SiO<sub>6</sub>, Li<sub>4</sub>SiO<sub>4</sub>, Li<sub>6</sub>Si<sub>2</sub>O<sub>7</sub>), when the capture temperature is lower than the turnover temperature of Li<sub>2</sub>SiO<sub>3</sub>, they can absorb CO<sub>2</sub> to form Li<sub>2</sub>CO<sub>3</sub> and SiO<sub>2</sub> with high CO<sub>2</sub> capture capacity. However, if the capture temperature is above the turnover temperature of Li<sub>2</sub>SiO<sub>3</sub>, the products will be Li<sub>2</sub>CO<sub>3</sub> and Li<sub>2</sub>SiO<sub>3</sub> with low CO<sub>2</sub> capture capacity. The SiO<sub>2</sub>-rich lithium silicates (Li<sub>2</sub>Si<sub>2</sub>O<sub>5</sub>, Li<sub>2</sub>Si<sub>3</sub>O<sub>7</sub>) can thermodynamically absorb CO<sub>2</sub> at relatively low temperature with low capture capacity. However, if the temperature is too low, the kinetics of CO<sub>2</sub> capture reaction is too slow as demonstrated by the experiments reported here. Therefore, some tradeoff must be made.

By measuring the isotherms of CO<sub>2</sub> absorbed by lithium silicates, we concluded that the CO<sub>2</sub> capture of lithium silicates is a two-step process. In the first step, the lithium silicate particles react with CO<sub>2</sub> at the particle surface. This superficial reaction involves the formation of an external shell composed of lithium carbonate and a metal oxide or a lithium secondary phase, depending on the initial composition. Once the first stage is complete, the second step corresponding to the bulk diffusion processes must be activated for the silicates to continue CO<sub>2</sub> chemisorption. The second step generally requires an increase in temperature. Our results showed that the second stage corresponding to the bulk diffusion is the controlling step for the kinetics and for the CO<sub>2</sub> capture capacity.

By changing the mixing ratio of Li<sub>2</sub>O and SiO<sub>2</sub>, we can obtain different lithium silicate solids which exhibit different thermodynamic behaviors, such as heats of reaction and turnover temperatures. These results can be used to provide guidelines for designing new CO<sub>2</sub> sorbents. One single material taken in isolation might not be an optimal CO<sub>2</sub> sorbent to fit the particular needs to operate at specific temperature and pressure conditions. By mixing or doping two or more materials to form a new material, it is possible to synthesize new CO<sub>2</sub>

sorbent formulations which can fit the industrial needs. For these purposes, we analyzed and discussed three scenarios for mixing different solid sorbents in an attempt to identify formulations with optimal performance for CO<sub>2</sub> capture applications.

## Appendix

In a multi-phase system constructed by *P* phases with *S* species, the Gibbs free energy is extensive:<sup>97</sup>

$$G = \sum_{j=1}^P G^{(j)} = \sum_{j=1}^P \sum_{i=1}^S \mu_i^{(j)} N_i^{(j)} \quad (\text{A1})$$

where *j* labels phases, *i* labels species,  $N_i^{(j)} = \chi_j n_j^i$ .

In case only CO<sub>2</sub> is in the gas phase, then

$$G = \sum_j x_j F_j + x_g \mu_g^{\text{CO}_2} n_g^c \quad (\text{A2})$$

Because the reactions proceed at fixed gas pressure and temperature and at fixed chemical composition of the solids, the reaction thermodynamics are obtained by minimization of a 'grand canonical' free energy *G'* defined by

$$G' = G - \mu_g^{\text{CO}_2} N_c \quad (\text{A3})$$

where *N<sub>c</sub>* is the total number of carbon atoms. Then since

$$x_g n_g^c = N_c - \sum_{j=1}^{p-1} x_j n_j^c \quad (\text{A4})$$

we rewrite *G'* as

$$G' = \sum_j x_j F_j - \mu_g^{\text{CO}_2} \sum_j x_j n_j^c \quad (\text{A5})$$

which is eqn (6).

## Notes and references

- 1 D. Cruz, S. Bulbulian, E. Lima and H. Pfeiffer, *J. Solid State Chem.*, 2006, **179**, 909–916.
- 2 K. Essaki, M. Kato and K. Nakagawa, *J. Ceram. Soc. Jpn.*, 2006, **114**, 739–742.
- 3 K. Essaki, M. Kato and H. Uemoto, *J. Mater. Sci.*, 2005, **40**, 5017–5019.
- 4 K. Essaki, K. Nakagawa, M. Kato and H. Uemoto, *J. Chem. Eng. Jpn.*, 2004, **37**, 772–777.
- 5 C. Gauer and W. Heschel, *J. Mater. Sci.*, 2006, **41**, 2405–2409.
- 6 J. Ida, R. T. Xiong and Y. S. Lin, *Sep. Purif. Technol.*, 2004, **36**, 41–51.
- 7 M. Kato and K. Nakagawa, *J. Ceram. Soc. Jpn.*, 2001, **109**, 911–914.
- 8 M. Kato, S. Yoshikawa and K. Nakagawa, *J. Mater. Sci. Lett.*, 2002, **21**, 485–487.
- 9 A. Lopez-Ortiz, N. G. P. Rivera, A. R. Rojas and D. L. Gutierrez, *Sep. Sci. Technol.*, 2004, **39**, 3559–3572.
- 10 H. A. Mosqueda, C. Vazquez, P. Bosch and H. Pfeiffer, *Chem. Mater.*, 2006, **18**, 2307–2310.

- 11 B. N. Nair, R. P. Burwood, V. J. Goh, K. Nakagawa and T. Yamaguchi, *Prog. Mater. Sci.*, 2009, **54**, 511–541.
- 12 K. Nakagawa and T. Ohashi, *J. Electrochem. Soc.*, 1998, **145**, 1344–1346.
- 13 K. Nakagawa and T. Ohashi, *Electrochemistry*, 1999, **67**, 618–621.
- 14 T. Okumura, K. Enomoto, N. Togashi and K. Oh-ishi, *J. Ceram. Soc. Jpn.*, 2007, **115**, 491–497.
- 15 M. Olivares-Marin, T. C. Drage and M. M. Maroto-Valer, *Int. J. Greenhouse Gas Control*, 2010, **4**, 623–629.
- 16 R. Rodriguez-Mosqueda and H. Pfeiffer, *J. Phys. Chem. A*, 2010, **114**, 4535–4541.
- 17 M. J. Venegas, E. Fregaso-Israel, R. Escamilla and H. Pfeiffer, *Ind. Eng. Chem. Res.*, 2007, **46**, 2407–2412.
- 18 R. Xiong, J. Ida and Y. S. Lin, *Chem. Eng. Sci.*, 2003, **58**, 4377–4385.
- 19 T. Yamaguchi, T. Niitsuma, B. N. Nair and K. Nakagawa, *J. Membr. Sci.*, 2007, **294**, 16–21.
- 20 X. S. Yin, Q. H. Zhang and J. G. Yu, *Inorg. Chem.*, 2011, **50**, 2844–2850.
- 21 M. Seggiani, M. Puccini and S. Vitolo, *Int. J. Greenhouse Gas Control*, 2011, **5**, 741–748.
- 22 J. Ortiz-Landeros, C. Gomez-Yanez and H. Pfeiffer, *J. Solid State Chem.*, 2011, **184**, 2257–2262.
- 23 Y. Duan and K. Parlinski, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2011, **84**, 104113.
- 24 Y. Duan, *J. Renewable Sustainable Energy*, 2012, **4**, 013109.
- 25 B. Y. Li, Y. Duan, D. Luebke and B. Morreale, *Appl. Energy*, 2013, **102**, 1439–1447.
- 26 M. E. Bretado, V. G. Velderrain, D. L. Gutierrez, V. Collins-Martinez and A. L. Ortiz, *Catal. Today*, 2005, **107–108**, 863–867.
- 27 T. Okumura, Y. Matsukura, K. Gotou and K. Oh-Ishi, *J. Ceram. Soc. Jpn.*, 2008, **116**, 1283–1288.
- 28 Y. J. Wang, L. Qi and W. J. Jiang, *Chin. J. Inorg. Chem.*, 2006, **22**, 268–272.
- 29 M. D. Donne, E. Gunther, G. Schumacher, G. Sordon, D. Vollath, H. Wedemeyer and H. Werle, *J. Nucl. Mater.*, 1991, **179**, 796–799.
- 30 Y. Duan, *J. Renewable Sustainable Energy*, 2011, **3**, 013102.
- 31 J. Ortiz-Landeros, C. Gomez-Yanez, L. M. Palacios-Romero, E. Lima and H. Pfeiffer, *J. Phys. Chem. A*, 2012, **116**, 3163–3171.
- 32 F. Durán-Muñoz, I. C. Romero-Ibarra and H. Pfeiffer, *J. Mater. Chem. A*, 2013, **1**, 3919–3925.
- 33 H. Migge, *J. Nucl. Mater.*, 1988, **151**, 101–107.
- 34 D. Vollath and H. Wedemeyer, *J. Nucl. Mater.*, 1986, **143**, 334–338.
- 35 F. C. Kracek, *J. Phys. Chem.*, 1930, **34**, 2641–2650.
- 36 S. Claus, H. Kleykamp and W. SmykatzKloss, *J. Nucl. Mater.*, 1996, **230**, 8–11.
- 37 H. Kruger, V. Kahlenberg and R. Kaindl, *J. Solid State Chem.*, 2007, **180**, 922–928.
- 38 W. Y. Ching, Y. P. Li, B. W. Veal and D. J. Lam, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1985, **32**, 1203–1207.
- 39 T. Uchino and T. Yoko, *J. Phys. Chem. B*, 1999, **103**, 1854–1858.
- 40 T. Uchino and T. Yoko, *J. Phys. Chem. B*, 1998, **102**, 8372–8378.
- 41 K. Munakata and Y. Yokoyama, *J. Nucl. Sci. Technol.*, 2001, **38**, 915–918.
- 42 J. C. Du and L. R. Corrales, *J. Chem. Phys.*, 2006, **125**, 114702.
- 43 J. C. Du and L. R. Corrales, *J. Non-Cryst. Solids*, 2006, **352**, 3255–3269.
- 44 J. C. Du and L. R. Corrales, *J. Phys. Chem. B*, 2006, **110**, 22346–22352.
- 45 Y. Duan and D. C. Sorescu, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2009, **79**, 014301.
- 46 G. Kresse and J. Hafner, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1993, **47**, 558–561.
- 47 G. Kresse and J. Furthmuller, *Comput. Mater. Sci.*, 1996, **6**, 15–50.
- 48 Y. Duan, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2008, **77**, 045332.
- 49 Y. Duan and D. C. Sorescu, *J. Chem. Phys.*, 2010, **133**, 074508.
- 50 Y. Duan, B. Zhang, D. C. Sorescu and J. K. Johnson, *J. Solid State Chem.*, 2011, **184**, 304–311.
- 51 H. J. Monkhorst and J. D. Pack, *Phys. Rev. B: Solid State*, 1976, **13**, 5188–5192.
- 52 C. J. Bradley and A. P. Cracknell, *The mathematical theory of symmetry in solids*, Clarendon press, Oxford, 1972.
- 53 S. Cristol, J. F. Paul, E. Payen, D. Bougeard, S. Clemendot and F. Hutschka, *J. Phys. Chem. B*, 2002, **106**, 5659–5667.
- 54 Y. Duan, D. Luebke and H. W. Pennline, *Int. J. Clean Coal Energy*, 2012, **1**, 1–11.
- 55 B. Zhang, Y. Duan and J. K. Johnson, *J. Chem. Phys.*, 2012, **136**, 064516.
- 56 M. W. J. Chase, *J. Phys. Chem. Ref. Data*, 1998, **9**, 1–1951.
- 57 A. R. Akbarzadeh, V. Ozolins and C. Wolverton, *Adv. Mater.*, 2007, **19**, 3233–3239.
- 58 V. Ozolins, E. H. Majzoub and C. Wolverton, *J. Am. Chem. Soc.*, 2009, **131**, 230–237.
- 59 R. B. Darst, *Introduction to linear programming: applications and extensions*, Marcel Dekker Inc., New York, 1991.
- 60 R. Hofmann and R. Hoppe, *Z. Anorg. Allg. Chem.*, 1987, **555**, 118–128.
- 61 H. Vollenkl, A. Wittman and H. Nowotny, *Monatsh. Chem.*, 1969, **100**, 295–303.
- 62 K. F. Hesse, *Acta Crystallogr., Sect. B: Struct. Crystallogr. Cryst. Chem.*, 1977, **33**, 901–902.
- 63 H. Voellenkle, *Z. Kristallogr.*, 1981, **154**, 77–81.
- 64 F. Liebau, *Acta Crystallogr.*, 1961, **14**, 389–395.
- 65 R. I. Smith, R. A. Howie, A. R. West, A. Aragonpina and M. E. Villafuertecastreion, *Acta Crystallogr., Sect. C: Cryst. Struct. Commun.*, 1990, **46**, 363–365.
- 66 S. Hull, T. W. D. Farley, W. Hayes and M. T. Hutchings, *J. Nucl. Mater.*, 1988, **160**, 125–134.
- 67 Y. Idemoto, J. W. Richardson, N. Koura, S. Kohara and C. K. Loong, *J. Phys. Chem. Solids*, 1998, **59**, 363–376.
- 68 N. R. Keskar and J. R. Chelikowsky, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1992, **46**, 1–13.
- 69 M. Ledyastuti, Y. F. Liang, C. R. Miranda and T. Matsuoka, *J. Chem. Phys.*, 2012, **137**, 034703.

- 70 J. R. Chelikowsky, N. Troullier, J. L. Martins and H. E. King, Jr., *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1991, **44**, 489–497.
- 71 T. Demuth, Y. Jeanvoine, J. Hafner and J. G. Angyan, *J. Phys.: Condens. Matter*, 1999, **11**, 3833–3874.
- 72 G. A. Lager, J. D. Jorgensen and F. J. Rotella, *J. Appl. Phys.*, 1982, **53**, 6751–6756.
- 73 B. H. W. S. Dejong, D. Ellerbroek and A. L. Spek, *Acta Crystallogr., Sect. B: Struct. Sci.*, 1994, **50**, 511–518.
- 74 F. D. Murnaghan, *Am. J. Math.*, 1937, **59**, 235–260.
- 75 F. Birch, *Phys. Rev.*, 1947, **71**, 809–824.
- 76 HSC Chemistry software 6.1, Pori: Outotec Research Oy, [www.outotec.com/hsc](http://www.outotec.com/hsc), 2006.
- 77 E. Gnani, S. Reggiani, R. Colle and M. Rudan, *IEEE Trans. Electron Devices*, 2000, **47**, 1795–1803.
- 78 N. Choudhury and S. L. Chaplot, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2006, **73**, 094304.
- 79 B. Dorner, H. Grimm and H. Rzany, *J. Phys. C: Solid State Phys.*, 1980, **13**, 6607–6612.
- 80 M. D. Donne, A. Goraieb, G. Piazza and G. Sordon, *Fusion Eng. Des.*, 2000, **49**, 513–519.
- 81 R. B. Khomane, B. K. Sharma, S. Saha and B. D. Kulkarni, *Chem. Eng. Sci.*, 2006, **61**, 3415–3418.
- 82 M. L. Gray, K. J. Champagne, D. Fauth, J. P. Baltrus and H. Pennline, *Int. J. Greenhouse Gas Control*, 2008, **2**, 3–8.
- 83 DOE-NETL, “Cost and Performance Baseline for Fossil Energy Plants”, Volume 1: Bituminous Coal and Natural Gas to Electricity Final Report, [http://www.netl.doe.gov/energy-analyses/baseline\\_studies.html](http://www.netl.doe.gov/energy-analyses/baseline_studies.html), 2007.
- 84 Z. Qi, H. Daying, L. Yang, Y. Qian and Z. Zibin, *AIChE J.*, 2013, **59**, 901–911.
- 85 V. L. Mejia-Trejo, E. Fregoso-Israel and H. Pfeiffer, *Chem. Mater.*, 2008, **20**, 7171–7176.
- 86 K. Wang, X. Guo, P. F. Zhao, F. Z. Wang and C. G. Zheng, *J. Hazard. Mater.*, 2011, **189**, 301–307.
- 87 J. Ortiz-Landeros, T. L. Avalos-Rendon, C. Gomez-Yanez and H. Pfeiffer, *J. Therm. Anal. Calorim.*, 2012, **108**, 647–655.
- 88 L. Martinez-dlCruz and H. Pfeiffer, *J. Phys. Chem. C*, 2012, **116**, 9675–9680.
- 89 I. Alcerreca-Corte, E. Fregoso-Israel and H. Pfeiffer, *J. Phys. Chem. C*, 2008, **112**, 6520–6525.
- 90 T. Avalos-Rendon, V. H. Lara and H. Pfeiffer, *Ind. Eng. Chem. Res.*, 2012, **51**, 2622–2630.
- 91 T. Avalos-Rendon, J. Casa-Madrid and H. Pfeiffer, *J. Phys. Chem. A*, 2009, **113**, 6919–6923.
- 92 L. Martinez-dlCruz and H. Pfeiffer, *Ind. Eng. Chem. Res.*, 2010, **49**, 9038–9042.
- 93 X. S. Yin, M. A. Song, Q. H. Zhang and J. G. Yu, *Ind. Eng. Chem. Res.*, 2010, **49**, 6593–6598.
- 94 M. Kato, K. Nakagawa, K. Essaki, Y. Maezawa, S. Takeda, R. Kogo and Y. Hagiwara, *Int. J. Appl. Ceram. Technol.*, 2005, **2**, 467–475.
- 95 Y. Duan, *Phys. Chem. Chem. Phys.*, 2013, **15**, 9752–9760.
- 96 K. Zhang, X. S. Li, Y. Duan, P. Singh, D. L. King and L. Li, *Int. J. Greenhouse Gas Control*, 2013, **12**, 351–358.
- 97 J. W. Halley, *Statistical Mechanics From first principles to macroscopic phenomena*, Cambridge University Press, New York, 2007.