

Original Article: Drug Delivery

pH-controlled drug loading and release from biodegradable microcapsules

Qinghe Zhao, PhD,^a Bingyun Li, PhD^{a,b,c,*}

^aDepartment of Orthopaedics, School of Medicine, West Virginia University, Morgantown, West Virginia

^bWVNano Initiative, Morgantown, West Virginia

^cDepartment of Chemical Engineering, College of Engineering and Mineral Resources, West Virginia University, Morgantown, West Virginia, USA

Abstract

Microcapsules made of biopolymers are of both scientific and technological interest and have many potential applications in medicine, including their use as controlled drug delivery devices. The present study makes use of the electrostatic interaction between polycations and polyanions to form a multilayered microcapsule shell and also to control the loading and release of charged drug molecules inside the microcapsule. Micron-sized calcium carbonate (CaCO₃) particles were synthesized and integrated with chondroitin sulfate (CS) through a reaction between sodium carbonate and calcium nitrate tetrahydrate solutions suspended with CS macromolecules. Oppositely charged biopolymers were alternately deposited onto the synthesized particles using electrostatic layer-by-layer self-assembly, and glutaraldehyde was introduced to cross-link the multilayered shell structure. Microcapsules integrated with CS inside the multilayered shells were obtained after decomposition of the CaCO₃ templates. The integration of a matrix (i.e., CS) permitted the subsequent selective control of drug loading and release. The CS-integrated microcapsules were loaded with a model drug, bovine serum albumin labeled with fluorescein isothiocyanate (FITC-BSA), and it was shown that pH was an effective means of controlling the loading and release of FITC-BSA. Such CS-integrated microcapsules may be used for controlled localized drug delivery as biodegradable devices, which have advantages in reducing systemic side effects and increasing drug efficacy.

© 2008 Elsevier Inc. All rights reserved.

Key words: Microcapsule; Controlled release; Drug delivery; Biodegradable

One major focus of drug delivery is to develop suitable carriers for therapeutic molecules.¹ The recent availability of many protein therapeutics has challenged and thus stimulated research on developing advanced drug delivery systems. Polyelectrolyte microcapsules, introduced in 1998,^{2,3} have attracted great attention as potential drug

carriers^{4,5} as a result of their ease of preparation, avoidance of hazardous procedures, use of simple building blocks, and the potential introduction of multifunctionality. So far, most of the effort has been dedicated to developing polyelectrolyte microcapsules using poly(styrene sulfonate) (PSS), poly(allylamine hydrochloride) (PAH), and poly(acrylic acid) as capsule shell components. For biomedical applications, especially for drug delivery, biodegradable polyelectrolyte microcapsules would be preferred to nondegradable ones, and there is increasing interest in microcapsules of biopolymers including polypeptides and polysaccharides. For instance, polysaccharides, proteins, polypeptides, and lipids⁶⁻¹⁴ have been used to form multilayer shells onto colloids such as melamine formaldehyde (MF), polystyrene (PS), poly-D,L-lactic acid, and calcium carbonate (CaCO₃) particles to fabricate polyelectrolyte microcapsules. Recently, De Geest et al. have reported a new type of

Received 2 November 2007; accepted 3 June 2008.

Financial support from National Aeronautics and Space Administration West Virginia Experimental Program to Stimulate Competitive Research, West Virginia University (WVU) Program to Stimulate Competitive Research, and WVU Senate Grant are acknowledged. No commercial associations, current and within the past 5 years, that might pose a potential, perceived, or real conflict of interest, were reported by the authors of this article.

*Corresponding author. Biomaterials, Bioengineering and Nanotechnology Laboratory, Department of Orthopaedics, School of Medicine, West Virginia University, Morgantown, West Virginia 26506-9196.

E-mail address: bli@hsc.wvu.edu (B. Li).

1549-9634/\$ – see front matter © 2008 Elsevier Inc. All rights reserved.

doi:10.1016/j.nano.2008.06.004

microcapsules.¹⁵ These microcapsules have self-rupturing properties and may be used as pulsed drug delivery systems. In addition, advances have been made in developing enzymatically degradable polyelectrolyte microcapsules, which may lead to enzyme-responsive release of encapsulated drugs.^{16,17} For instance, chitosan–dextran sulfate microcapsules have been prepared and can degrade in the presence of chitosanase,¹⁶ and poly(L-arginine)–dextran sulfate microcapsules may degrade in a cell culture system and could have promising potential for intracellular drug delivery.¹⁷ Meanwhile, there is increasing attention on *in vitro* and *in vivo* studies of the interactions between biodegradable polyelectrolyte microcapsules and cells and tissues.^{17–19}

Polyelectrolyte microcapsules, compared to traditional liposomes, have controllable stability and high permeability for polar molecules,^{20,21} and have attracted great attention for encapsulation of various materials. Polyelectrolyte microcapsules have been used as carriers of drugs; the simplest method of encapsulation is to use the template itself as a substance to be encapsulated.^{8,22} However, such substances should be able to form colloidal particles and have low solubility under the assembly conditions. This substantially limits the application of such an encapsulation method, in that there are very few such materials. Also, drugs may be preloaded into the templates, usually porous and decomposable, before the formation of microcapsule shells^{23,24}; however, decomposition of the templates may affect the integrity of the capsules and may change the properties of the drugs.

Alternatively, drugs can be loaded and released by finely tuning the capsule interior or wall properties. In efforts devoted to controlling drug loading, preformed hollow capsules have been loaded with a variety of materials by changing the permeability of the capsule wall, the swelling–shrinking behavior of capsules, and the solubility of small molecules.^{25–32} More recently, a spontaneous encapsulation of charged molecules based on electrostatic interaction with a precursor matrix was reported.^{31,33–37} Macromolecules such as PAH have been immobilized in capsules as a preloaded polymer by co-precipitating PAH with multivalent metal ions into decomposable templates, followed by multilayer shell formation and template decomposition.^{34,35} PSS has also been entrapped as a precursor polymer within polyelectrolyte microcapsules through a polymerization synthesis process.³³ The polymerization approach has been applied to form several polymers within microcapsules. However, there are some concerns such as uncontrollable formation of polymers within the capsule shells and thereby modification of the properties and possible destruction of the capsule shells.³³ There have also been several efforts dedicated to controlling drug release, with polyelectrolyte microcapsules responsive to light,^{38–41} magnetism,⁴² pH (PSS/PAH-based),^{43–45} salt,^{46,47} glucose,^{48,49} and redox^{10,50} having emerged recently. Such drug delivery systems, releasing their payload in response to internal or external

triggers, offer great advantages. However, the development of stimuli-responsive polyelectrolyte microcapsules, especially those made of biopolymers, is still in the early stage.

Because of the short development history of polyelectrolyte microcapsule technology, great potential for biomedical applications, and the almost infinite possibility of varying parameters in the preparation process, further studies are needed to advance the development of biodegradable drug delivery systems. The focus of this work was to develop biodegradable microcapsules with controllable loading and release capabilities for drug delivery applications. CaCO₃ particles, integrated with chondroitin sulfate (CS), were prepared, and CS, a polyanion, was used as a tool to control the subsequent loading and release of charged drugs. The CaCO₃ particles integrated with CS are referred to as CaCO₃ (CS). Poly-L-lysine (PLL), a polycation, and CS were alternately deposited onto CaCO₃(CS) particles, and cross-linking of the multilayered shell was achieved using glutaraldehyde (GA), which has been extensively used on scaffolds and implants in animals and humans. No apparent histological or other evidence of toxicity related to the use of GA has been observed.⁵¹ GA was also used to cross-link multilayered microcapsules of PAH and PSS,⁵² and of chitosan and alginate.⁵³ No cytotoxicity was detected in the *in vitro* studies of human fibroblasts cultured with GA-cross-linked multilayered microcapsules.⁵³ Microcapsules with CS integrated inside the shells were obtained after decomposition of the templates (i.e., CaCO₃ particles) using disodium ethylenediaminetetraacetic acid (EDTA). A model drug, bovine serum albumin labeled with fluorescein isothiocyanate (FITC-BSA), was successfully incorporated into the microcapsules through its electrostatic interaction with the CS macromolecules integrated inside the multilayered shells. The control of loading and release of FITC-BSA by means of pH was studied.

Methods

Materials

Poly-L-lysine hydrobromide (PLL, MW 150–300 kDa), chondroitin sulfate sodium salt (CS), glycine, sodium carbonate (Na₂CO₃), calcium nitrate tetrahydrate (Ca(NO₃)₂), FITC-BSA, and GA were purchased from Sigma (St. Louis, Missouri). EDTA was obtained from Fisher (Fair Lawn, New Jersey), and quartz slides were purchased from Electron Microscopy Sciences (Hatfield, Pennsylvania). A 0.05 M glycine solution of pH 5.5 was prepared and used throughout this study. PLL (1 mg/mL) and CS (1 mg/mL) solutions were prepared by dissolving PLL and CS, respectively, in the glycine solution. To quantify the amount of BSA loaded or released, its labeled product (FITC-BSA) was used, and its solutions (1 mg/mL) of pH 3.4, 3.8, 4.2, 4.6, and 5.0 were prepared. Solutions of pH 7.4, 5.0, and 1.0 were also prepared for the FITC-BSA release study.

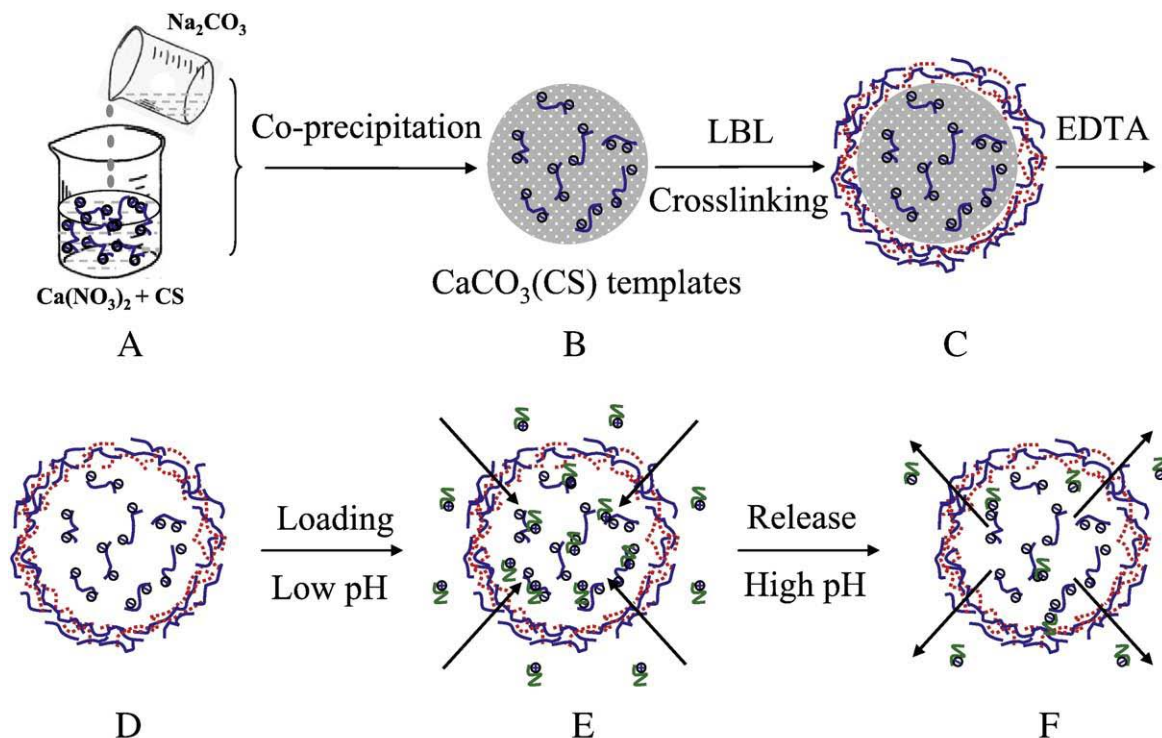





Figure 1. Schematic diagram for the preparation of CS-integrated multilayered microcapsules and related loading and release of FITC-BSA. **A**→**B**, Preparation of CS-integrated CaCO_3 templates. **B**→**C**, Self-assembly and cross-linking of multilayered shell on $\text{CaCO}_3(\text{CS})$ templates. **C**→**D**, Decomposition of the CaCO_3 templates and formation of CS-integrated multilayered microcapsules. **D**→**E**, Loading of BSA into CS-integrated microcapsules at a pH at which BSA has net positive charges. **E**→**F**, Release of BSA from CS-integrated microcapsules at neutral pH where BSA has net negative charges.  CS,  Cross-linked multilayered shell,  BSA. The net charge of BSA is positive below its pI (pH 5.0) and negative above its pI.

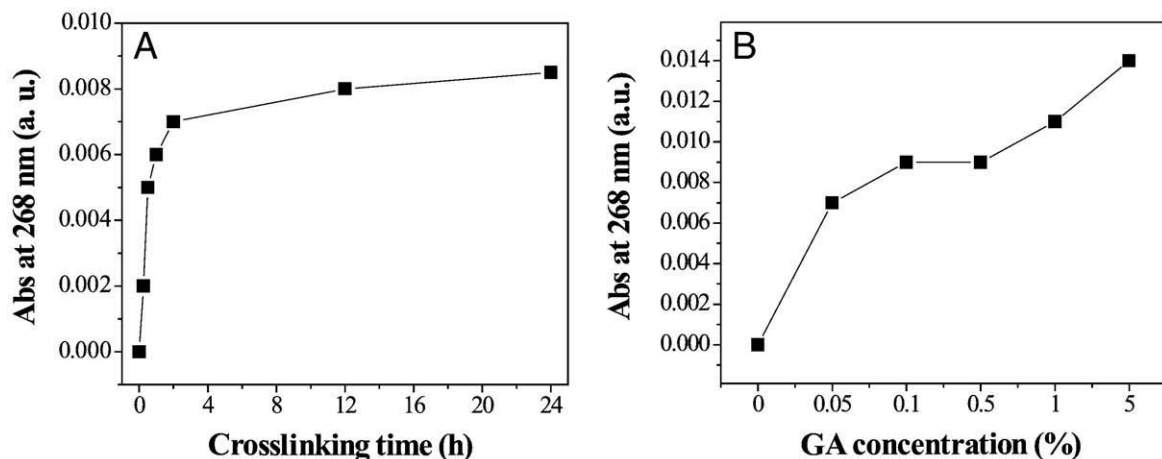


Figure 2. Absorbance of $(\text{PLL-CS})_5$ multilayers on quartz slides (**A**) after cross-linking using 0.5% GA as a function of time, and (**B**) after cross-linking with different concentrations of GA for 24 hours.

Preparation of CaCO_3 microparticles integrated with CS

CaCO_3 microparticles integrated with CS were synthesized by mineralization of Na_2CO_3 and $\text{Ca}(\text{NO}_3)_2$ solutions suspended with CS (Figure 1, **A**→**B**). A 100-mL 0.33 M $\text{Ca}(\text{NO}_3)_2$ solution was mixed with 2 mL of 10% (w/v) CS

solution, to which 100 mL 0.33 M Na_2CO_3 solution was rapidly poured under agitation. CaCO_3 microparticles were formed immediately and collected through centrifugation. CS content in the $\text{CaCO}_3(\text{CS})$ microparticles was measured by inductively coupled plasma optical emission spectroscopy (ICP-OES; Varian Inc., Palo Alto, California). Briefly,

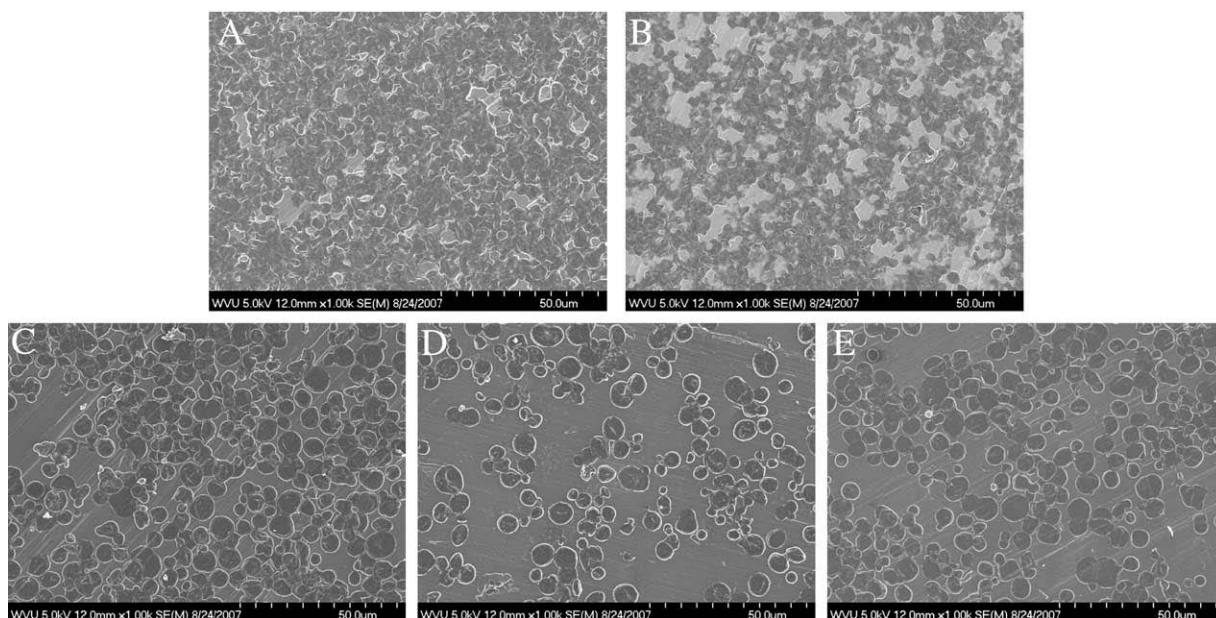


Figure 3. Scanning electron microscope images of (PLL-CS)₅ microcapsules cross-linked for 24 hours using GA at a concentration of (A) 0.05% (v/v), (B) 0.1% (v/v), (C) 0.5% (v/v), (D) 1% (v/v), and (E) 5% (v/v).

0.5 g CaCO₃(CS) microparticles were dissolved in 5 mL hydrochloric acid (HCl) and 10 mL nitric acid (HNO₃), then supplemented with deionized water to 50 mL. The solution was heated at 118°C for 2.5 hours, then cooled to ambient temperature (25°C). Deionized water was added to bring the solution volume back to 50 mL, and the solution was analyzed by ICP-OES.

PLL-CS multilayer assembly and microcapsule preparation

Multilayered microcapsules were fabricated using electrostatic layer-by-layer (LBL) self-assembly nanotechnology. PLL and CS were alternately assembled onto CaCO₃(CS) microparticles. CaCO₃(CS) colloidal particles (200 mg) were rinsed twice with the glycine solution and then incubated in 1 mg/mL PLL solution for 10 minutes. The particles were then washed three times by immersing in glycine solution for 1 minute followed by centrifugation at 5000 rpm for 30 seconds. In the next step, the microparticles were incubated in 1 mg/mL CS solution for 10 minutes, followed by three washings. Repeating the deposition of PLL and CS led to the formation of PLL-CS multilayers with the desired number of layers on CaCO₃(CS) microparticles (Figure 1, B→C). After completion of the multilayer assembly, the template-shell particles were subjected to cross-linking using GA at ambient temperature (Figure 1, B→C), and the particles were treated with glycine solution overnight to eliminate any unreacted aldehyde groups. The template-shell particles were rinsed three times in deionized water and then transferred to 30 mL 0.1 M EDTA solution for 1 hour to decompose the CaCO₃ templates (Figure 1, C→D); this process was repeated once, and microcapsules integrated with CS were obtained. The prepared micro-

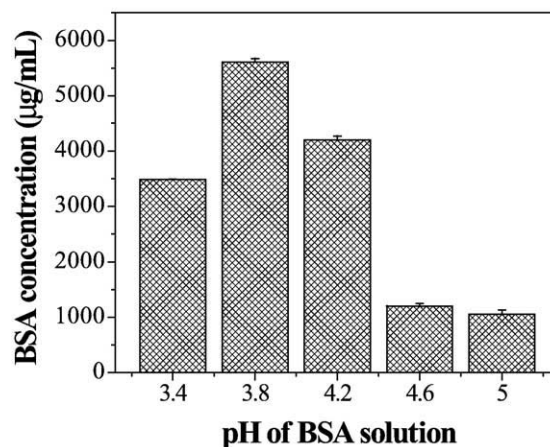


Figure 4. FITC-BSA concentrations in the microcapsule interior as a function of pH of BSA solution.

capsules were washed three times in deionized water before further use. The morphology of the CS-integrated microcapsules was examined using scanning electron microscopy (Hitachi S-4700; Hitachi, Tokyo Japan). Similar deposition and cross-linking procedures (with no centrifugation) were used to prepare PLL-CS multilayered films on quartz slides, which allowed monitoring of the multilayer formation using an ultraviolet-visible (UV-vis) spectrophotometer (Biomate 3; Thermo Scientific, Madison, Wisconsin).

Loading of BSA into CS-integrated microcapsules

FITC-BSA was used as a model drug, and the effect of pH on drug loading was studied. The pH of FITC-BSA studied

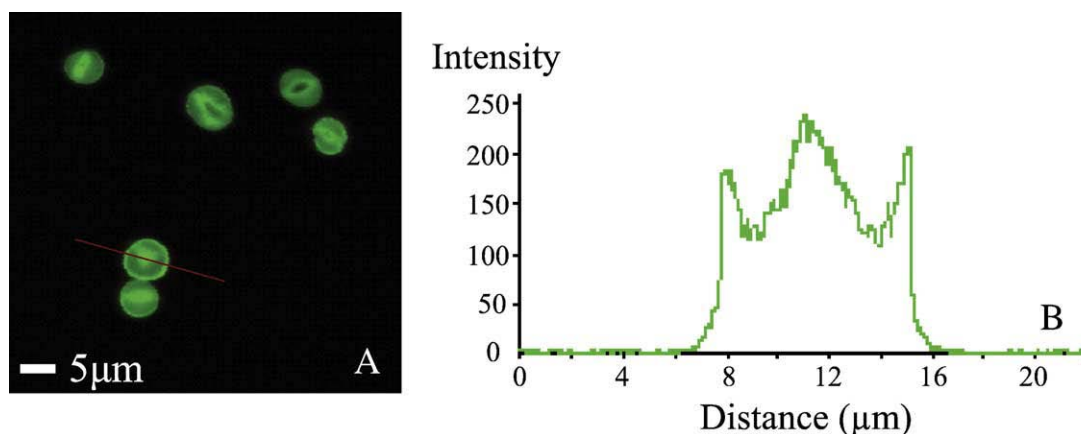


Figure 5. Loading of FITC-BSA within CS-integrated (PLL-CS)₅ microcapsules at pH 3.8. (A), Confocal laser scanning microscope image; (B), fluorescence profile of the microcapsule shown in (A).

was in the range of 3.4 to 5.0. After mixing 2×10^8 microcapsules with 200 μL 1 mg/mL FITC-BSA, the mixture was incubated for 12 hours at ambient temperature, followed by centrifugation at 3500 rpm for 5 minutes. FITC-BSA was quantified, using a UV-vis spectrophotometer, according to its absorbance peak at 458 nm. Raw data were converted to concentration ($\mu\text{g/mL}$) of BSA using the standard curves obtained at various pH values (data not shown). The loading of FITC-BSA was also confirmed using a Zeiss LSM 510 confocal laser scanning microscope (Thornwood, New York).

Release profiles of BSA from CS-integrated microcapsules

After mixing 2×10^8 microcapsules with 200 μL of 1 mg/mL FITC-BSA solution at pH 3.8, the mixture was incubated at ambient temperature for 12 hours. After centrifugation at 3500 rpm for 5 minutes and removal of the supernatant, the FITC-BSA-loaded microcapsules were mixed with 1 mL phosphate-buffered saline (PBS; pH 7.4) or 1 mL HCl solution (pH 5.0 or 1.0) and incubated at ambient temperature under gentle shaking. A 200- μL aliquot of supernatant was taken out at a given time and supplemented with 200 μL fresh PBS or HCl solution. Each 200 μL of supernatant was diluted with PBS or HCl solution, the absorbance of FITC-BSA at 458 nm was recorded, and the cumulative release of FITC-BSA was calculated. Statistical analysis of the release at different pH values (i.e., pH values 7.4, 5.0, and 1.0) at certain time periods (i.e., 30 and 65 minutes) was conducted. One-way ANOVA and Duncan's multiple-range test for post hoc comparisons were carried out, and $\alpha = 0.05$ significant level was used.

Results

In this study, CaCO_3 microparticles integrated with CS were prepared, and LBL was applied to form multilayered shells on the particles. After dissociation of the CaCO_3 particles, polyelectrolyte microcapsules were obtained, and

the integration of CS inside the capsules was intended to alter the physical properties of the capsule interior, which would allow control of subsequent drug loading and release via pH. A model drug, FITC-BSA, was loaded and its release investigated. pH was explored as a means to control the loading and release of FITC-BSA. It should be pointed out that our focus was to study the effect of pH on the loading and release of BSA, and the impact of pH on structural change or bioactivity of BSA was not investigated.

Preparation of multilayered microcapsules

$\text{CaCO}_3(\text{CS})$ microparticles were prepared by mineralization of Na_2CO_3 and $\text{Ca}(\text{NO}_3)_2$ solutions suspended with CS (Figure 1, A→B). ICP-OES tests showed that there was approximately 1.8 wt% CS inside the $\text{CaCO}_3(\text{CS})$ microparticles. The diameter of the $\text{CaCO}_3(\text{CS})$ microparticles was found in the range of 3 to 6 μm , which was obtained from scanning electron microscopic images of 50 randomly selected particles. To form microcapsules, oppositely charged polyelectrolytes (i.e., PLL and CS) were deposited on $\text{CaCO}_3(\text{CS})$ microparticles using LBL technology (Figure 1, B→C). EDTA was used to decompose the CaCO_3 templates and to obtain microcapsules (Figure 1, C→D). Energy-dispersive x-ray analysis showed no calcium in the microcapsule samples (data not shown).

The stability of microcapsules was improved by cross-linking using GA. It was reported that the aldehyde and amine groups react and produce $-\text{C}=\text{N}-$ bonds (Schiff base) that have a characteristic peak at a wavelength around 268 nm.⁵² Conditions for cross-linking were optimized based on the study on quartz slides, which allowed us to monitor formation of PLL-CS multilayered coatings using a UV-vis spectrophotometer. Figure 2 shows the absorbance spectra of PLL-CS multilayers at 268 nm. Cross-linking was very effective in the first 2 hours and continued to increase the absorbance of the coatings and thereby the mass deposited up to 24 hours (Figure 2, A). Absorbance of the multilayered coatings also increased with the increase of GA

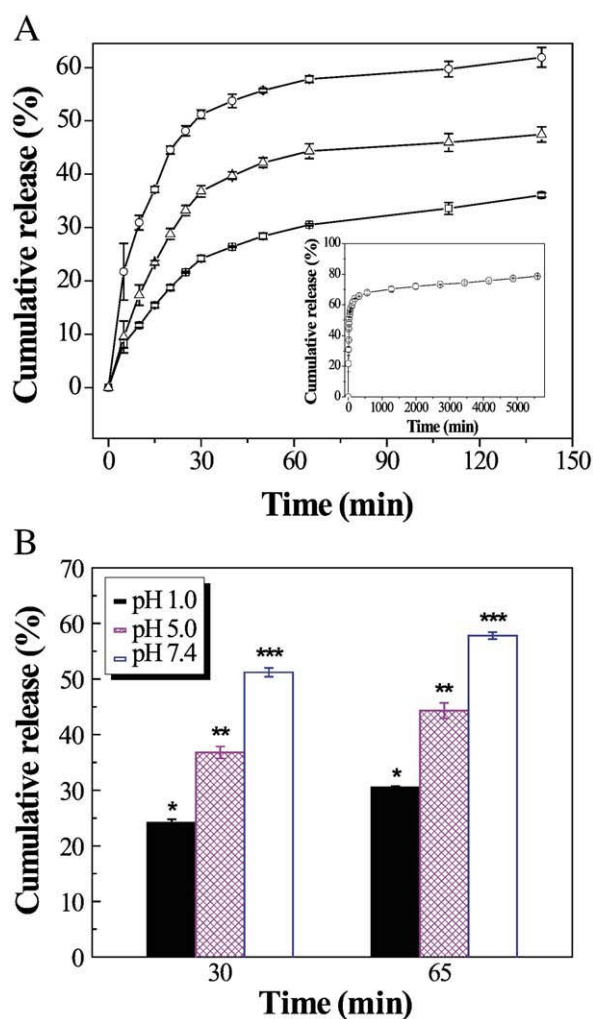


Figure 6. FITC-BSA cumulative release from CS-integrated microcapsules versus incubation time. (A), Release profiles at pH values 7.4, 5.0, and 1.0. The inset is the release of FITC-BSA at pH 7.4 for up to 5600 minutes. (B), Release of FITC-BSA at 30 and 65 minutes. (*)Release was significantly different between the pH values tested. Release was conducted at 37°C at pH 7.4 (○), 5.0 (△), and 1.0 (□) solutions.

concentration, in the range of 0 to 5% (Figure 2, B). Correspondingly, stable microcapsules (Figure 3, C–E) were obtained after cross-linking for 24 hours when GA in the range of 0.5% to 5% was used.

pH-controlled loading of BSA inside the CS-integrated microcapsules

pH was applied to control the loading of FITC-BSA, a model protein drug, into the CS-integrated microcapsules (Figure 1, D→E). Figure 4 shows that the loading of FITC-BSA varied remarkably with pH changes. The microcapsules had the lowest loading of FITC-BSA at pH 5.0. The loading of FITC-BSA increased substantially, from 1.0 mg/mL to 5.6 mg/mL, as the pH decreased from 5.0 to 3.8, and maximum loading of FITC-BSA was reached at pH 3.8. The loading of FITC-BSA decreased as pH decreased from 3.8 to

3.4. The loading of FITC-BSA inside CS-integrated microcapsules was further confirmed by confocal laser scanning microscopic images (Figure 5). FITC-BSA was incorporated both in the capsule interior and also within the multilayered shells, and high fluorescent intensity was observed in the microcapsule cores (Figure 5, B).

pH-controlled release of BSA from the CS-integrated microcapsules

pH was used to trigger or tune the release of encapsulated FITC-BSA from the CS-integrated microcapsules (Figure 1, E→F); the release profiles are shown in Figure 6, A. There was a burst release at the early stage (0–65 minutes), followed by a sustained release (Figure 6, A, inset). The release rate of BSA was higher at a higher pH. Sixty percent of BSA was released at 65 minutes at pH 7.4, and by contrast, only 44% and 30% of BSA were released at pH 5.0 and 1.0, respectively. The release (e.g., at 30 and 65 minutes) was significantly different between pH values 7.4, 5.0, and 1.0 (Figure 6, B).

Discussion

Development of biodegradable drug delivery systems with controllable loading and release capabilities is of importance. Despite the progress made in the last couple of years in preparation of polyelectrolyte microcapsules, the control of drug loading and release from polyelectrolyte microcapsules is still a challenging task for researchers in biotechnology and medicine. The present study reports a new strategy to load charged drug molecules in polyelectrolyte microcapsules for triggered or sustained release. Electrostatic interaction is used to control the loading and release of a model drug (FITC-BSA) by integrating CS into the biopolymer microcapsules. As shown in Figure 1, we intended to incorporate CS macromolecules inside the templates (CaCO₃ particles) to control the subsequent capture and release of charged drug molecules after microcapsule formation and template removal. We prepared CaCO₃(CS) microparticles by mineralization of Na₂CO₃ and Ca(NO₃)₂ solutions suspended with CS (Figure 1, A→B). CS was incorporated in the CaCO₃ particles, as shown by ICP-OES tests: approximately 1.8 wt% CS was found inside the CaCO₃(CS) microparticles. LBL methodology was successfully used to build a multilayer of PLL and CS—(PLL-CS)₅—on the CaCO₃(CS) microparticles (Figure 1, B→C). To enhance stability of the polyelectrolyte multilayers, GA was introduced and cross-linking was achieved through the reaction of aldehyde groups of GA with amino groups of PLL. As shown in Figures 2 and 3, the stability of microcapsules could be controlled by cross-linking time and concentration of GA, and stable microcapsules were prepared after cross-linking.

The CaCO₃ templates were then removed using EDTA, and microcapsules were prepared (Figure 1, C→D). Removal

of CaCO_3 was confirmed by energy-dispersive x-ray analysis, in that no calcium was detected in the microcapsule samples. The use of CaCO_3 microparticles as templates is advantageous as compared with the use of PS or MF templates. Polyelectrolyte microcapsules made of PSS/PAH, were initially obtained by dissolving PS or MF microparticles under harsh conditions (e.g., pH 1.0). However, the removal of PS or MF has created problems in maintaining the integrity of the capsules,^{37,54} and drug molecules should be loaded after the dissociation of the templates. By contrast, the use of CaCO_3 microparticles as templates for polyelectrolyte microcapsules has shown great promise for biomedical applications, because CaCO_3 particles can easily be dissolved in mild conditions by EDTA, and can be loaded with drug molecules during or after their preparation. In addition, the developed PLL-CS multilayered microcapsules are superior, to some degree, to the recently reported CS microcapsules, which were continually produced in a multi-loop reactor and had an average diameter of 1.0 μm .⁵⁵ This is because the LBL technique (1) allows the formation of microcapsules of sizes from hundreds of nanometers to millimeters,^{2,32} (2) permits the control over the shell thickness (in the nanometer scale), composition, and density, and (3) allows the subsequent selective control of drug loading and release (Figures 4 and 6) by introducing a matrix (CS) within PLL-CS microcapsules.

It is known that the interior of polyelectrolyte microcapsules can be used to encapsulate proteins, nucleotides, antibiotics, or other biologically relevant molecules, because polyelectrolyte multilayers developed by LBL are porous⁵⁶ and drug molecules can penetrate in and out of the capsules.⁵⁷ Meanwhile, the physicochemical differences between the capsule interior and exterior can be used to control the capture of drug molecules inside the capsules. Immobilization of a matrix, such as CS macromolecules, inside polyelectrolyte microcapsules may modify the physical properties (type of charge, charge density, hydrophobicity) of the capsule interior from those of its exterior medium. This may allow selective control of subsequent drug loading and release. In this study, CS macromolecules were integrated inside the polyelectrolyte microcapsules, and the influence of pH on subsequent drug loading and release were investigated. We showed that FITC-BSA, a model protein drug, was loaded inside the CS-integrated microcapsules (Figure 5). Electrostatic interaction was the main driving force for BSA incorporation (Figure 1, $D \rightarrow E$), although other forces such as hydrophobicity might also play a role in drug loading, in that a small amount of FITC-BSA was loaded at pH 5.0 (Figure 4). The CS macromolecules inside the microcapsules are negatively charged, whereas BSA has no net charge at its isoelectric point (pI; i.e., pH 5.0 [ref.⁵⁸]) and has more net positive charges as the pH decreases. As a result, the microcapsules had the lowest loading of BSA at pH 5.0 (Figure 4) in the pH range 3.4 to 5.0. Therefore, by integrating CS macromolecules inside the capsules and by choosing the right pH conditions, charged

drug molecules (e.g., FITC-BSA) could be loaded into microcapsules, and more FITC-BSA was loaded into the CS-integrated microcapsules at a lower pH. The decrease of BSA loading at pH 3.4 compared with that of pH 3.8 might be associated with a possible structural change of BSA.

pH can also be used to trigger or tune the release of encapsulated drug molecules from CS-integrated microcapsules. Figure 6 shows that the encapsulated FITC-BSA could be released from the CS-integrated microcapsules and that its release was pH controlled. The concentration gradient between the microcapsule and its environment causes diffusion of FITC-BSA out of the microcapsule. It is believed that any release condition that weakens the interaction between BSA and the CS inside the microcapsule will lead to a faster releasing rate and higher releasing amount. The electrostatic attraction of BSA and CS decreases as pH increases from pH 1.0 to 7.4. This is because BSA has net negative charges above its pI (pH 5.0) and net positive charges below its pI, and CS is negatively charged. As a result, BSA and CS repel each other at a high pH (e.g., pH 7.4) and attract each other at a low pH (e.g., pH 1.0). This leads to a faster release of BSA at a higher pH (Figures 6, A and B).

In summary, a biodegradable drug delivery system with controllable loading and release properties was developed. We integrated CS macromolecules, intended to facilitate the control of subsequent drug loading and release via pH, into CaCO_3 particles during the preparation of the particles. We formed a multilayered shell on the CS-integrated CaCO_3 particle using LBL nanotechnology. After dissociation of the CaCO_3 templates, biopolymer multilayered microcapsules integrated with CS were obtained. A model drug (FITC-BSA) was loaded and its release studied. pH-controlled loading and release behavior was observed. Substantially more BSA was loaded at pH 3.8 than at pH 5.0 (i.e., pI of BSA), and the release of BSA was faster at a higher pH. With further research still to be done, CS-integrated biopolymer microcapsules seem promising for controlled drug delivery and other release applications.

Acknowledgments

The authors appreciate the use of the confocal laser scanning microscope at the Microscopic Imaging Facilities at West Virginia University Health Sciences Center. The authors also thank Suzanne Smith for proofreading.

References

1. Langer R, Tirrell DA. Designing materials for biology and medicine. *Nature* 2004;428:487-92.
2. Caruso F, Caruso R, Möhwald H. Nanoengineering of inorganic and hybrid hollow spheres by colloidal templating. *Science* 1998;282: 1111-4.
3. Donath E, Sukhorukov GB, Caruso F, Davis SA, Möhwald H. Novel hollow polymer shells by colloid-templated assembly of polyelectrolytes. *Angew Chem Int Ed Engl* 1998;37:2202-5.

4. De Geest BG, Sanders NN, Sukhorukov GB, Demeester J, De Smedt SC. Release mechanisms for polyelectrolyte capsules. *Chem Soc Rev* 2007;36:636-49.
5. Peyratout CS, Dähne L. Tailor-made polyelectrolyte microcapsules: from multilayers to smart containers. *Angew Chem Int Ed Engl* 2004;43:3762-83.
6. Berth G, Voigt A, Dautzenberg H, Donath E, Möhwald H. Polyelectrolyte complexes and layer-by-layer capsules from chitosan/chitosan sulfate. *Biomacromolecules* 2002;3:579-90.
7. Balabushevich NG, Tiourina OP, Volodkin DV, Larionova NI, Sukhorukov GB. Loading the multilayer dextran sulfate/protamine micro-sized capsules with peroxidase. *Biomacromolecules* 2003;4:1191-7.
8. Shenoy DB, Sukhorukov GB. Engineered microcrystals for direct surface modification with layer-by-layer technique for optimized dissolution. *Eur J Pharm Biopharm* 2004;58:521-7.
9. An ZH, Lu G, Möhwald H, Li JB. Self-assembly of human serum albumin (HSA) and L-alpha-dimyristoylphosphatidic acid (DMPA) microcapsules for controlled drug release. *Chem Eur J* 2004;10:5848-52.
10. Haynie D, Palath N, Liu Y, Li B, Pargaonkar N. Biomimetic nanotechnology: inherent reversible stabilization of polypeptide microcapsules. *Langmuir* 2005;21:1136-8.
11. Yu A, Wang Y, Barlow E, Caruso F. Mesoporous silica particles as templates for preparing enzyme-loaded biocompatible microcapsules. *Adv Mater* 2005;17:1737-41.
12. Zhi ZL, Haynie DT. High-capacity functional protein encapsulation in nanoengineered polypeptide microcapsules. *Chem Commun* 2006;37:147-9.
13. Caruso F, Möhwald H. Protein multilayer formation on colloids through a stepwise self-assembly technique. *J Am Chem Soc* 1999;121:6039-46.
14. Shchukin DG, Patel AA, Sukhorukov GB, Lvov YM. Nanoassembly of biodegradable microcapsules for DNA encasing. *J Am Chem Soc* 2004;126:3374-5.
15. De Geest BG, Dejgnat C, Prevot M, Sukhorukov GB, Demeester J, De Smedt SC. Self-rupturing and hollow microcapsules prepared from bio-polyelectrolyte-coated microgels. *Adv Funct Mater* 2007;17:531-7.
16. Itoh Y, Matsusaki M, Kida T, Akashi M. Enzyme-responsive release of encapsulated proteins from biodegradable hollow capsules. *Biomacromolecules* 2006;7:2715-8.
17. De Geest BG, Vandenbroucke RE, Guenther AM, Sukhorukov GB, Hennink WE, Sanders NN, et al. Intracellularly degradable polyelectrolyte microcapsules. *Adv Mater* 2006;18:1005-9.
18. Cortez C, Tomaskovic-Crook E, Johnston APR, Radt B, Cody SH, Scott AM, et al. Targeting and uptake of multilayered particles to colorectal cancer cells. *Adv Mater* 2006;18:1998-2003.
19. De Koker S, De Geest BG, Cuvelier C, Ferdinande L, Deckers W, Hennink WE, et al. In vivo cellular uptake, degradation, and biocompatibility of polyelectrolyte microcapsules. *Adv Funct Mater* 2007;17:3754-63.
20. Donath E, Moya S, Neu B, Sukhorukov GB, Georgieva R, Voigt A, et al. Hollow polymer shells from biological templates: fabrication and potential applications. *Chem Eur J* 2002;8:5481-5.
21. Lasic DD. *Liposomes: from physics to applications*. Amsterdam: Elsevier; 1993.
22. Li N, Kommireddy DS, Lvov YM, Liebenberg W, Tiedt LR, De Villiers MM. Nanoparticle multilayers: surface modification of photosensitive drug microparticles for increased stability and in vitro bioavailability. *J Nanosci Nanotechnol* 2006;6:3252-60.
23. Balabushevich NG, Sukhorukov GB, Moroz NA, Volodkin DV, Larionova NI, Donath E, et al. Encapsulation of proteins by layer-by-layer adsorption of polyelectrolytes onto protein aggregates: factors regulating the protein release. *Biotechnol Bioeng* 2001;76:207-13.
24. Marinakos SM, Anderson MF, Ryan JA, Martin LD, Feldheim DL. Encapsulation, permeability, and cellular uptake characteristics of hollow nanometer-sized conductive polymer capsules. *J Phys Chem B* 2001;105:8872-6.
25. Sukhorukov GB, Dähne L, Hartmann J, Donath E, Möhwald H. Controlled precipitation of dyes into hollow polyelectrolyte capsules based on colloids and biocolloids. *Adv Mater* 2000;12:112-5.
26. Ibarz G, Dähne L, Donath E, Möhwald H. Smart micro- and nanocontainers for storage, transport, and release. *Adv Mater* 2001;13:1324-7.
27. Gaponik N, Radtchenko IL, Sukhorukov GB, Weller H, Rogach AL. Toward encoding combinatorial libraries: charge-driven microencapsulation of semiconductor nanocrystals luminescing in the visible and near IR. *Adv Mater* 2002;14:879-82.
28. Shchukin DG, Sukhorukov GB, Möhwald H. Smart inorganic/organic nanocomposite hollow microcapsules. *Angew Chem Int Ed Engl* 2003;42:4472-5.
29. Gao CY, Leporatti S, Moya S, Donath E, Möhwald H. Swelling and shrinking of polyelectrolyte microcapsules in response to changes in temperature and ionic strength. *Chem Eur J* 2003;9:915-20.
30. Gao CY, Möhwald H, Shen JC. Enhanced biomacromolecule encapsulation by swelling and shrinking procedures. *Chem Phys Chem* 2004;5:116-20.
31. Zhu HG, Srivastava R, McShane MJ. Spontaneous loading of positively charged macromolecules into alginate-templated polyelectrolyte multilayer microcapsules. *Biomacromolecules* 2005;6:2221-8.
32. Sukhorukov GB, Rogach AL, Zebli B, Liedl T, Skirtach AG, Kohler K, et al. Nanoengineered polymer capsules: tools for detection, controlled delivery, and site-specific manipulation. *Small* 2005;1:194-200.
33. Dähne L, Leporatti S, Donath E, Möhwald H. Fabrication of micro reaction cages with tailored properties. *J Am Chem Soc* 2001;123:5431-6.
34. Radtchenko IL, Sukhorukov GB, Möhwald H. Incorporation of macromolecules into polyelectrolyte micro- and nanocapsules via surface controlled precipitation on colloidal particles. *Colloids Surfaces A* 2002;202:127-33.
35. Shenoy DB, Antipov AA, Sukhorukov GB, Möhwald H. Layer-by-layer engineering of biocompatible, decomposable core-shell structures. *Biomacromolecules* 2003;4:265-72.
36. Tong WJ, Dong WF, Gao CY, Möhwald H. Charge-controlled permeability of polyelectrolyte microcapsules. *J Phys Chem B* 2005;109:13159-65.
37. Gao C, Donath E, Möhwald H, Shen JC. Spontaneous deposition of water-soluble substances into microcapsules: phenomenon, mechanism, and application. *Angew Chem Int Ed Engl* 2002;41:3789-93.
38. Skirtach AG, Antipov AA, Shchukin DG, Sukhorukov GB. Remote activation of capsules containing Ag nanoparticles and IR dye by laser light. *Langmuir* 2004;20:6988-92.
39. Radt B, Smith TA, Caruso F. Optically addressable nanostructured capsules. *Adv Mater* 2004;16:2184-9.
40. Tao X, Li JB, Möhwald H. Self-assembly, optical behavior, and permeability of a novel capsule based on an azo dye and polyelectrolytes. *Chem-A Eur J* 2004;10:3397-403.
41. Angelatos AS, Radt B, Caruso F. Light-responsive polyelectrolyte/gold nanoparticle microcapsules. *J Phys Chem B* 2005;109:3071-6.
42. Lu ZH, Prouty MD, Guo ZH, Golub VO, Kumar CSSR, Lvov YM. Magnetic switch of permeability for polyelectrolyte microcapsules embedded with Co@Au nanoparticles. *Langmuir* 2005;21:2042-50.
43. Sukhorukov GB, Antipov AA, Voigt A, Donath E, Möhwald H. pH-controlled macromolecule encapsulation in and release from polyelectrolyte multilayer nanocapsules. *Macromol Rapid Commun* 2001;22:44-6.
44. Antipov AA, Sukhorukov GB, Leporatti S, Radtchenko IL, Donath E, Möhwald H. Polyelectrolyte multilayer capsule permeability control. *Colloids Surfaces A* 2002;198:535-41.
45. Dejgnat C, Halozan D, Sukhorukov GB. Defined picogram dose inclusion and release of macromolecules using polyelectrolyte microcapsules. *Macromolecular Rapid Commun* 2005;26:961-7.

46. Schuler C, Caruso F. Decomposable hollow biopolymer-based capsules. *Biomacromolecules* 2001;2:921-6.
47. Shchukin DG, Sukhorukov GB. Nanoparticle synthesis in engineered organic nanoscale reactors. *Adv Mater* 2004;16:671-82.
48. Brown JQ, Srivastava R, McShane MJ. Encapsulation of glucose oxidase and an oxygen-quenched fluorophore in polyelectrolyte-coated calcium alginate microspheres as optical glucose sensor systems. *Biosens Bioelectron* 2005;21:212-6.
49. De Geest BG, Jonas AM, Demeester J, De Smedt SC. Glucose-responsive polyelectrolyte capsules. *Langmuir* 2006;22:5070-4.
50. Zelikin AN, Quinn JF, Caruso F. Disulfide cross-linked polymer capsules: en route to biodeconstructible systems. *Biomacromolecules* 2006;7:27-30.
51. Yannas IV, Orgill DP, Skrabut EM, Burke JF. Skin regeneration with a bioreplaceable polymeric template. In: Gebelein CG, editor. *Polymeric materials and artificial organs*. Washington, DC: American Chemical Society; 1984. p. 191-7 [Chap 13].
52. Tong WJ, Gao CY, Möhwald H. Manipulating the properties of polyelectrolyte microcapsules by glutaraldehyde cross-linking. *Chem Mater* 2005;17:4610-6.
53. Zhao QH, Mao ZW, Gao CY, Shen JC. Assembly of multilayer microcapsules on CaCO₃ particles from biocompatible polysaccharides. *J Biom Sci Polym Ed* 2006;17:997-1014.
54. Dong WF, Ferri JK, Adalsteinsson T, Schonhoff M, Sukhorukov GB, Möhwald H. Influence of shell structure on stability, integrity, and mesh size of polyelectrolyte capsules: mechanism and strategy for improved preparation. *Chem Mater* 2005;17:2603-11.
55. Bubenikova S, Lacik I, Bakos D, Vodna L. Chitosan polyelectrolyte complexes for use in tissue engineering and drug delivery. *Mater Sci Forum* 2007;539-543:577-582.
56. Chung AJ, Rubner MF. Methods of loading and releasing low molecular weight cationic molecules in weak polyelectrolyte multilayer films. *Langmuir* 2002;18:1176-83.
57. Sukhorukov GB, Brumen M, Donath E, Möhwald H. Hollow polyelectrolyte shells: exclusion of polymers and Donnan equilibrium. *J Phys Chem B* 1999;103:6434-40.
58. Sundaram S. Protein adsorption in microporous membrane filtration. In: Meltzer TH, Jornitz MW, editors. *Filtration in biopharmaceutical industry*. New York: Informa Healthcare; 1997. p. 557.